


Lab on a Chip

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: Q. Chen, S. Utech, D. Chen, R. M. Prodanovic, J. Lin and D. A. Weitz, *Lab Chip*, 2016, DOI: 10.1039/C6LC00231E.

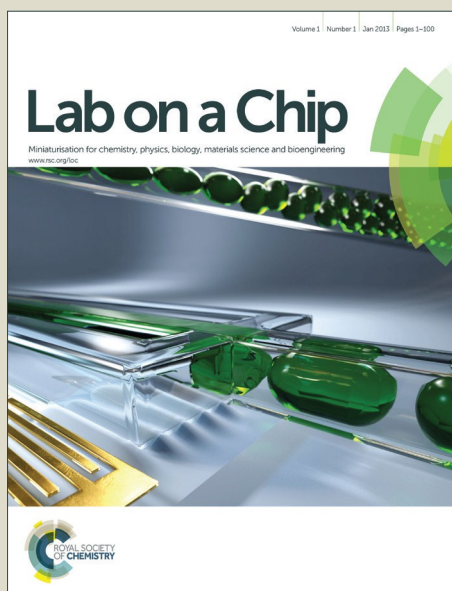

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Lab on a Chip

COMMUNICATION

Controlled Assembly of Heterotypic cells in a Core-Shell Scaffold:
Organ in a DropletReceived 00th January 2016,
Accepted 00th February 2016Qiushui Chen,^{a,b} Stefanie Utech,^b Dong Chen,^b Radivoje Prodanovic,^c Jin-Ming Lin,^{a*} and David A. Weitz^{b*}

DOI: 10.1039/x0xx00000x

www.rsc.org/

1 This paper reports a droplet-based microfluidics approach to
2 fabricate a large number of monodisperse, portable microtissues,
3 each in an individual drop. We use water-water-oil double
4 emulsions as templates and spatially assemble hepatocytes in the
5 core and fibroblasts in the shell, forming a 3D liver model in a droplet.

6 Nearly all tissues are integrated three-dimensional (3D) structures
7 of multiple types of cells and extracellular matrices (ECMs).^{1,2} The
8 function of a tissue is typically governed by multiple cues, ranging
9 from intercellular signalings to cell interactions with the
10 surrounding ECMs.³⁻⁶ Liver, for example, consists of primary
11 hepatocytes, hepatic stellate cells, Kupffer cells, endothelial cells
12 and fibroblasts, which are arranged in a 3D scaffold.⁷ Hepatocytes
13 alone show very low levels of liver-specific functions, because
14 conventional two-dimensional (2D) cultures of a monolayer of the
15 cells on a plastic dish are poor mimics of tissues found in vivo.⁸
16 Instead, improved functionality of liver tissue mimics requires the
17 development of 3D models that consist of simplified but similar
18 scaffolds with multiple types of cells embedded in ECMs and that
19 express improved functionality.⁹⁻¹²

20 Well-defined spatial distributions of different cells in 3D
21 architectures made of biocompatible ECMs are required to
22 construct artificial tissues that mimic the *in vivo* microenvironment.
23 Miniaturized, multiwell culture systems,¹³⁻¹⁵ 3D cell printing,^{16,18}
24 and 3D cell molding,¹⁹ have each been used to develop 3D artificial
25 liver models. In each case, hepatocytes are co-cultured with other
26 cells in micro-patterned 3D scaffolds; they are separated in space
27 while close enough to each other that they can interact
28 biochemically. Therefore, different cells are able to coordinate both
29 homotypic and heterotypic cell-cell interactions and show improved
30 liver-specific functions.²⁰⁻²² However, these technologies are limited

in terms of uniformity, portability and quantity; versatile human
microtissues composed of different cells in precisely controlled 3D
structures are, as yet, unavailable.

Droplet-based microfluidics can produce monodisperse
droplets whose size can be precisely controlled and whose internal
structure can be tailored to incorporate different cells in designated
locations.²³⁻²⁶ However, previous microfluidic-based research
focused on biocompatible hydrogel microparticles templated from
single water-in-oil (w/o) emulsions.²⁷⁻³¹ These would lead to over-
simplified 3D cellular microenvironment with limitations both in
terms of impaired cell-cell contact and undefined spatial
distribution of different cells in the drops. More sophisticated
structures with well-defined 3D architectures are, therefore,
required.

In this paper, we report the first study of reconstituting “organ
in a droplet” by controlled assembly of heterotypic cells in
biocompatible 3D core-shell hydrogel scaffolds. We use droplet-
based microfluidics to produce highly monodisperse structures that
enable multiple types of cells to be optimally arranged to create an
artificial liver in a drop. We produce water-water-oil (w/w/o)
double emulsions which we use as templates to successfully
integrate the 3D core-shell scaffold with hepatocytes in the core
surrounded by fibroblasts in the shell. We cross-link the shell of
alginate hydrogel by triggered release of calcium cations; this
method avoids exposure to harsh environments during fabrication
and creates structures with good integrity and high permeability.
Hepatocytes and fibroblasts co-cultured in the drop develop both
homotypic and heterotypic cell-cell interactions, which cannot be
achieved in a 2D culture system. Albumin secretion and urea
metabolism, which are good assays of liver-specific functions, both
exhibit higher activity in the microtissues as compared to that in
hepatocytes alone.

To construct the core-shell scaffolds, we use w/w/o double
emulsions as templates and generate core-shell droplets in a flow-
focusing microfluidic device, as shown in **Figure 1**. The inner phase
is cell culture medium and the middle phase is alginate aqueous
solution, a well-studied biocompatible polymer that shows
excellent cell function and survival in the network.³² The inner
phase co-flows with the middle phase due to their low Reynolds

^a Department of Chemistry, Tsinghua University, Beijing 100084, P.R.China E-mail:
jmlin@tsinghua.edu.cn.

^b John A. Paulson School of Engineering and Applied Sciences, Department of
Physics, Harvard University, Cambridge, MA 02139, USA E-mail:
weitz@seas.harvard.edu.

^c Faculty of Chemistry, University of Belgrade, Studentski trg 12, Belgrade, Serbia.

*Electronic Supplementary Information (ESI) available: Preparation of the core-shell scaffold, controlled assembly of multiple cells into the 3D scaffold, cell viability analysis, morphology characterization and biomarker measurements. See
DOI: 10.1039/x0xx00000x

numbers; a fluorinated carbon oil at the cross-junction for
monodisperse droplets consisting of an aqueous core and
hydrogel shell (Figures 1b and c). Instead of cross-linking by
exposure, which is generally harmful to cells, we introduce
additional oil flow containing 0.15% acetic acid downstream and
trigger release of Ca^{2+} from the Ca-EDTA complex in the alginate
solution; the divalent Ca^{2+} subsequently binds to two different
carboxylic groups of alginate chains, forming a cross-linked
network (Figure 1a). The *in situ* cross-linking locks alginate in the
shell, which is directly visualized with fluorescent confocal
microscopy by labeling alginate with fluorescein (see Supporting
Information, Scheme S1), as shown in the inset of Figure 1d. Using
these w/w/o double emulsions as templates, we are able to
fabricate a large number of monodisperse core-shell droplets with
well-controlled internal structure (Diameter = $169 \pm 6 \mu\text{m}$, see
Supporting Information, Figure S1).

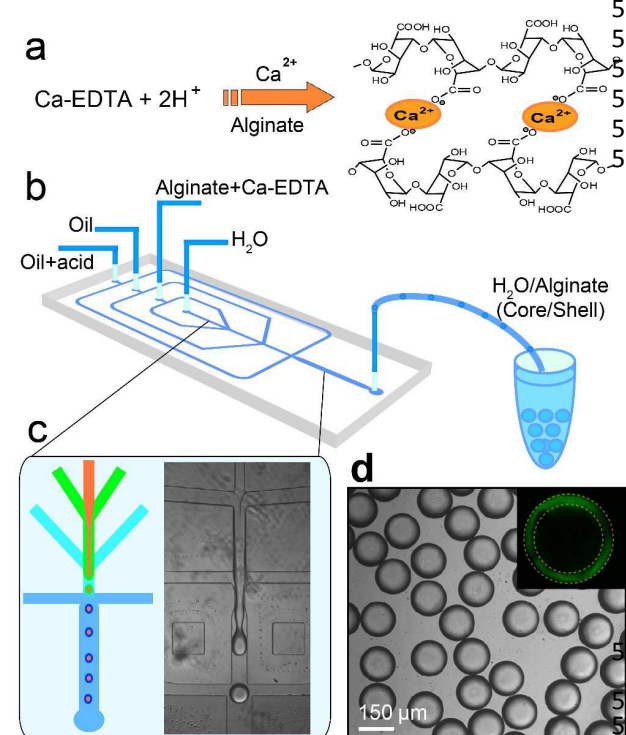


Figure 1. Construction of 3D scaffold in a drop consisting of an aqueous core and a hydrogel shell. a) Cross-link of alginate network by triggered release of Ca^{2+} from Ca-EDTA complex. b) Schematic diagram of the PDMS device. c) Fabrication of core-shell droplets using w/w/o double emulsions as templates. d) Monodisperse core-shell droplets generated using the droplet-based microfluidics. The shell of alginate hydrogel is clearly identified under confocal microscope when alginate is labeled with fluorescein, as shown in the inset.

To assemble hepatocytes in the core, we suspend hepatocytes in the cell culture medium and inject them with the inner phase (see Supporting Information, Figure S2). Hepatocytes are subsequently encapsulated in the core by the hydrogel shell and they start to form aggregates after several days' culture, as shown in Figure 2a. The aggregate is a common phenotype of healthy

hepatocytes and is clear proof of direct cell-cell contacts due to homotypic cell-cell interactions. Similarly, we distribute fibroblasts in the shell by premixing them with the alginate solution and injecting them with the middle phase (see Supporting Information, Figure S3). The fibroblasts are then confined in the shell by the cross-linked alginate network and there are no cells observed in the core, as shown in Figure 2b. Random co-cultures of hepatocytes and fibroblasts in the same compartment will have lower liver-specific functions due to the lost balance of homotypic and heterotypic cell-cell interactions;¹³ therefore, to mimic the 3D structure of human liver *in vivo* and to develop an artificial liver in each drop, we simultaneously assemble hepatocytes (HepG2 cells) in the core surrounded by fibroblasts (NIH-3T3 cells) in the shell, forming a spheroid of different cells embedded in a 3D ECM (see Supporting Information, Figure S4 and Movie S1). In our study, the heterocellular spheroids are generated by one-step *in situ* cross-linking of alginate in the shell, after which the spheroids are quickly transferred to cell culture medium. The exposure of cells to mild acidic conditions during the whole process is limited and has little effect on the viability of cells, as evidenced by the predominance of live cells (green) and the complete lack of any dead cells (red) in the live-dead assay, as shown in Figure 2c.

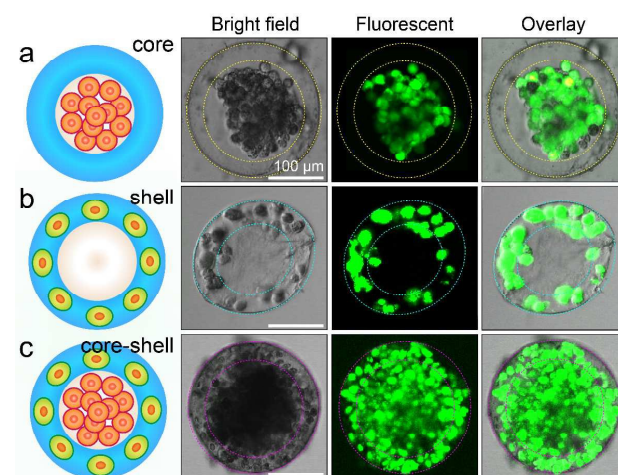


Figure 2. Spatial assembly of different cells in the 3D core-shell scaffold. a) HepG2 cells confined in the core by the hydrogel shell. b) NIH-3T3 fibroblasts immobilized by the cross-linked alginate network in the shell. c) Simultaneous assembly of hepatocytes in the core and fibroblasts in the shell, forming an artificial liver in a drop. Cell viability is characterized by Calcein AM/EthD-1 staining kit. The scale bars are 100 μm .

We culture the core-shell spheroids in the medium at 37°C. The spheroids maintain their spherical shape even for two weeks' culture, during which time the cells grow denser, as shown in Figures 3a-c. The distinct spherical shape is also observed in freeze-dried samples using scanning electron microscopy, as shown in Figure 3d and magnified in Figure 3e. Moreover, the cross-section of a freeze-dried spheroid reveals dense cell aggregates in the core and dispersed cells in the shell, as shown in Figure 3f. These observations suggest that the hydrogel shell of cross-linked alginate is mechanically strong. This strength, together with the portability of each microtissue in a drop enables us to store them at -80°C,

thaw them at 37°C and culture them again without destroying the structure or affecting the viability of cells, as shown in Figure 3. While the shell of alginate hydrogel is robust, it is also highly permeable, enabling nutrients and metabolites to pass through; therefore, cells in the spheroids can be cultured for long periods of time, as evidenced by the high viability of cells cultured in the spheroids. After 10 days' culture, cells are predominantly alive (green) and there is complete lack of dead cells (red), as revealed by a live-dead staining kit (Figure 3h). During the period, cells have grown denser. However, because cells can't attach to unmodified alginate network, cells can't migrate from one layer to the other over time. Therefore, hepatocytes and fibroblasts remain spatially separated, which is beneficial for their liver-specific functions. Even after 14 days, a slight decrease in cell viability is observed; the percentage of dead cells is about 34%, as shown in Figure 3i. It is possible that a hypoxic core developed at day 14 due to cell proliferation and the resulting high cell density.

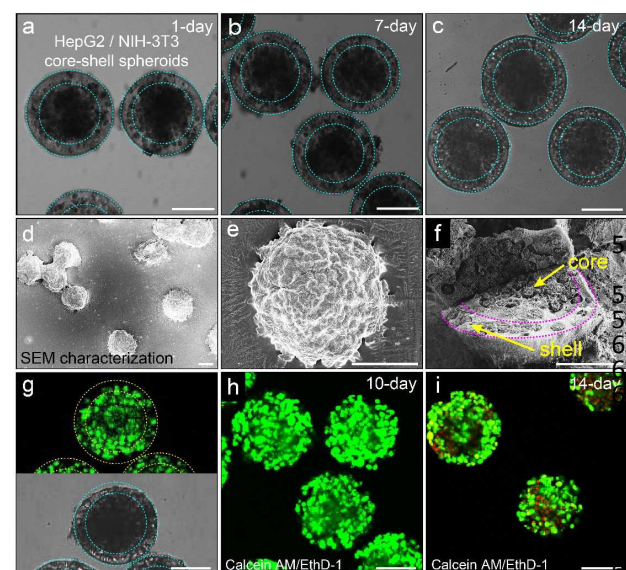


Figure 3. Co-culture of hepatocytes and fibroblasts in the core-shell spheroids. Morphology of the heterocellular spheroids and viability of the cells in the hydrogel scaffold. a-c) Co-culture of hepatocytes in the core and fibroblasts in the shell for 1 day, 7 days and 14 days, respectively. The heterocellular spheroids maintain their spherical morphology over time. d-f) SEM image and e) magnified image show individual spheroids that maintain their structural integrity after freeze-drying. f) Spatially confined cell ensembles in the core-shell structure. g) High viability of cells encapsulated in the spheroids after being frozen at -80°C for two weeks and then thawed at 37°C. Cells are predominantly alive (green) and there is complete lack of dead cells (red). h) Co-culture of cells encapsulated in the spheroids for 7 days shows high cell viability. i) The viability of cells cultured for 14 days decreases slightly, as evidenced by the appearance of dead cells (red). Cell viability is characterized by Calcein AM/EthD-1 staining kit. The scale bar is 100 μm in all images.

To measure the liver-specific functions of the microtissues in each drop, we monitor their albumin secretion and urea synthesis over time; the two metabolites are key biomarkers of the liver and this response has been widely used in drug screening.³³ We culture two samples with same amount of hepatocytes, one in the core-shell

structure with fibroblasts in the shell and the other without fibroblasts, and monitor the concentration of albumin and urea in the medium using albumin and urea assay kits, respectively. Compared to monotypic culture of hepatocytes alone, co-culture of hepatocytes and fibroblasts in the core-shell spheroids displays both increased albumin secretion and urea synthesis, as shown in Figures 4a and b. The enhanced liver-specific functions substantially differentiate our 3D microscale co-culture from conventional monotypic cell culture (statistically significant, * $p < 0.01$). These results suggest that co-culture of hepatocytes and fibroblasts embedded in the 3D core-shell scaffold is a good model of the liver *in vitro* and has a balance of homotypic and heterotypic cell-cell interactions, which are beneficial for the expressions of their liver-specific functions. High-throughput assays of human tissue responses using these uniform, portable microtissues, each in a drop, will be valuable for rapid assessment of drugs, chemicals and cosmetics.

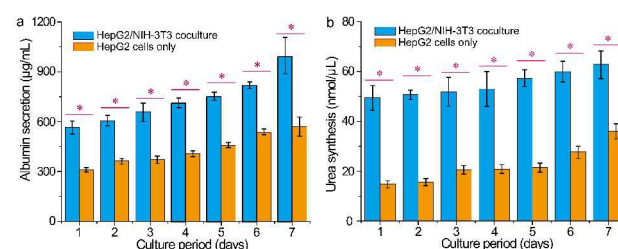


Figure 4. Comprehensive assays of liver-specific functions of hepatocyte/fibroblast co-culture and hepatocyte culture. a) Albumin secretion and b) urea synthesis of HepG2/NIH-3T3 co-culture and HepG2 culture measured over seven days. The liver-specific functions enhanced by the co-culture of hepatocytes and fibroblasts in the 3D core-shell spheroids are statistically significant (* $p < 0.01$).

Conclusions

We use droplet-based microfluidics and hierarchically assemble hepatocytes and fibroblasts into a 3D core-shell scaffold, forming an artificial liver in each drop. The strong mechanical property and high permeability of the hydrogel shell enable cells in the spheroids to be cultured for long periods of time. Within the optimized microscale structure that promotes both homotypic and heterotypic cell-cell interactions, co-culture of hepatocytes in the core surrounded by fibroblasts in shell successfully expresses high-level liver-specific functions. Thousands of monodisperse microtissues, each in an individual drop, are achievable using the microfluidics technology, and each maintains enhanced liver-specific functions. In addition, hepatocytes and fibroblasts can easily be replaced with other cells to construct other tissue models and study cell-to-cell interaction in general. Thus, these structures are a promising *in vitro* liver model for high-throughput drug screening assays.^{34,35}

COMMUNICATION

Lab on a Chip

1 Acknowledgements

2 Q. Chen acknowledges the China Scholarship Council (2012[30131])
 3 and the staff of *Experimental Soft Condensed Matter* at Harvard
 4 University. This work was financially supported by the National
 5 Natural Science Foundation of China (Nos. 214350002, 912133056
 6 and 81373373) and China Equipment and Education Resources
 7 System (No. CERS-1-75). This work was also supported by the
 8 National Science Foundation (DMR-1310266), by the
 9 Harvard Materials Research Science and Engineering
 10 Center (DMR-1420570) and the National Institutes of Health
 11 (R01EB014703). S. Utech was supported by Deutsche
 12 Forschungsgemeinschaft.

13 References

- 14 1 E. S. Place, N. D. Evans, M. M. Stevens, *Nat. Mater.* **2009**, *8*,
 15 457-470.
- 16 2 J. M. Grolman, D. Zhang, A. M. Smith, J. S. Moore, and K. A.
 17 Kilian, *Adv. Mater.* **2015**, *27*, 5512.
- 18 3 V. Vogel, M. Sheetz, *Nature Reviews Molecular Cell Biology*
 19 **2006**, *7*, 265.
- 20 4 W. P. Daley, S. B. Peters, M. Larsen, *Journal of Cell Science*
 21 **2008**, *121*, 255.
- 22 5 F. Klein, B. Richter, T. Striebel, C. M. Franz, G. von Freymann
 23 M. Wegener, M. Bastmeyer, *Adv. Mater.* **2011**, *23*, 1341.
- 24 6 T. P. Kraehenbuehl, R. Langer, L. S. Ferreira, *Nat. Methods*
 25 **2011**, *8*, 731.
- 26 7 Z. Kmiec, *Adv. Anat. Embryol. Cell Biol.* **2001**, *161*, 1.
- 27 8 X. Gidrol, B. Fouque, L. Ghenim, V. Haguët, N. Picollet-
 28 D'hahan, B. Schaack, *Current Opinion in Pharmacology* **2009**, *9*,
 29 664.
- 30 9 F. T. Moutos, L. E. Freed, F. Guilak, *Nat. Mater.* **2007**, *6*, 16283
- 31 10 S. F. Wong, D. Y. No, Y. Y. Choi, D. S. Kim, B. G. Chung, S. H.
 32 Lee, *Biomaterials* **2011**, *32*, 8087.
- 33 11 Q. Chen, J. Wu, Q. C. Zhuang, X. X. Lin, J. Zhang, J.-M. Lin, *S*
 34 *Rep.* **2013**, *3*, 2433.
- 35 12 J. El-Ali, P. K. Sorger, K. F. Jensen, *Nature* **2006**, *442*, 403.
- 36 13 S. R. Khetani, S. N. Bhatia, *Nat. Biotechnol.* **2008**, *26*, 120.
- 37 14 Y. Nakao, H. Kimura, Y. Sakai, and T. Fujii, *Biomechanics*
 38 **2011**, *5*, 022212.
- 39 15 B. J. Kane, M. J. Zinner, M. L. Yarmush, and M. Toner, *Anal.*
 40 *Chem.* **2006**, *78*, 4291.
- 41 16 M. Matsusaki, K. Sakaue, K. Kadowaki, M. Akashi,
 42 *Adv. Healthcare Mater.* **2013**, *2*, 534.
- 43 17 S. V. Murphy, A. Atala, *Nat. Biotechnol.* **2014**, *32*, 773.
- 44 18 J. O. Hardin, T. J. Ober, A. D. Valentine, and J. A. Lewis, *Adv*
 45 *Mater.* **2015**, *27*, 3279.
- 46 19 Y. T. Matsunaga, Y. Morimoto, S. Takeuchi, *Adv. Mater.* **2019**
 47 *23*, H90;
- 48 20 A. Khademhosseini, R. Langer, J. Borenstein, J. P. Vacanti,
 49 *Proc. Natl. Acad. Sci. U.S.A.* **2006**, *103*, 2480.
- 50

- 51 21 B. Guillotin, F. Guillemot, *Trends in Biotechnol.* **2011**, *29*, 183.
- 52 22 C. H. Cho, J. Park, A. W. Tilles, F. Berthiaume, M. Toner, and
 53 M. L. Yarmush, *Biotechniques* **2010**, *48*, 47.
- 54 23 C. Kim, S. Chung, Y. E. Kim, K. S. Lee, S. H. Lee, K. W. Oh, J. Y.
 55 Kang, *Lab Chip* **2011**, *11*, 246.
- 56 24 S. Utech, R. Prodanovic, A. S. Mao, R. Ostafe, D. J. Mooney,
 57 D. A. Weitz, *Adv. Healthcare Mater.* **2015**, *4*, 1628.
- 58 25 H. N. Joensson, H. A. Svahn, *Angew. Chem. Int. Ed.* **2012**, *51*,
 59 12176.
- 60 26 D. M. Headen, G. Aubry, H. Lu, and A. J. García, *Adv. Mater.*
 61 **2014**, *26*, 3003.
- 62 27 M. T. Guo, A. Rotem, J. A. Heyman, D. A. Weitz, *Lab Chip*
 63 **2012**, *12*, 2146.
- 64 28 T. Rossow, J. A. Heyman, A. J. Ehrlicher, A. Langhoff, D. A.
 65 Weitz, R. Haag, S. Seiffert, *J. Am. Chem. Soc.* **2012**, *134*, 4983.
- 66 29 R. Novak, Y. Zeng, J. Shuga, G. Venugopalan, D. A. Fletcher,
 67 M. T. Smith, R. A. Mathies, *Angew. Chem. Int. Ed.* **2011**, *50*, 390.
- 68 30 D. Steinhilber, T. Rossow, S. Wedepohl, F. Paulus, S. Seiffert,
 69 R. Haag, *Angew. Chem. Int. Ed.* **2013**, *52*, 13538.
- 70 31 L. Yu, S. M. Grist, S. S. Nasser, E. Cheng, Y.-C. E. Hwang, C. Ni,
 71 and K. C. Cheung, *Biomechanics* **2015**, *9*, 024118.
- 72 32 A. D. Augst, H. J. Kong, D. J. Mooney, *Macromol. Biosci.* **2006**,
 73 *6*, 623.
- 74 33 B. E. Uygun, A. Soto-Gutierrez, H. Yagi, M.-L. Izamis, M. A.
 75 Guzzardi, C. Shulman, J. Milwid, N. Kobayashi, A. Tilles, F.
 76 Berthiaume, M. Hertl, Y. Nahmias, M. L. Yarmush and K. Uygun,
 77 *Nat. Med.* **2010**, *16*, 814.
- 78 34 E. W. Esch, A. Bahinski, D. Huh, *Nat. Rev. Drug Discov.* **2015**,
 79 *14*, 248.
- 80 35 Q. Chen, Z. He, W. Liu, X. Lin, J. Wu, H. Li, J.-M. Lin, *Adv.*
 81 *Healthcare. Mater.* **2015**, *4*, 2291-2296
- 82
- 83
- 84
- 85
- 86
- 87
- 88
- 89
- 90
- 91
- 92
- 93
- 94
- 95
- 96
- 97
- 98
- 99
- 100
- 101
- 102

The table of contents

Organ in a Drop: We use droplet-based microfluidics to fabricate large-scale, monodisperse, portable micro organ, each in an individual drop. We spatially assemble hepatocytes and fibroblasts in a biocompatible core-shell scaffold, forming an artificial liver in each drop. These micro livers express enhanced liver-specific functions and are valuable for high throughput drug assays.

