


Chem Soc Rev

Chemical Society Reviews

rsc.li/chem-soc-rev

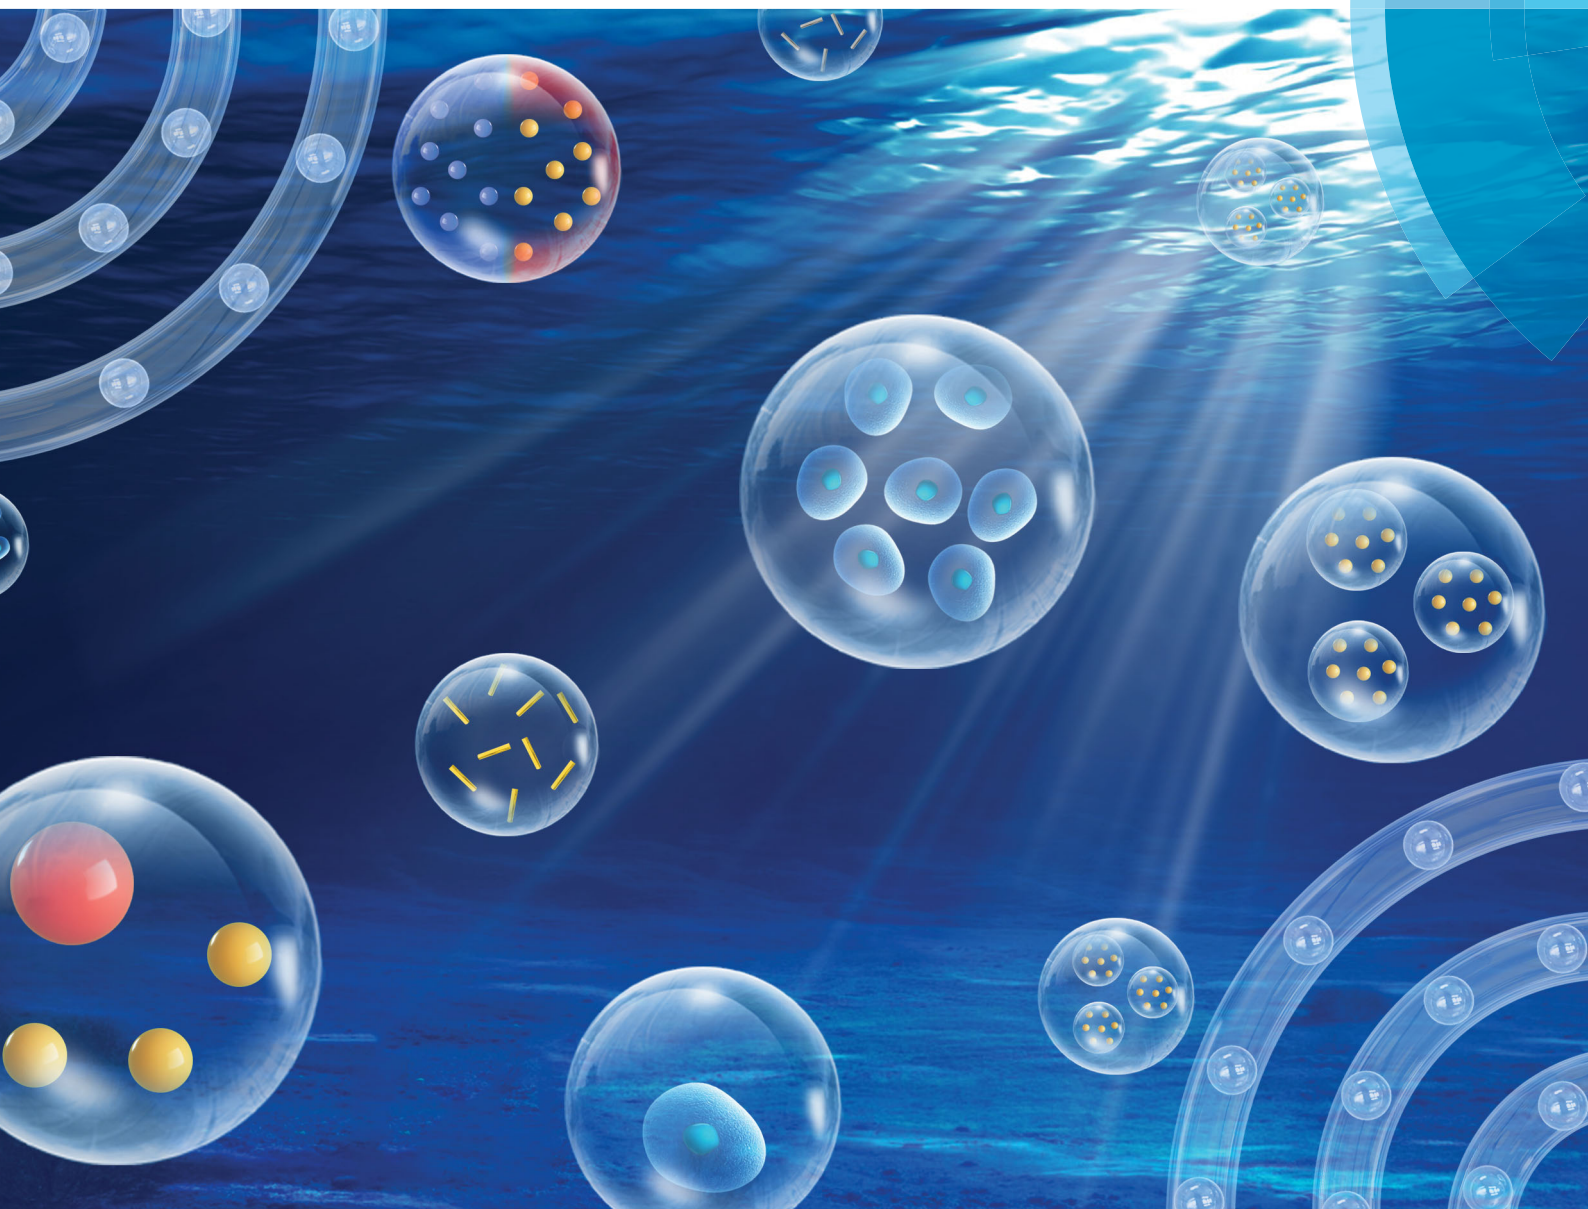

ISSN 0306-0012



REVIEW ARTICLE

Wen Li, Hyomin Lee, David A. Weitz *et al.*

Microfluidic fabrication of microparticles for biomedical applications



Cite this: *Chem. Soc. Rev.*, 2018, 47, 5646

Microfluidic fabrication of microparticles for biomedical applications

Wen Li, ^{†*ab} Liyuan Zhang,^{†b} Xuehui Ge,^{†bc} Biyi Xu, ^{bd} Weixia Zhang, ^b Liangliang Qu,^b Chang-Hyung Choi, ^{be} Jianhong Xu, ^c Afang Zhang, ^a Hyomin Lee ^{*bf} and David A. Weitz ^{*b}

Droplet microfluidics offers exquisite control over the flows of multiple fluids in microscale, enabling fabrication of advanced microparticles with precisely tunable structures and compositions in a high throughput manner. The combination of these remarkable features with proper materials and fabrication methods has enabled high efficiency, direct encapsulation of actives in microparticles whose features and functionalities can be well controlled. These microparticles have great potential in a wide range of bio-related applications including drug delivery, cell-laden matrices, biosensors and even as artificial cells. In this review, we briefly summarize the materials, fabrication methods, and microparticle structures produced with droplet microfluidics. We also provide a comprehensive overview of their recent uses in biomedical applications. Finally, we discuss the existing challenges and perspectives to promote the future development of these engineered microparticles.

Received 8th April 2018

DOI: 10.1039/c7cs00263g

rsc.li/chem-soc-rev

^a School of Materials Science & Engineering, Department of Polymer Materials, Shanghai University, 333 Nanchen Street, Shanghai 200444, China. E-mail: wli@shu.edu.cn

^b School of Engineering and Applied Sciences, Department of Physics, Harvard University, 29 Oxford Street, Cambridge, MA 02138, USA. E-mail: weitz@seas.harvard.edu

^c The State Key Laboratory of Chemical Engineering, Tsinghua University, Gongwuguan 772, Haidian District, Beijing 100084, China

^d State Key Laboratory of Analytical Chemistry for Life Science and Collaborative Innovation Center of Chemistry for Life Sciences, School of Chemistry and Chemical Engineering, Nanjing University, Nanjing 210023, China

^e Division of Cosmetic Science and Technology, Daegu Haany University, Gyeongsan, Gyeongbuk 38610, Republic of Korea

^f Department of Chemical Engineering, Pohang University of Science and Technology (POSTECH), 77 Cheongam-Ro, Nam-Gu, Pohang, Gyeongbuk 37673, Republic of Korea. E-mail: hyomin@postech.ac.kr

[†] These authors contributed equally to this work.



Wen Li

Wen Li received her PhD in Polymer Chemistry from Swiss Federal Institute of Technology in Zürich (ETH Zürich) in 2010. She then joined the School of Materials Science & Engineering, Shanghai University, China, where she is currently an associate professor of polymer chemistry and materials. Since 2016, she has worked as a visiting researcher in the group of Prof. David A. Weitz in the School of Engineering and Applied Sciences and Department of

Physics at Harvard University. Her research interests include topological polymers, hydrogel-based biomaterials and droplet microfluidics technology for microparticles fabrication.



Liyuan Zhang

Liyuan Zhang received her PhD in Polymer Chemistry & Physics from Jilin University, Changchun, China in 2014. Since then, she has worked as a postdoctoral researcher in School of Engineering and Applied Sciences at Harvard University under the supervision of Prof. David A. Weitz. Her research focuses on smart encapsulation and delivery systems, biomaterials for tissue engineering and lithium batteries.

1. Introduction

Microparticles with sizes ranging from 1 μm to 1000 μm have emerged as advanced functional materials for a wide range of biomedical applications, such as drug delivery, tissue engineering, biosensing, and cellular life science.^{1–3} These applications of microparticles depend on their properties which correlate with their size, structure, composition and configuration. Therefore, it is essential to fabricate microparticles in a controlled manner to improve their pharmaceutical capability and reliability for biological studies.^{4–6} However, it has long been a challenge to produce microparticles with such desired properties through conventional methods including emulsion polymerization, dispersion polymerization and spray drying.⁷ These methods normally result in microparticles with large polydispersity, poor

reproducibility, limited functionality, and less tunable morphology. To overcome these limitations, various technologies, including droplet microfluidics, flow lithography microfluidics, electrohydrodynamic co-jetting, photolithography, and soft lithography-based imprinting and micromolding have recently been explored for tailored fabrication of microparticles.^{8–10}

Among these, droplet microfluidics is one of the most effective techniques, as it offers exquisite control over multiple fluids at the microscale. Therefore, it allows precise tuning of the compositions and geometrical characteristics of microparticles.^{11,12} Exploiting these advantages, engineered microparticles with controlled sizes, monodispersity, diverse morphologies, and specific functions can be generated, and are playing an increasingly important role in biomedical fields.^{5,13} For instance, as drug delivery vehicles,^{6,14,15} microcapsules or multi-core



From left to right: Biyi Xu, Weixia Zhang, Liangliang Qu, Chang-Hyung Choi, Jianhong Xu and Afang Zhang

Biyi Xu obtained her PhD in analytical chemistry at Nanjing University in 2013 and is now an associate researcher there. In 2017, she joined the Weitz lab at Harvard University as a visiting scholar. Her research focuses on developing microfluidic platforms for high throughput single cell and organoid profiling with combined optical, electrochemical and mass spectrometric analysis. Weixia Zhang received his PhD from Purdue University in 2014. He is a postdoctoral researcher in the Weitz lab at Harvard University. His research focuses on surface chemistry, biomedical materials and microfluidics. Liangliang Qu received her PhD from Sichuan University in 2010. She is a postdoctoral researcher in the Weitz lab at Harvard University. Her research interests include high-performance functional materials and microfluidics. Chang-Hyung Choi received his PhD from Chungnam National University and was a postdoctoral researcher at Harvard University from 2014 to 2016. He is currently an assistant professor at Daegu Haany University (DHU). His research focuses on the development of functional materials by microfluidic systems. Jianhong Xu received his PhD from Tsinghua University in 2007 and is now on the faculty there. In 2016, he received an awarded as a Young Scholar of “Chang Jiang Scholars Program of China” of the MOE. His research focuses on microstructured chemical systems and multiphase microfluidic technology. Afang Zhang received his PhD from Peking University in 1999. He is a distinguished professor at Shanghai University and leads a group working on polymer chemistry and biomimetic materials.



Xuehui Ge

Xuehui Ge received her PhD in Chemical Engineering from Tsinghua University in 2018. From 2016 to 2017, she was supported by the China Scholarship Council as a visiting student in the group of Prof. David A. Weitz at Harvard university. She will move to the college of chemical engineering, Fuzhou University in 2018, as an associate professor. Her research interests include multiphase emulsions formation, morphology design and their applications in chemical reaction and bio-related fields.



Hyomin Lee

Hyomin Lee received his PhD in Chemical Engineering from Massachusetts Institute of Technology (MIT). Then, he worked as a postdoctoral researcher in School of Engineering and Applied Sciences at Harvard University from 2014 to 2017. In 2017, he moved to Pohang University of Science and Technology (POSTECH), where he is currently an assistant professor in the department of chemical engineering. His research focuses on the use of microfluidic tools to understand and control the structure and dynamics of soft matter at interfaces and engineer new functional materials.

microparticles can be prepared with well-defined structures and compositions that allow for high encapsulation efficiency and well-controlled release of the encapsulants. As cell carriers,¹⁶ hydrogel microparticles can be produced to act as extracellular matrix (ECM) to protect cells from the surrounding environment and maintain efficient nutrient and metabolic exchanges for long term cell culture. As a result, these cell-laden microparticles have direct applications in tissue engineering,¹⁷ stem cell therapy,¹⁸ and single cell studies.¹⁹ In addition, liposomes or polymersomes with multicompartment structures can be generated by droplet microfluidics in an exquisite and facile manner, making them ideal candidates for artificial cells.^{20,21} Furthermore, tremendous effort has been expended on exploring new droplet microfluidic system as well as materials chemistry to produce microparticles with good biocompatibility, rich functionalities, and high production rates. This leads to new and exciting opportunities for further development in their use for advanced diagnostics and therapeutics.

In this review, we provide an overview of microparticles fabricated by droplet microfluidics, and highlight the most recent progress in biomedical fields. We introduce the droplet formation mechanism and describe devices used to generate various types of droplets. We summarize methods to prepare microparticles templated from these droplets and emphasize the unique and complex structures enabled by microfluidic techniques. We then describe the biomedical applications of these microparticles, focusing on recent advancements in their use as drug delivery vehicles and cell-laden matrices. Other applications including biosensors and artificial cells are also briefly described. Lastly, we discuss the existing challenges that can potentially impact the practical use of these microparticles and conclude with perspectives and potential implications.

2. Droplet generation

In droplet microfluidics, properties of immiscible fluids are exploited at a microscale to generate and manipulate droplets.²² To produce droplets that meet the sophisticated requirements in biomedical applications, microfluidic chips that allow precise manipulation of fluidic elements on a small length scale are

required. In this section, we first discuss the mechanisms of droplet formation and various device geometries used for droplet generation. Then, we describe two of the most widely used microfluidic devices including glass capillary devices and lithographically fabricated poly(dimethylsiloxane) (PDMS) devices for generating various types of emulsion droplets from single emulsions to double emulsions and to even more complex emulsions. Lastly, other devices made from materials that have high stability and tolerate harsh operating conditions, as well as technologies for large scale production are discussed.

2.1 Droplet generation mechanism

An emulsion is a mixture of two immiscible liquids where one liquid is dispersed in another immiscible liquid. Most conventional methods for generating emulsions involve droplet breakup using shear or impact stresses generated by agitation. However, due to the nonuniform shear stresses applied, the resulting emulsions are highly polydisperse in size. In contrast, microfluidic devices offer an alternate and versatile route to produce emulsions.^{11,23} An emulsion is produced in a microfluidic device by precisely fabricating one drop at a time. This process is an outcome of a well-controlled balance between various forces acting on the fluid flow. These forces include inertial force, viscous force, interfacial tension, and buoyancy. In some cases, external forces such as electric,^{24,25} magnetic,^{26,27} and centrifugal forces²⁸ are also utilized. The balance of these forces determines the fluid behaviour and thus the mechanism of droplet formation. Typically, in microfluidic systems, buoyancy is small compared to interfacial and viscous forces during droplet formation due to the relatively small channel size, flow velocity and droplet volume. Therefore, the complex phenomenon of droplet breakup is determined by various dimensionless numbers, which are related to the fluid properties, channel geometries, and the flow conditions. Capillary number (C_a) and Weber number (W_e) are two main dimensionless numbers that determine the flow behavior in the channel. The capillary number represents the relative effect of viscous forces and surface tension, while the Weber number reflects the balance between inertial and surface tension forces. For instance, in a single emulsion system comprising of a dispersed phase and a continuous phase, C_a of the continuous phase and W_e of the dispersed phase are typically low, yielding formation of droplets one by one, which is the dripping mode.

While there are various modes of droplet breakup including squeezing, dripping, jetting, tip-streaming,²⁹ and tip-multi-breaking,³⁰ the dripping mode is most widely utilized due to the high monodispersity of the droplets generated. In this mode, the size of droplets can be tuned by changing the tip size and the flow rates of the fluid phases. Moreover, droplets within droplets dispersed in a third continuous phase, or double emulsions, and even higher order multi-phase (multiple) emulsions with tunable size, morphology, and the number of inner drops, can be produced. More detailed descriptions about droplet formation mechanism and their relationships to various dimensionless numbers can be found in other reviews.^{31,32}



David A. Weitz

David Weitz received his PhD in Physics from Harvard University and then joined Exxon Research and Engineering Company, where he worked for nearly 18 years. He then became a professor of physics at the University of Pennsylvania and moved to Harvard at the end of the last millennium as professor of physics and applied physics. He leads a group studying soft matter science with a focus on materials science, biophysics and microfluidics.

The droplet breakup modes can be applied to various channel geometries including cross-flow, co-flow, and flow-focusing. These three device geometries rely mainly on the viscous shear force for droplet breakup, as shown in Fig. 1a. In a cross-flow geometry, also called T-junction, the dispersed phase is sheared in a T-shaped junction which has an angle θ ($0^\circ < \theta \leq 180^\circ$) between the dispersed and the continuous phase channels. This device geometry is widely used in the production of single emulsions due to the simplicity in device fabrication, which requires no additional alignment. The droplets generated have high monodispersity with a coefficient of variation (CV) typically less than 2%. The size of the droplets generated in a T-junction is generally larger than $10\ \mu\text{m}$ due to the limitation of the channel dimension. In a co-flow geometry, also called coaxial junction, dispersed phase channel is inserted into and aligned with the continuous phase channel, and dispersed phase and continuous phase fluids flow in parallel through the channels. In most cases, droplets are formed in a dripping mode, and have low CV (less than 3%). However, the droplet sizes are larger than the tip diameter, thus, are typically larger than $10\ \mu\text{m}$. Flow-focusing has a channel geometry that is similar to that of co-flow but has a focus unit that suddenly shrinks the fluid passageway. Fluid phases form a hydrodynamic flow that contracts through the focus unit resulting in high fluid flow rate. This enhances the viscous shear force and allows formation of droplets with sizes down to a few hundred nanometers.

There are also geometries that allow massive parallelization of multiple nozzles to achieve high throughput production of droplets. For example, step-emulsification devices can produce uniform droplets with high throughput.^{33,34} In such a device, droplet formation is governed by the large difference in the capillary pressure caused by the step change in channel height as shown in Fig. 1b.^{33,35,36} Since the droplet formation is mainly

driven by interfacial tension, without shear forces, the droplet size is independent of the flow rates of both the dispersed and the continuous phases.^{37,38} As long as the dispersed phase flow rate is less than the droplet formation rate at the step, the droplet size is determined only by the height of the inlet channel. This spontaneous droplet formation mechanism often limits the production rate from each nozzle, which is typically much slower than conventional flow-focusing device. However, these devices are much suitable for parallelization as droplet formation does not rely on the shear force from the adjacent immiscible phase. Examples of these devices include, microchannel devices,³⁷ edge-based droplet generation devices,³⁹ millipede devices (Fig. 2a),³⁶ and step emulsification devices. In addition, nozzle geometry³⁶ as well as device materials other than PDMS³³ have been investigated to further expand the utility of these devices. Moreover, external forces such as magnetic,⁴⁰ and centrifugal forces⁴¹ can also be utilized in combination with the step-emulsification device to achieve droplet formation without use of any pumps. Buoyancy can effectively remove droplets from the parallelized step-emulsifier nozzle exits allowing operation with high production rates without impairing monodispersity as shown in Fig. 2b.⁴² Furthermore, tandem emulsification,⁴³ a two-step process in which both step-emulsification and flow-focusing geometry with distinctive surface wettability are utilized, can also produce double emulsion droplets with high-throughput. Here, single emulsions generated from the first device are re-injected directly into the second device to circumvent the spatial control of wettability in a single device as shown in Fig. 2c.

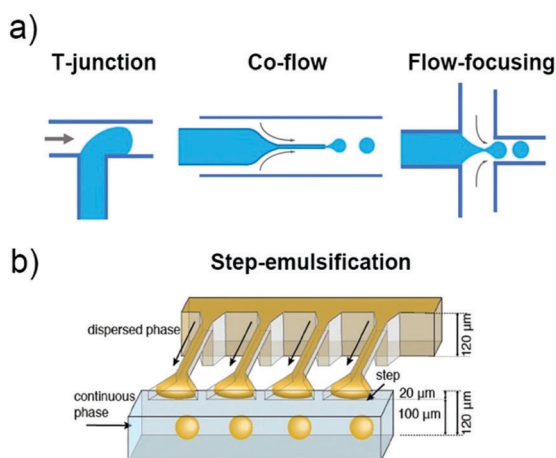


Fig. 1 (a) Schematic illustration of various channel geometries including cross-flow, co-flow, and flow-focusing. (b) Schematic illustration of a step-emulsification channel arranged with four parallelized drop markers.³³ The drop breakup occurs at the step between the nozzle and the continuous phase channel. Reprinted with permission from ref. 33. Copyright 2016, John Wiley & Sons, Inc.

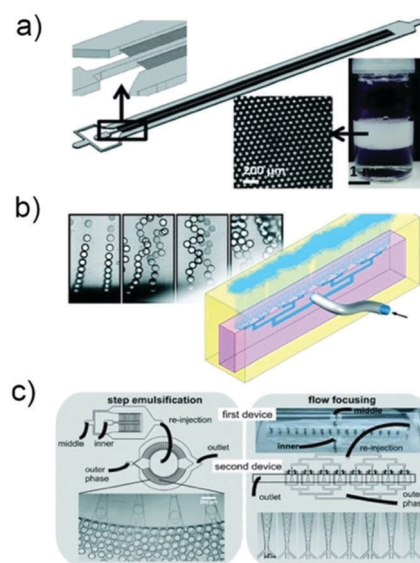


Fig. 2 (a) Schematic illustration of the millipede device³⁶ and the drops produced. Reprinted with permission from ref. 36. Copyright 2016, The Royal Society of Chemistry. (b) Droplet clearance from the nozzle exits in PDMS volcano device.⁴² Reprinted with permission from ref. 42. Copyright 2018, The Royal Society of Chemistry. (c) Schematic illustration of tandem-emulsification.⁴³ Reprinted with permission from ref. 43. Copyright 2017, The Royal Society of Chemistry.

2.2 Droplet microfluidic device

Fabrication of microfluidic devices with well-defined geometry and material compatibility is important for generating and manipulating droplets. Various microfluidic devices have been explored to fulfil the following requirements: material-inherent properties and compatibility with the operating fluid combinations, flexibility in tuning the channel morphologies, level of automation in the fabrication process, as well as the feasibility for large-scale commercialization. Two dominant types of droplet microfluidic devices used in generating various types of emulsion droplets are discussed. One is glass capillary microfluidics that have the advantage of high chemical resistance and ideal coaxial flow-focusing which enables preparation of droplets with wide range of material compositions and structures. The other is lithographically fabricated poly(dimethylsiloxane) (PDMS) devices that have the advantage of preparing a large number of identical devices, making them attractive for large-scale production of droplets.

2.2.1 Capillary microfluidic devices. Capillary microfluidic devices have been widely used to form monodisperse emulsions since 2005.⁴⁴ Capillary microfluidic devices do not require complicated fabrication process and are simple and highly robust, as they involve simply assembling basic modules including injection tube, transition tube, and collection tube.⁴⁵ Typically, a capillary microfluidic device consists of coaxial assemblies of glass capillaries. For example, a tapered cylindrical glass capillary is carefully inserted into a square glass capillary to form water-in-oil (W/O) (Fig. 3a) or oil-in-water (O/W) single emulsion droplets. Prior to insertion, the injection cylindrical capillary surface is rendered to have a higher affinity to the continuous phase than to the dispersed phase; this prevents the adhesion or wetting of droplets on the capillary surface. The surface is rendered hydrophobic for W/O single emulsion, whereas it is rendered hydrophilic for O/W single emulsion. Flowing one fluid inside the cylindrical capillary and flowing a second fluid through the interstices between the square and the cylindrical capillary from the same direction results in a three-dimensional (3D) coaxial flow of the two fluids; this is known as the co-flow geometry. When both

fluid flow rates are low, monodisperse droplets are formed at the tip of the capillary orifice in the dripping mode. If the flow rate of either fluid reaches beyond a certain critical limit, the result is a jet, which is a long stream of the inner fluid with droplets forming downstream. This typically results in droplets with a broader size distribution than that of droplets formed from dripping. Another type of geometry for droplet formation in capillary devices is the flow-focusing geometry. In contrast to co-flow capillary devices, the two fluids are introduced from the two ends of the same square capillary, from opposite directions. The inner fluid is hydrodynamically focused by the outer fluid through the narrow orifice of the tapered cylindrical capillary, enabling formation of monodisperse droplets with sizes smaller than that of the orifice.

A double emulsion is one droplet within another droplet dispersed in a third immiscible phase. The high degree of control offered by glass capillary microfluidic devices enables fabrication of these droplets with a core-shell structure. The most common design combines both co-flow and flow-focusing in which the device consists of two tapered cylindrical capillaries that are inserted into opposite ends of a square capillary from the opposite direction. Similar to the single emulsion device, the glass capillaries are treated to have the desired surface wettability prior to assembly. The inner phase fluid flows through the tapered injection cylindrical capillary while the middle phase fluid, which is immiscible with the inner and outer fluids, flows through the interstices between the injection cylindrical capillary and the square capillary in the same direction, as shown in Fig. 3b. Simultaneously, the outermost phase fluid flows through the interstices between the collection cylindrical capillary and the square capillary in the opposite direction, and hydrodynamically focuses the coaxially flowing stream of the inner and middle fluids. When the three fluids enter the collection tube, double emulsions are formed. By selectively tuning the surface wettability of the cylindrical capillaries and properly choosing fluid types for these three phases, stable formation of either water-in-oil-in-water (W/O/W) (Fig. 3b) or oil-in-water-in-oil (O/W/O) double emulsions can be achieved. Furthermore, by using a modified glass capillary device, which has an injection capillary with two separate internal channels, multi-core double emulsion droplets can also be prepared.⁴⁶ This structure has great potential for co-encapsulation of more than two incompatible actives or reactants without cross-contamination.

Even higher-order multiple emulsions (triple-, quadruple-), can be made through sequential co-flow emulsification by adding additional co-flow junctions composed of injection and transition tubes,⁴⁵ or by combining basic building blocks (a drop maker, a connector and a liquid extractor) to form a scalable device.⁴⁷ Here, surface treatment of the glass capillaries is also required to enhance controllability in droplet formation and promote droplet stability. The high droplet stability ensures accurate and independent control of droplet size and the number of the inner droplets in multiple emulsions. Furthermore, triple emulsion droplets can also be prepared by simultaneous breakup of a core-sheath stream in a single step

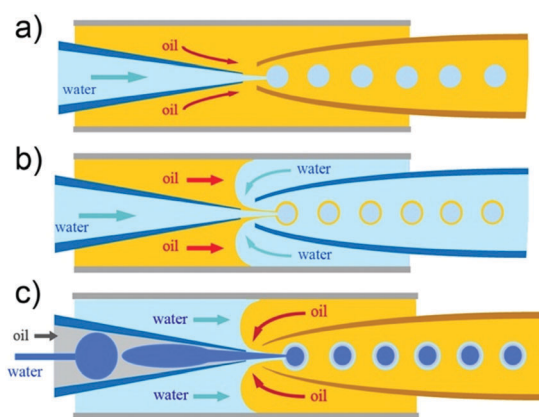


Fig. 3 Schematic illustration of the coaxial capillary microfluidic devices for generation of (a) single (W/O), (b) double (W/O/W) and (c) triple (W/O/W/O) emulsions.

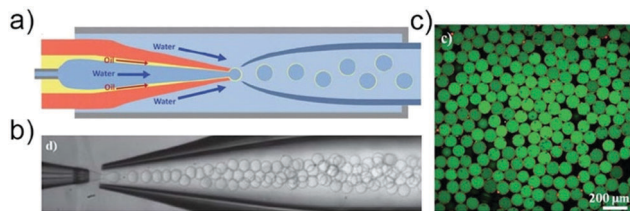


Fig. 4 (a) Schematic illustration of the microfluidic device for preparation of double-emulsion droplets with an ultra-thin shell.⁴⁹ (b) Optical microscope image showing the continuous generation of double emulsion in dripping mode. (c) Confocal microscope images of microcapsules with a poly(lactic acid) membrane. Reprinted with permission from ref. 49. Copyright 2011, The Royal Society of Chemistry.

without sequential emulsification. One major advantage of this approach is that it allows formation of ultra-thin inner shells in triple emulsion droplets,⁴⁸ such as water-in-oil-in-water-in-oil (W/O/W/O) (Fig. 3c). This strategy is also used to form ultra-thin shells in double emulsion droplets (Fig. 4).⁴⁹ For both cases, the shell thickness can be reduced to less than 1 μm, which is difficult to achieve through sequential emulsification. Capillary microfluidic devices can also be parallelized to some extent. A parallelized device comprising of four drop makers produces monodisperse double emulsion droplets from each device simultaneously.⁵⁰

2.2.2 PDMS microfluidic devices. While capillary microfluidic devices are easy to assemble and enable high precision flow control, the manual fabrication process makes it difficult to prepare more than a few devices at a time and the devices prepared often suffer from a lack of reproducibility. Thus, producing large numbers of devices with similar geometry is challenging. A widely used alternative is PDMS microfluidic devices due to the simple and reproducible device fabrication procedures. Such PDMS devices are prepared using soft lithography which enables the formation of identical devices through replica molding, fabrication of devices with micron-scale resolution, and greater flexibility in the channel design compared to capillary devices. Moreover, PDMS is optically transparent, biologically inert, permeable to gases, and low in cost of fabrication.^{51,52}

A PDMS device fabrication process involves preparing master from photomask, forming a PDMS replica, and sealing. Briefly, to fabricate three-dimensional microfluidic devices, the photomasks are firstly prepared. To create a device from the photomask, a silicon wafer is coated with a photoresist to the desired height of the microfluidic channels. The coated wafer is then heated to evaporate the solvent, and cooled to solidify the coating. Then, the photomask is placed on top of the coated wafer and the two are exposed to ultra-violet (UV) light. The light that passes through the transparent regions of the photomask is crosslinked while the uncrosslinked parts are removed by using a solvent. To mold a microfluidic device from this “master,” another polymer, PDMS is poured to form a clear, rubbery layer. Then, the imprinted side is bonded to either another block of PDMS or a glass substrate for sealing with an oxygen plasma treatment. There are also methods such as the membrane

sandwich method⁵³ and solid-object printing⁵⁴ that enable preparation of PDMS device with 3D microchannels. Moreover, geometries including T-junction⁵⁵ and flow-focusing⁵⁶ have been developed in PDMS microfluidic devices for droplet formation. While T-junctions tend to yield more monodisperse droplets at low flow rates, due to the enhanced flow stability with only a single continuous phase inlet.⁵⁷ Flow-focusing junctions yield emulsions at higher flow rates since the centered position of the dispersed phase enables dripping at higher flow speeds.

Regardless of the geometry used for droplet formation, the wetting properties of the channels are of critical importance in determining the types of emulsions that can be formed. The inherent hydrophobic nature of PDMS often limits the types of these emulsion droplets. For example, to form O/W single emulsions, the microchannel surface needs to be modified to be hydrophilic to ensure an effective wetting of the channel surface by the continuous aqueous phase. To resolve these issues, various surface modification techniques have been developed to make the PDMS surface hydrophilic. These methods include oxidation, silane treatment, acid treatment, chemical vapor deposition (CVD), Layer-by-Layer (LBL) deposition, sol-gel method and graft polymer coating.^{58–60} However, to form double or higher order emulsion droplets in PDMS microfluidic devices, the surface wettability needs to be spatially patterned to have subsequent continuous fluids favourably wet the microchannel to form double or even multiple emulsions using multiple flow junctions in microfluidic devices; this allows the inner droplets to be formed in one part of the device and the outer droplets in another part. The need to spatially control the wettability in PDMS devices has stimulated development of various techniques to spatially modify device surface properties.^{61,62} For example, a simple and rapid method to spatially pattern the surface wetting properties of PDMS microfluidic devices is through layer-by-layer deposition of polyelectrolytes using syringe-vacuum-induced segmented flow in 3D microchannels.⁶³ This technique offers selective surface modification in microfluidic chips with multiple flow-focusing junctions, enabling production of monodisperse double- and triple-emulsion droplets.

2.2.3 Other microfluidic devices. Other microfluidic devices based on various materials have also been explored to fulfil specific requirements for droplet formation. For example, fluoropolymer-based devices are commonly used in systems that involve chemical reactions with long-residence-time due to excellent chemical stability and moderate heat resistance. Organic reactions under strongly acidic and basic conditions can be carried out in perfluoropolyether (PFPE) devices even at elevated temperatures.⁶⁴ Quantum dots can be synthesized using the polytetrafluoroethylene (PTFE)-based microfluidic device.⁶⁵ However, PTFE tube is not resistant to high pressure, and the upper limit in operating temperature is only about 200 °C.

With the recent advances in 3D printing technology, 3D printed chips are gaining more attention in microsystems. The basic concept of 3D printing is additive manufacturing of materials. Specifically, 3D digital models from the computer

designed by CAD software or 3D scanners are used to create a series of layers in the Z direction that is solidified layer-by-layer to form a 3D entity. Various techniques utilized in 3D printing process mainly differ by the form of the source material (liquids/powders), various sequences to achieve multiple layers (bottom-up or top-down), solidification methods (UV or heat), and the feature resolution. Among these source materials, photocurable resins are widely used due to their biocompatibility. These resins include PEG diacrylate, gelatin methacrylate, hyaluronic acid and PEGylated/functionalized alginates. Acrylonitrile has also been used to form T-junction microfluidic device for droplet production. Monodisperse aqueous droplets are produced with polydispersity index similar to those produced in analogous PDMS chips.⁶⁶ Microfluidic flow-focusing devices are also made to generate aqueous droplets around 500 μm in diameter.⁶⁷ Double emulsions are also made using a 3D-printed microcapillary assembly (Fig. 5a).⁶⁸ These examples reveal that 3D printing allows formation of a true 3D design of channels such as tapered geometry in XYZ in a cost-effective manner. Another unique advantage of 3D printing is the automation of microfluidic kit. Microfluidic channels as well as pumps, mixers, and valves can be printed simultaneously.⁶⁹ Even non-expert users can produce functional modules with 3D printing and can combine them to create their specific integrated microfluidic devices.⁷⁰ However, 3D printing techniques have many remaining challenges, such as relatively low resolution, lack of suitable materials, and immature methods to modify the surface wetting properties.

Microfluidic devices can also be prepared through hot-embossing,⁷¹ which is a very versatile replication method that

uses high pressure and elevated temperature to transfer structures in the master to the polymer. Many thermoplastic polymers, such as polycarbonate, polymethylmethacrylate, polyethylene, copolyester, cyclic olefin copolymers, polystyrene, polythiophene, can be processed using hot-embossing to fabricate microfluidic devices.⁷² Advantages of hot-embossing for microfluidics include the ability to achieve very clean and precise features quickly and cost-effectively with materials that otherwise cannot be prepared using other technologies. Three modes of hot-embossing have been developed, including plate-to-plate, roll-to-plate and roll-to-roll. Among these, the roll-to-roll (R2R) process allows large-scale production of microfluidic devices in the most cost-effective manner.^{73,74} In a typical R2R process, a thermoplastic foil is continuously fed through a pressurized area between a heated embossing cylinder and a blank counter cylinder to generate microscale geometries with high throughput.⁷³ Although R2R hot embossing (Fig. 5b) offers high throughput, high automation, and decreased cost compared to conventional soft-lithography, high aspect ratio structures are challenging to fabricate using this method.⁷⁵

3. Fabrication of microparticles

Droplet microfluidics provides a powerful strategy for generating versatile monodisperse droplets, which can be used as templates for fabricating various microparticles with tailored physical and chemical properties. With the recent growing recognition of the necessity of producing microparticles for biomedical applications, a variety of materials and fabrication methods are being explored in microfluidically produced emulsions with complex structures. Each immiscible phase or compartment within these emulsions serves as a template that bears physical and chemical reactions either in the entirety or between the interfaces, enabling flexible synthesis of microparticles with tunable sizes and morphologies, as well as distinctive bio-related functionalities. Moreover, recent advances in utilizing aqueous two-phase systems (ATPS) in droplet microfluidics⁷⁶ as well as high-order multiple emulsion drops⁴⁸ enable the generation of engineered microparticles that fulfil sophisticated requirements in biomedical applications such as biocompatibility and multicomponents. A host of materials can be selected for microparticle fabrication, which is essential for achieving desired properties to meet different application purposes. These materials can be categorized into two types:^{16,77} first, natural macromolecules including natural polysaccharides (alginate, agarose, dextran, chitosan), proteins (gelatin, collagen, peptides) and hyaluronic acid, and second, synthetic polymers including poly(ethylene glycol), polyglycerol, poly(acrylic acid) and poly(acrylamide).

In this section, we introduce the basic principles on how microparticles are fabricated directly using monodisperse droplets as templates. These produced droplets are converted into solid microscale particles by various methods including polymerization, ionic crosslinking, solvent evaporation, *etc.* Each fabrication method is described in detail, followed by approaches in fabricating microparticle with various structures

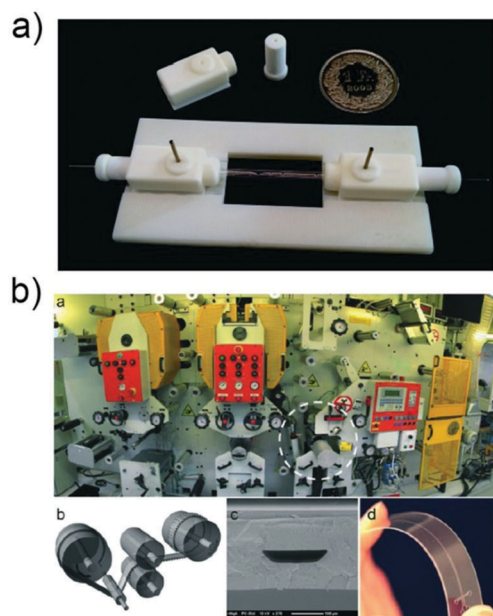


Fig. 5 (a) A 3D-printed assembly of capillary device ready for use.⁶⁸ Reprinted with permission from ref. 68. Copyright 2014, The Royal Society of Chemistry. (b) Roll-to-roll hot embossing of microfluidic chips.⁷⁵ Reprinted with permission from ref. 75. Copyright 2016, The Royal Society of Chemistry.

from simple microspheres to multi-compartmental microcapsules. Importantly, each fabrication method is not exclusive and by combining these methods, microparticles with unique properties can be achieved.

3.1 Methods for microparticle fabrication

3.1.1 Polymerization. Polymerization is the most popular method for converting emulsion droplets to solid particles due to the versatile and efficient protocols, as well as the variety in the choice of polymerizable materials. By addition of monomers or oligomers in the dispersed phase along with a small amount of suitable initiator such as thermal or photoinitiator, emulsion droplets can be polymerized upon heating or UV irradiation. For thermally triggered polymerization, thermal initiator produces radicals which initiate and propagate the polymerization above a certain temperature. However, this strategy is less preferred as high temperature can perturb the activity of biomolecules and also cause unstable emulsion interfaces, leading to coalescence before solidification.

Photopolymerization is one of the most prevalent ways to initiate polymerization due to the fast response time, which can induce polymerization within seconds, enabling less consideration of emulsion stability. For instance, UV-polymerizable hydrogel precursor droplets dispersed in an oil carrier phase can be polymerized upon exposure to UV, resulting in biocatalyst

immobilized microparticles (Fig. 6a).⁷⁸ The size of the microparticles can be adjusted from tens to hundreds of micrometers by changing the flow rate of the constituent fluids. The same principle has been extensively applied to a large number of monomers and oligomers for the synthesis of hydrogel microparticles. By using W/O droplets with water-soluble monomers, hydrogel microparticles such as polyacrylamide (PAAm),⁷⁹ poly(ethylene glycol)diacrylate (PEGDA)⁸⁰ and gelatin methacrylate (GelMA)⁸¹ were fabricated, which possess great potential as substrates or carriers in biochemical analysis and building units for tissue engineering. In addition to photoinitiated polymerization, microparticles can also be synthesized *via* redox-initiated polymerization.^{82,83} For example, *E. coli* loaded PEG microparticles were fabricated without usage of UV irradiation, as the irradiation can potentially damage the encapsulated microorganisms and cells even under a short period of exposure. Thus, enhanced cell viability in microparticles was achieved (Fig. 6b).⁸² Also, organic polymer resin microparticles such as ethoxylated trimethylolpropane triacrylate (ETPTA), 1,6-hexanediol diacrylate (HDDA), and tripropylene glycol diacrylate (TPGDA) were prepared through use of oil droplets as templates.^{84–86} Furthermore, thiol-ene photopolymerization was recently exploited to fabricate advanced microcapsules with tunable encapsulation, degradation, and thermal properties.⁸⁷

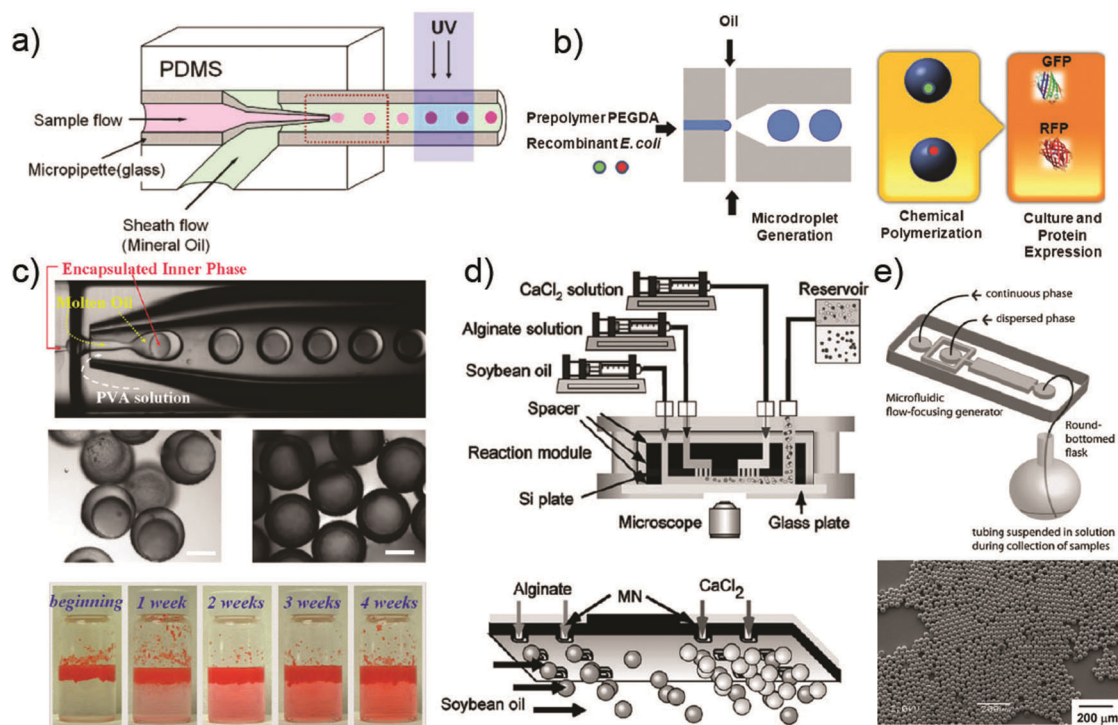


Fig. 6 Various methods utilized in converting emulsion droplets to solid microparticles. (a) Fabrication of microparticles *via* photopolymerization.⁷⁸ Reprinted with permission from ref. 78. Copyright 2005, American Chemical Society. (b) Synthesis of microparticles encapsulating cells *via* redox-initiated chemical polymerization.⁸² Reprinted with permission from ref. 82. Copyright 2010, John Wiley & Sons, Inc. (c) Fabrication of microcapsules *via* freezing. Series of photographs below show the leakage of Allura Red AC food dye from the microcapsules over time.⁸⁸ Reprinted with permission from ref. 88. Copyright 2011, American Chemical Society. (d) Synthesis of alginate microparticles through coalescence of two separately prepared drops and subsequent physical crosslinking.⁹⁰ Reprinted with permission from ref. 90. Copyright 2005, Elsevier. (e) Synthesis of PLGA microparticles through solvent evaporation.⁹³ Reprinted with permission from ref. 93. Copyright 2009, John Wiley & Sons, Inc.

3.1.2 Temperature induced gelation and freezing. Micro-particles prepared by polymerization method result in a polymeric matrix with covalent linkages which make them chemically resistant as well as mechanically durable as compared to other methods. However, radicals generated during polymerization can cause serious problems considering their biotoxicity. Solidification of droplets through temperature induced physical gelation and freezing can alleviate some of these issues. The gelation method is applicable to droplets comprising of natural biological resources including collagen, agarose, and gelatin, which can be transformed into hydrogel by simply changing the temperature.¹⁶ The freezing method relies on the fact that some hydrocarbon molecules and lipid molecules including glycerides possess melting point at or above room temperature. By operating above the melting point and collecting the generated droplets at either room temperature or in an ice bath, temperature triggered phase transition results in solid microparticles or a solid shell in microcapsules. These types of microparticles are particularly appealing as delivery vehicles due to their biocompatibility and thermo-responsive behavior. However, microcapsules prepared by freezing exhibit large pores in the shell, inducing leakage of encapsulants, thus additional treatments are required to block these pores (Fig. 6c).^{88,89}

3.1.3 Ionic crosslinking. One of the most studied ionic crosslinking material in droplet microfluidics is alginate hydrogel microparticles where gel precursor droplets are cross-linked by divalent ions. This is typically triggered by ionic reactions among charged polysaccharide residues and divalent cations such as calcium ions (Ca^{2+}). However, unlike photopolymerization, incorporation of both polymer precursors and cross-linking agents in the same compartment can result in instantaneous consolidation and clogging of the microfluidic channel. Thus, delicate control over the onset of solidification is required. One method utilizes coalescence or fusing of two separately prepared droplets, each comprising of precursor polymers and cross-linking agents, which mix and crosslink downstream of the microfluidic device (Fig. 6d).⁹⁰ Other methods rely on diffusion of Ca^{2+} from the continuous phase into the dispersed aqueous phase solely containing alginate polymers.⁹¹ Nanoparticles which release divalent cations by triggered ionization can also be incorporated within the same droplet but in an inactive state to control the onset of gelation reaction.⁹²

3.1.4 Solvent evaporation/diffusion. Polymers approved by the U.S. Food and Drug Administration (FDA) such as poly(lactic acid) (PLA) and poly(lactic-co-glycolic acid) (PLGA) are biocompatible and biodegradable, which make them one of the most appealing materials for drug delivery systems (DDS). However, these polymers are not applicable for polymerization or ionic cross-linking, and thus solvent evaporation or diffusion method is applied to produce microparticles. This fabrication method typically utilizes dissolution and assembly of organic compound in a volatile solvent, allowing the use of almost unlimited sets of materials in microparticles; any polymers or active materials dissolvable in a volatile solvent can be incorporated. For example, monodisperse biodegradable drug-loaded

PLGA microparticles were prepared by dissolving both PLGA and drug in dichloromethane (DCM) droplets which rapidly evaporate to form solid particles. The size of the particles can be tuned by controlling the flow rate. Also, the resulting monodisperse microparticles exhibit significantly reduced burst release and slower overall rates of drug release than conventional, polydisperse microparticles with similar characters (Fig. 6e).⁹³ In a separate work,⁹⁴ PLA microparticles were generated by dissolving the polymers in ethyl acetate, an organic solvent with low toxicity. Furthermore, use of a volatile organic solvent in the middle phases of multi-phase emulsion droplets enables formation of solid shells by removal of the solvent through evaporation or diffusion into the adjacent phases. Due to the relatively slow consolidation process, this method demands a long lifetime or stability of the multiple-emulsion droplets; otherwise, undesired products can be obtained. With the stability of the emulsion droplets secured, functional materials can be readily incorporated within the shell membrane to impart stimuli-responsiveness as well as microcapsules with even sub-micron shell thickness.⁴⁹

3.1.5 Phase separation/dewetting. One remarkable feature of solvent evaporation/diffusion method is that the co-solvent or two organic compounds with different solubilities may undergo internal physical processes, such as phase separation and dewetting, as the composition changes due to solvent evaporation or mass transfer with the surroundings through the interfaces. This process often yields at least two immiscible phases, which can remodel the droplets into more complex configurations. Here, we highlight some representative examples including generation of Janus microparticles and higher-order microparticles from a homogeneous single emulsion *via* phase separation,⁹⁵ and production of liposomes/polymersomes *via* dewetting.^{96,97}

Janus particles composed of biodegradable and pH-responsive compartments have also been prepared using solvent evaporation induced phase separation (Fig. 7a).⁹⁸ Briefly, emulsion droplets containing two polymers are homogeneous at the beginning, and then transform into microparticles with multiple compartments as solvent is depleted from the droplets. By tuning the polymer pairs, pH value of the continuous phase, and type of organic solvent, configuration of the microparticles can be altered into core-shell, Janus, and core-double shell structures. In addition, phase separation of two biodegradable polymers, PCL and PLGA, has also been studied in double emulsion droplets using the similar principles to result in a Janus shell, where one component forms the shell and the other component dewets on the surface.⁹⁹ Phase separation can even result in higher-order multiple emulsions with onion-like configuration from a homogeneous single emulsion droplet.^{95,100} It was showed that a ternary mixture of ethanol, water, and an oil, diethyl phthalate (DEP), emulsified in an aqueous solution can result in droplets with multiple layers by internal phase separation (Fig. 7b). In a separate material system, higher-order emulsion droplets can be prepared from single-emulsion droplets.¹⁰⁰

Phase separation can also be used to fabricate vesicles, which are microcapsules with a membrane composed of a

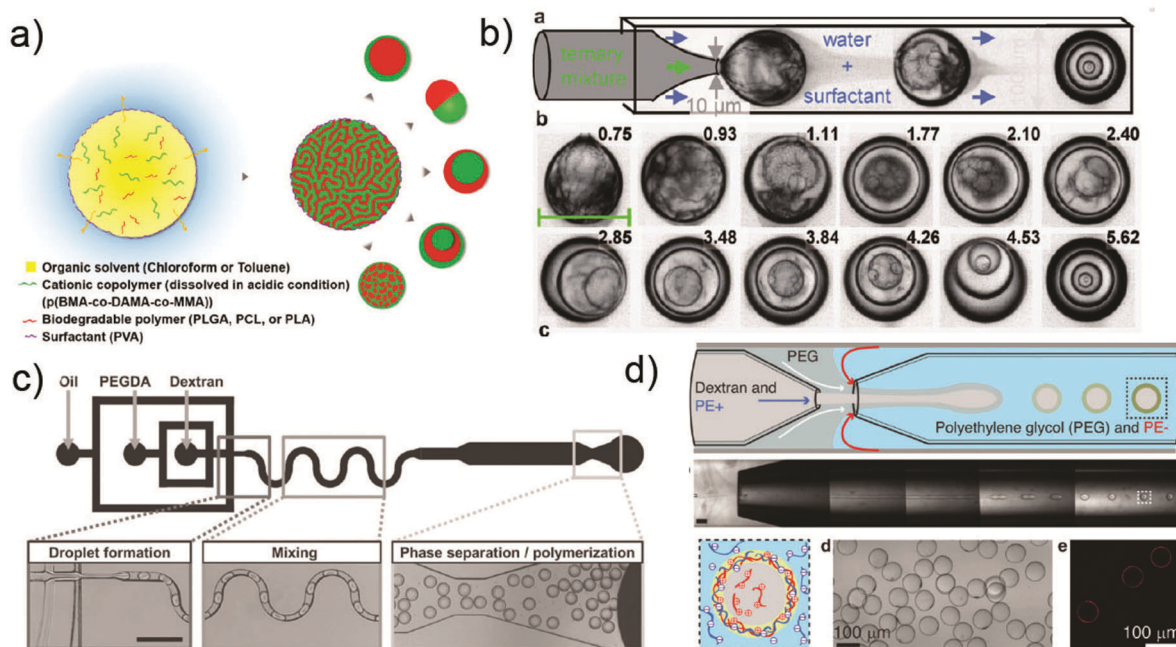


Fig. 7 Other methods utilized in converting emulsion droplets to solid microparticles. (a) Formation of microparticles with various configuration through phase separation in emulsion drops.⁹⁸ Reprinted with permission from ref. 98. Copyright 2016, American Chemical Society. (b) Formation of quintuple emulsion drops from single emulsion drops via phase separation.⁹⁵ Reprinted with permission from ref. 95. Copyright 2014, John Wiley & Sons, Inc. (c) Synthesis of dextran/PEG microparticles by utilizing ATPs.¹⁰⁹ Reprinted with permission from ref. 109. Copyright 2012, John Wiley & Sons, Inc. (d) Fabrication of microparticles through interpolymer complexation between polyelectrolytes in ATPs.¹¹³ Reprinted with permission from ref. 113. Copyright 2016, John Wiley & Sons, Inc.

molecular bilayer. Depending on the composition of the bilayer membrane, they can be categorized into liposome for lipid molecules, and polymersomes for amphiphilic block-copolymers. Vesicles are promising for delivery vehicles, as well as for investigating cellular physiological activities in response to various stimuli due to their structure which resembles natural biomembrane systems. While various methods have been developed¹⁰¹ to prepare both liposomes and polymersomes, droplet microfluidic techniques using multi-phase emulsion droplets as templates^{96,97} allow fabrication of vesicles in a highly controlled manner. Briefly, W/O/W double emulsion droplets are generated with an oil shell containing either lipids or amphiphilic polymers in two solvent mixture; one is a good solvent with high volatility and the other is a poor solvent with low volatility. Evaporation and diffusion of the good solvent into the continuous phase result in the amphiphiles aligned at both inner and outer interfaces to attract and the poor solvent with low volatility to dewet. After dewetting of oil on the surface of the inner droplet, this either remains to form a local multilayer or becomes completely separated from the water core, resulting in a single bilayer vesicle. By tuning the composition of each phase of the emulsion droplets, unilamellar and multicompartamental liposomes can be prepared. In addition, multiple polymersomes, or polymersomes-in-polymersomes, can be prepared for programmed release of different ingredients.¹⁰² Furthermore, multi-functional vesicles have been fabricated by embedding hydrophobic functional materials such as quantum dots, gold, and magnetic nanoparticles in the shell for triggered release.¹⁰³

3.1.6 Aqueous two-phase system (ATPs). Typical droplet formation in microfluidic devices involves the use of an oil phase and an aqueous phase. However, droplets can also be generated in aqueous two-phase systems (ATPs) consisting of two aqueous solutions that are immiscible with each other. ATPs comprises of hydrophilic materials that are each dissolved in an aqueous phase that demix into two water-rich phases when their concentrations exceed a certain value. The phase separation occurs when the entropic driving force that favours mixing becomes less than the enthalpic penalty that opposes it.⁷⁶ All aqueous environment offered by ATPs provides a mild surrounding environment compared to typical oils, enabling incorporation of active biomolecules such as proteins without potential denaturation. This makes them well suited for biomedical applications. However, the interfacial tension between the two phases in ATPs is substantially low compared to that between oil and water. Therefore, droplets are often formed at jetting regime as the viscous and inertial forces dominate during drop formation, resulting in polydisperse droplets. To overcome this challenge, various techniques have been developed, such as operation at low droplet generation rate with weak viscous and inertial forces,¹⁰⁴ all-aqueous electrospray technique,¹⁰⁵ applying external forces including pulse,¹⁰⁶ mechanical vibration,¹⁰⁷ and piezo-electricity.¹⁰⁸ The most established ATPs system comprising of PEG and dextran has been employed in synthesizing hydrogel microparticles through mechanical piezoelectric induced generation of W/W droplets.¹⁰⁸ The same system has also been used to synthesize

microparticles with complex shape *via* polymerization in single-emulsion droplets (Fig. 7c).¹⁰⁹

3.1.7 Interfacial reaction and complexation. Many of the methods described in the previous sections rely on converting a selected compartment within an emulsion droplets to a solid. However, one of the major advantages of having more than one immiscible fluid is that one can induce reactions at the fluid interfaces. This is generally achieved by using either two reactive reagents or complementary interacting polymer pairs that are each separately dissolved in the dispersed phase and the continuous phase. This facilitates reactions or complexation that occur on droplet interfaces, enabling fabrication of microcapsules directly from single emulsions. For example, hollow metal–organic framework (MOF) microcapsules were synthesized by the interfacial reaction among the organic and inorganic precursors that were initially dissolved in two immiscible solvents.¹¹⁰ Guest species were also encapsulated in microcapsules under the mild reaction conditions. Similarly, core–shell chitosan microcapsules were fabricated by cross-linking with glutaraldehyde that was initially present in the inner and outer fluids in O/W/O double emulsions.¹¹¹ Polyelectrolyte (PE) microcapsules have been prepared through interfacial complexation of polymers in emulsions followed by spontaneous droplet hatching.¹¹² Briefly, two complementary polyelectrolytes were each initially dissolved in the inner and middle phase of W/O/W double emulsion drops. Then, the two polymers formed a complex at the inner W/O interface of the W/O/W double emulsion followed by dewetting of the oil drop resulting in polyelectrolyte microcapsules. Polyelectrolyte microcapsules can also be synthesized by combining ATPs and interfacial complexation in W/W/W double emulsion droplets (Fig. 7d).¹¹³ These double emulsion droplets serve as a transient template while interpolymer complexation occurs between two oppositely charged polyelectrolytes.

3.1.8 Colloidal assembly. Emulsion droplets prepared *via* droplet microfluidics serve as an excellent template to geometrically confine and induce organization of colloidal particles into ordered superstructures, including colloidal clusters and 3D spherical colloidal crystals. By utilizing colloidal nanoparticles with tunable size, uniformity, and surface functionality as the building block in droplets, sacrificial templates, interfacial stabilizers, colloidal crystal beads, inverse opals, and particles with surface patterns can be synthesized in a highly controlled way for various applications. For example, magneto-responsive Janus photonic crystal particles for bioassay were synthesized by combining phase separation and self-assembly of silica and magnetic nanoparticles.¹¹⁴ Moreover, multi-color encoded microspheres with silica nanoparticles arrays were synthesized by combining photopolymerization and self-assembly of functional silica nanoparticles on the surface of the microparticle for multiplex immunoassays.¹¹⁵

3.2 Microparticle structures

In this section, we describe how to prepare microparticles with various structures, as summarized in Fig. 8. We also focus on how these microparticles fulfill the different requisites in diverse fields of biomedical applications.

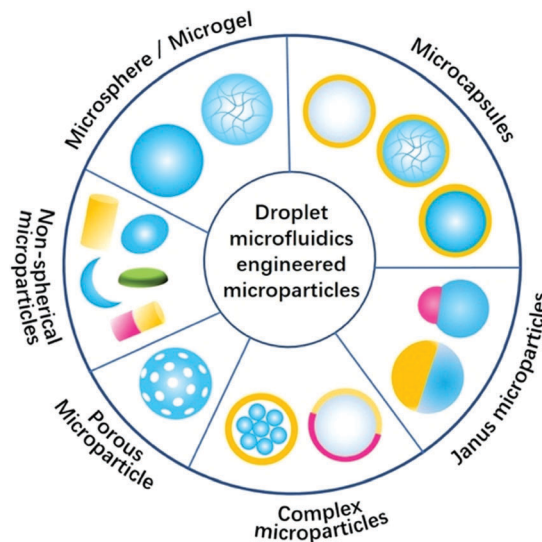


Fig. 8 Microfluidically engineered microparticles with various structures. The gray color represents the liquid phase, while all other colors represent either solid or hydrogel phase.

3.2.1 Microspheres and microgels. Monodisperse emulsion droplets produced *via* droplet microfluidics in their natural state maintain a spherical shape due to the minimization of their surface energy. In the simplest case, polymeric microspheres or microgels composed of either polymer chains or crosslinked polymer networks can be obtained by solidification of single emulsion droplets. Production of monodisperse microparticles with well-defined sizes, mechanical properties, and functionalities have an enormous impact on biomedical applications such as drug delivery and cell encapsulation. For instance, polymeric microspheres or microgels prepared *via* droplet microfluidics enable flexible delivery of drugs as particle size and material composition strongly affects their release profile, biodistribution, and administration route. Moreover, encapsulation of cells in microgels provide a biocompatible 3D microenvironment for living cells by protecting the cells from the surroundings while simultaneously supplying adequate amount of water, oxygen, and nutrients required to sustain the cells. Molecular architecture within the microgel has also been tuned to vary the mechanical properties of the microgels encapsulating the cells; these factors govern cell migration, proliferation, and differentiation.^{116,117} Cell-encapsulating microgels also serve as scaffolds for tissue engineering and implantable carriers for cell therapy.

3.2.2 Non-spherical microparticles. Nonspherical microparticles can be prepared by adjusting the reaction conditions during the fabrication process. This includes, for example, an aqueous solution of sodium alginate flowing through an oil layer and into a reservoir containing Ca^{2+} . Due to relatively slow sedimentation process and reaction rate, which can be tuned by changing the viscosity and Ca^{2+} concentration, tear droplet or tail shaped particles can be prepared (Fig. 9a).¹¹⁸ Other examples utilize polymerization of the deformed droplet during spatial confinement to result in microparticles with various shapes

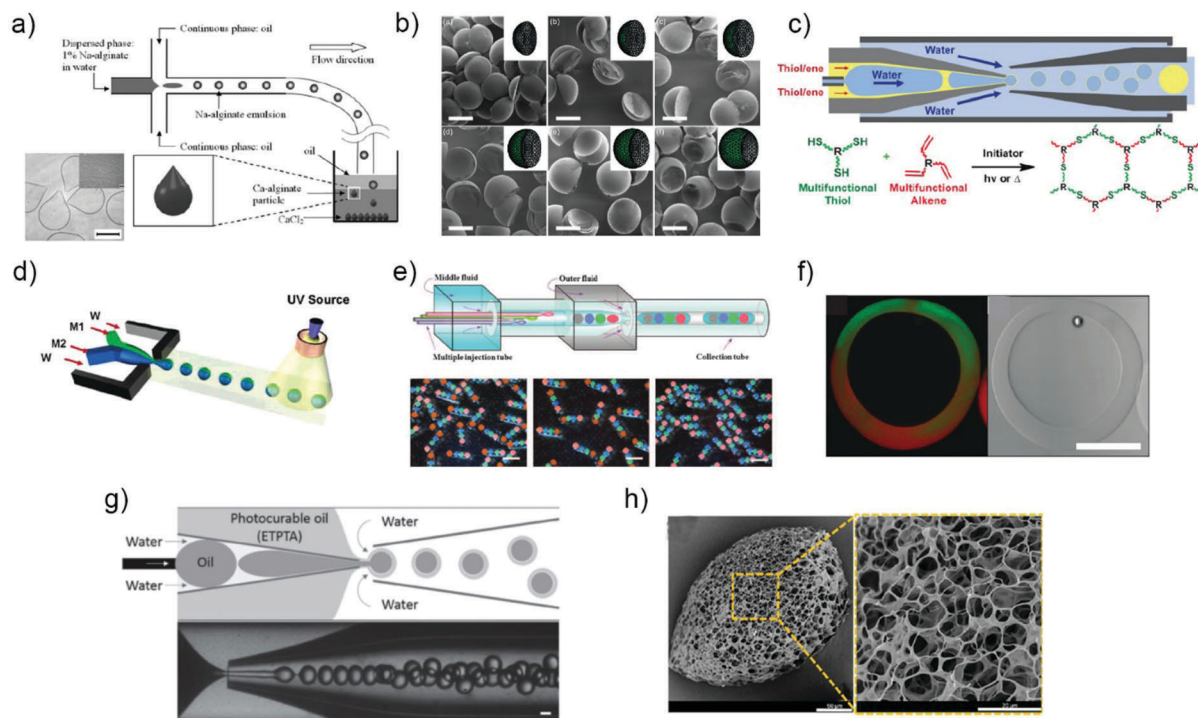


Fig. 9 Fabrication of microparticles with various structures. Synthesis of (a) tear drop or tail shaped alginate microparticles,¹¹⁸ Reprinted with permission from ref. 118. Copyright 2013, John Wiley & Sons, Inc. (b) Microparticles with complex shapes by selective solidification of a Janus type emulsion drop,¹²⁰ Reprinted with permission from ref. 120. Copyright 2011, American Chemical Society. (c) Microcapsules with tunable encapsulation, degradation, and thermal properties by exploiting thiol-ene chemistry,⁸⁷ Reprinted with permission from ref. 87. Copyright 2017, American Chemical Society. (d) Amphiphilic Janus particles,¹²⁴ Reprinted with permission from ref. 124. Copyright 2006, American Chemical Society. (e) Microcapsules with multiple core components by using multiple inner flows during emulsification,¹²⁸ Reprinted with permission from ref. 128. Copyright 2010, Nature Publishing Group. (f) Microcapsules with Janus shells,¹²⁹ Reprinted with permission from ref. 129. Copyright 2010, American Chemical Society. (g) Triple emulsion drops with an ultra-thin intermediate layer for encapsulation of hydrophobic cargo in polymeric microcapsules⁴⁸ (Reprinted with permission from ref. 48. Copyright 2016, John Wiley & Sons, Inc.) and (h) porous microparticles by addition of tiny oil drops as porogens.¹³² Reprinted with permission from ref. 132. Copyright 2014, American Chemical Society.

including spheres, disks, and rods.¹¹⁹ Furthermore, by selectively solidifying a compartment in a Janus type emulsion droplet, microparticles with complex shape can be prepared. For instance, dumbbell, acornlike, sharp-edged, or moon-crescent type microparticles were produced by tuning the relative values of the interfacial tension (Fig. 9b).¹²⁰ A similar conceptual idea was applied to create microlenses with shapes from convex to planar and even concave.¹²¹

3.2.3 Microcapsules with core-shell structure. Core-shell microparticles, or microcapsules, are typically composed of solid, liquid, or gas bubbles surrounded by a protective shell. Due to the unique core-shell structure, such microcapsules enable highly efficient encapsulation and protection of valuable and delicate cargoes from the surrounding environment. Moreover, the high flexibility of material selection for the shell enables production of microcapsules with diverse properties and functionalities such as enhanced retention, controlled release, and stimuli-responsiveness. Therefore, they have been widely applied in the delivery of therapeutics. The ability to fabricate uniform emulsion droplets with precisely controlled size and morphology offers powerful advantages as it allows generation of microcapsules with adjustable release profiles as well as minimal possibilities of burst release, which can cause

serious issues in delivery of therapeutics. While microcapsules can be prepared from homogeneous single emulsion droplets by phase separation^{95,100} or by merging of single emulsion droplets by wettability control,¹²² they are most commonly derived from double emulsion droplets using different shell solidification processes. As long as the stability of the double emulsion droplets is secured during the solidification of the shell phase, almost unlimited variety of substances can be employed as the core and the shell materials. Moreover, by creating a biphasic flow within the injection capillary and forming a sheath flow consisting of a thin layer of the middle phase fluid with high affinity to the capillary wall, double emulsion droplets with even sub-micron thick shells can be prepared.⁴⁹ All these provide enormous opportunities for tailoring microcapsules for specific applications. For example, advanced microcapsules with tunable encapsulation, degradation, and thermal properties can be prepared by exploiting thiol-ene chemistry in the middle phase of double emulsion droplets (Fig. 9c).⁸⁷ The details of many other examples can be found in several other papers.^{11,123}

3.2.4 Janus microparticles. Janus microparticles have two separate compartments with distinctive physicochemical properties which make them appealing for drug delivery, micromotors, and self-assembly. They are synthesized from

either Janus droplets or homogeneous droplets. When Janus droplets serve as templates, the particles are directly synthesized through either polymerization or ionic crosslinking of the constituent phases. Various types of Janus particles have been synthesized using droplet microfluidics. Amphiphilic Janus particles with different volume fractions of the constituent phases form clusters with different aggregation numbers (Fig. 9d).¹²⁴ Also, selective modification of the surface of Janus particles was employed to impart additional functionality. In another example, Janus hydrogel particles with super-paramagnetic properties and chemical anisotropy were self-assembled into two-dimensional chain-like structures under an external magnetic field.¹²⁵ Homogeneous emulsion droplets can also be employed to synthesize Janus particles through phase separation. For example, a pH-responsive cationic copolymer and another biodegradable polymer were dissolved in an organic solvent which went through phase separation upon evaporation.⁹⁸ Thermo-responsive volume-phase transition can also induce particles with Janus structure when poly(*N*-isopropylacrylamide) (PNiPAM) nanoparticle suspensions containing acrylamide are heated above its transition temperature.¹²⁶

3.2.5 Microparticles with complex structures (multi-core, higher-order). The structure of microcapsules can be much more diversified by incorporating an additional compartment in the emulsion droplet, either in the core or the shell. For example, microcapsules with multiple core components were synthesized by using several separate inner flows during emulsification. These inner cores can be either separated by a solid shell or have a single Janus core within the shell after UV irradiation.¹²⁷ By adding more inner flows, microcapsules with even more number of cores can be produced (Fig. 9e).¹²⁸ Furthermore, microcapsules with Janus shells can also be prepared by using parallel middle phase flows during emulsification (Fig. 9f).¹²⁹

Triple emulsion droplets offer even more flexibility in the selection of core and shell material as well as an effective route to achieve high encapsulation efficiency of incompatible cargos. Triple emulsion droplets with an ultra-thin intermediate layer enable highly efficient encapsulation of hydrophobic cargoes in polymeric microcapsules, directly dispersed in water (Fig. 9g).⁴⁸ In addition, by replacing the ultra-thin water layer with a fluorocarbon oil layer, high loading efficiency of a broad range of polar and non-polar cargoes in a single platform was achieved.¹³⁰

3.2.6 Porous microparticles. Porous microparticles can be prepared by introducing sacrificial templates into the precursor droplet and subsequently removing them after solidification. For example, PNiPAM microparticles with tunable structures and temperature-sensitive properties were prepared by addition of PEG with different concentration and molecular weight¹³¹ or by addition of tiny oil droplets that act as porogens (Fig. 9h).¹³² Polystyrene (PS) microbeads were also used as a sacrificial template and selectively removed with organic solvent to create porous hydrogel microparticles.¹³³ Other examples include using gas bubbles, either initially included¹³⁴ or post-generated,¹³⁵ self-assembling dendrimer-dye complex¹³⁶ as porogens to synthesize monodisperse porous microspheres. In addition,

phase-separation can also be employed to prepare porous microparticles.¹³⁷

4. Biomedical applications

Droplet microfluidics provides a unique method for fabrication of monodisperse microparticles with control over the size, morphology, and functionality, in a high throughput manner. This technique also allows on-chip encapsulation of various bioactives, such as drugs, cells and other bio-reagents in microparticles with high efficiency (Fig. 10), and even direct co-encapsulation of multi-components.¹³⁸ Moreover, enhanced retention as well as controlled release of bioactives can be achieved by adjusting the particle size, structure and composition. These advantages make microfluidically engineered microparticles beneficial for various biomedical applications including development of advanced delivery vehicles and fundamental studies of cell biology.

4.1 Drug delivery

An advanced drug delivery carrier requires excellent biocompatibility, biodegradability, and high drug loading efficiency. This drug carrier also need to deliver drugs to the target site with desired release rate upon demand. The microparticles generated by droplet microfluidics allow high drug loading efficiency (> 96%) through on-chip encapsulation.^{139,140} Their uniformity in size, structure, and composition also guarantee a consistent drug release profile. Various biocompatible materials and fabrication methods discussed in Section 3 are applicable in producing microparticles with desired properties and functions as advanced microcarriers.¹⁴¹ The size of the microparticle is essential for choosing the appropriate drug administration route. Microparticles produced by microfluidics with sizes ranging from a few microns to hundreds of microns are most

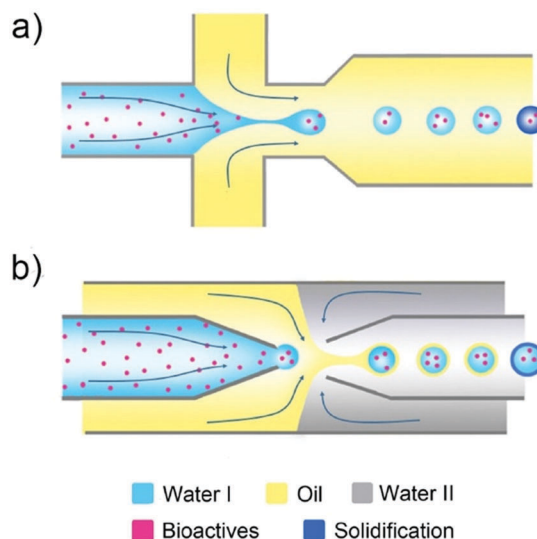


Fig. 10 Encapsulation of bioactives, such as drugs, proteins, and cells, (a) in microspheres/microgels templated with single emulsions generated from a PDMS device and (b) in the liquid core of microcapsules templated with double emulsions generated from a glass capillary device.

suitable for oral drug delivery. Particles with sizes of 10 to 250 μm can also be used for subcutaneous or intramuscular injection.²

4.1.1 Drug encapsulation. A typical drug encapsulation process using droplet microfluidic technique is shown in Fig. 10. Briefly, a precursor solution containing drugs, such as antibodies, proteins, anticancer drugs or other therapeutics, is first emulsified to form discrete droplets. Drugs directly encapsulated inside these droplets are then solidified into microparticles. To achieve effective therapeutic delivery, drugs should be well-encapsulated to avoid side effects due to premature leakage. Besides, a delicate selection of materials and emulsion templates based on the physicochemical properties of drugs including molecular weight, polarity, and bioactivity, is necessary.

Single emulsion templated microparticles solidified from W/O or O/W emulsions can directly encapsulate either hydrophilic or hydrophobic drugs within these particles. To efficiently encapsulate drugs, it is essential to use materials that have good compatibility with the drugs. For instance, chitosan-based microspheres have been fabricated by droplet microfluidics to encapsulate hydrophilic ampicillin¹⁴² or bovine serum albumin (BSA) drugs.¹⁴³ Amphiphilic microgels fabricated from random copolymers comprising of hydrophilic acrylic acid (AA) and hydrophobic *n*-butyl acrylate (BuA) enable encapsulation of both hydrophobic and hydrophilic moieties.¹⁴⁴

Microparticles with core-shell structure allow encapsulation of drugs inside the core with high loading efficiency, while the shell performs as a diffusion barrier to control the release profile by enhancing the retention of the drugs. The drug release period can be adjusted by tuning the shell thickness and the mesh size of the polymeric shell. For example, microcapsules with a semi-permeable PLGA shell were prepared.¹⁴⁵ The shell thickness can be controlled in the range of 70–150 nm by adjusting the initial PLGA concentration to achieve sustained release of the payloads up to 3–5 months. The enhanced encapsulation can also be achieved through modification of the shell or the core of the microcapsules. By generating solid precipitates within the shell of microcapsules,⁸⁸ small pores of the shell can be blocked, enabling a significant reduction of the dye leakage from 16% to 3% in 4 weeks (Fig. 11a). Microcapsules with a hydrogel core were fabricated for enhanced fragrance encapsulation and retention.¹⁴⁶ The hydrogel core serves as a physical barrier to immobilize the individual fragrance droplets and prevents them from interacting with the shell, resulting in a substantial reduction in leakage (Fig. 11b). This is especially beneficial for long-term retention of perfume in cosmetics.

Microparticles with multicompartiment structure enable separate coencapsulation and synergistic release of multiple drugs. This approach reduces the risk of cross-contamination between the drugs and keeps independent control over drug release, which is advantageous for combination therapy. It also ensures the correct local concentrations of both drugs, which can be essential for synergistic release. For example, microcapsules with one or multiple GelMA hydrogel cores and PLGA solid shell were prepared (Fig. 12a).¹⁴⁷ Hydrophilic and hydrophobic

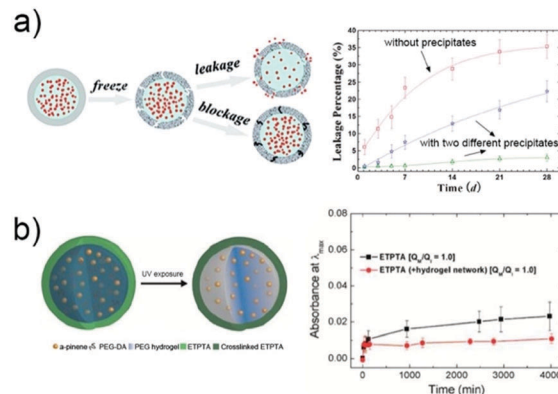


Fig. 11 Drug encapsulation in microparticles for long term retention. (a) The enhanced encapsulation of actives in self-sealing microcapsules by formation of precipitates in the capsule shells.⁸⁸ Reprinted with permission from ref. 88. Copyright 2011, American Chemical Society. (b) The microcapsules with a hydrogel core enhance retention of fragrance molecules.¹⁴⁶ Reprinted with permission from ref. 146. Copyright 2016, American Chemical Society.

drugs, doxorubicin hydrochloride (DOX) and camptothecin (CPT) were loaded into the core and the shell, respectively. These drugs can be released sequentially upon gradual degradation of the biopolymer shell. Multicompartiment microcapsules with heterogeneous Ca-alginate hydrogel shells were fabricated by using combined coextrusion microfluidic devices (Fig. 12b).¹⁴⁸ Each compartment is covered with a distinctive shell, allowing incorporation of multiple components and independent

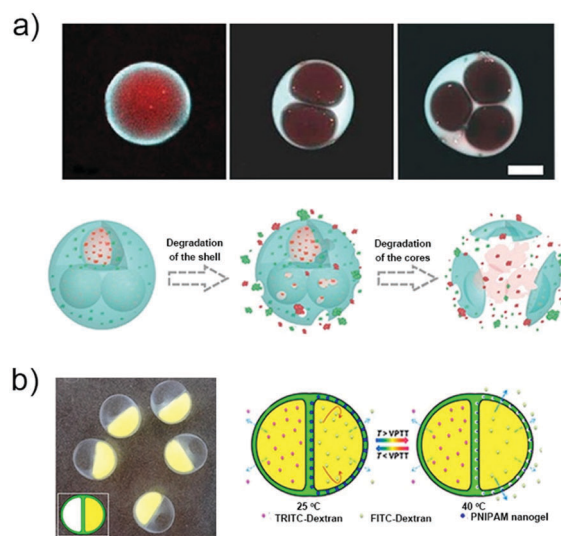


Fig. 12 Multicompartiment microparticles for coencapsulation of multi-drugs. (a) CLSM images of DOX (red) and CPT (blue) loaded microparticles with single or multiple cores, and illustration of sequenced fracture of the shell and the core to release the drugs.¹⁴⁷ Reprinted with permission from ref. 147. Copyright 2017, Science China Press. (b) Optical micrograph of microcapsules with dual compartments and heterogeneous shell, and illustration of microcapsules exhibiting both temperature triggered release and sustained release.¹⁴⁸ Reprinted with permission from ref. 148. Copyright 2016, American Chemical Society.

control over their release. In dual compartmental capsules with thermoresponsive nanogels introduced into one-half of the Janus shell, the release of actives in the two compartments can be triggered by temperature and concentration gradient, respectively.

4.1.2 Drug release. Drugs loaded in the microparticles can be released either by diffusion through the pores of the particle matrix or by degradation of the particle matrix.¹⁴¹ The release of drugs can also be realized from microparticles comprised of stimuli-responsive materials, which change their physical or chemical properties upon external stimuli such as temperature,^{149,150} pH,^{151–153} ultrasound,^{154,155} or light.^{156–158} Different drug release profiles, including sustained release and burst release, can be achieved by tuning the properties of the microparticles. Sustained release refers to gradual release of drugs over an extended period of time. It normally entails an initial fast release followed by a slow and steady release. This release profile is desirable for many therapeutic treatments which require minimal drug dosage for maximum patient compliance to achieve long-term safe and effective drug delivery.^{159,160} By contrast, burst release refers to a quick and abrupt release of drugs, resulting in a rapid increase in local drug concentration within a short period. Microparticles with stimuli-responsive properties can exhibit burst release profile, which are desirable for release of drugs at the designated site to achieve fast relief.¹⁶¹ It is important to develop microparticles with the desired release profile to fulfil various therapeutic requirements.

4.1.2.1 Sustained release. Release of drugs in microparticles through diffusion or degradation of the polymer matrix¹⁵⁹ can be regulated by several parameters, including particle size,¹⁴⁷ shell thickness,¹⁴⁵ particle structure,¹⁴³ matrix mesh size,^{162,163} or affinity of the drugs to the polymer matrix in the microparticles.¹³² By tuning these parameters, drugs can be gradually released from the microparticles for a predetermined period of time. In general, increase of particle size and shell thickness results in decreased release rate and prolonged duration.^{145,147}

The mesh size of the polymer matrix in microparticles is one of the key parameters controlling the diffusion and release of drugs.¹⁶⁴ Drugs with hydrodynamic diameter that are smaller than the mesh size can migrate freely through the polymer matrix. As the size of the drug increases, steric hindrance by the matrix becomes stronger, resulting in a slower release rate. For instance, fluorescein sodium salt ($M_w = 376$ Da) encapsulated inside a protein-based microcapsules is released 60% in 1 h, because of its smaller size compared to the mesh size of the microcapsule membrane.¹⁶⁵ By contrast, large FITC-bovine serum albumin (BSA) ($M_w = 68\,000$ Da) almost does not leak within the same period. For a microcapsule membrane composed of polyelectrolytes,¹¹³ the release time is extended significantly, from 10 to 1000 min, when the molecular weight of neutral dextran molecules increases from 5 to 40 kDa. The interaction between the drug and polymer matrix also influences the release rate, apart from the mesh size. When a negatively charged protein with a size similar to the 40 kDa dextran is encapsulated in the polyelectrolyte microparticles,

only ~20% is released after 600 min. This large suppression in release is a result of the enhanced electrostatic interaction between the protein and the polyelectrolyte membrane. A similar phenomenon is also observed when using nanofibril microgels composed of amyloid proteins as microcarriers:¹⁶⁶ dyes which have a strong affinity to amyloid gels are not fully released after 1 week, whereas other dyes or drugs reach their maximum release rate after 1 h.

The rate of sustained release can also be tuned by altering the microparticle structure. Chitosan microspheres with three different types of structures, including solid, porous, and core-shell structures, were fabricated from W/O emulsions by controlling the solidification time. Different release profiles of BSA were demonstrated due to the difference in mesh size and structure,¹⁴³ as shown in Fig. 13a. Introduction of a shell on a microparticle has proven to be an efficient strategy for suppressing drug release. Four model drugs with different solubility and lipophilicity were encapsulated in porous silicon microparticles covered with a solid lipid membrane shell.¹⁶⁷ The release rate of these drugs from these particles was always slower than that of the bare silica microparticles in all pH conditions tested (1.2, 5.0 and 7.4). In another example, polyacrylamide (PAM)/poly(ethylene glycol) (PEG) microcapsules with multicore structures were prepared from hydrogel/water/oil (H/W/O) emulsions, which exhibit different protein release rate.⁷⁹ The release of BSA in the first hour from a single-core microparticle is slower than that from a quadruple-core microparticle.

Sustained release can also be achieved in microparticles composed of responsive materials by applying external stimuli. For example, the release time scale can be adjusted by introducing ultrasound as an external stimulus which can change the mesh size or destroy the particle matrix. Microcapsules of PDMS with eccentric and core-centered internal hollow structures were produced from W/O/W droplets, and their release profile was regulated by ultrasound. For both microcapsules, rhodamine 6G was only very slightly released in the absence of ultrasound whereas it was continuously released from the microcapsules in the presence of ultrasound. The eccentric microcapsules with thinner walls exhibited higher release rate than core-centered microcapsules, as shown in Fig. 13b.¹⁶⁸

Microparticles with pH responsive property show great potential for targeted drug delivery due to the variation of pH in the human body, such as the acidic condition in the stomach and the basic condition in parts of the intestine and colon. A series of composite microparticles were microfluidically engineered and exhibited pH triggered sustained release profile. The utility of these particles as advanced oral drug co-delivery vehicles for combination anticancer therapy was demonstrated.^{169,170} For example, multi-drug loaded polymer/porous silicon (PSi) composite microparticles were fabricated from O/W droplets in a flow-focusing capillary device (Fig. 13c).¹⁶⁹ Two drugs atorvastatin (AVA) and celecoxib (CEL) were selected due to their synergetic effect for cancer therapy. The AVA was loaded inside PSi, which were then encapsulated together with the CEL into microparticles composed of two pH-responsive polymers. These composite microparticles showed multi-stage

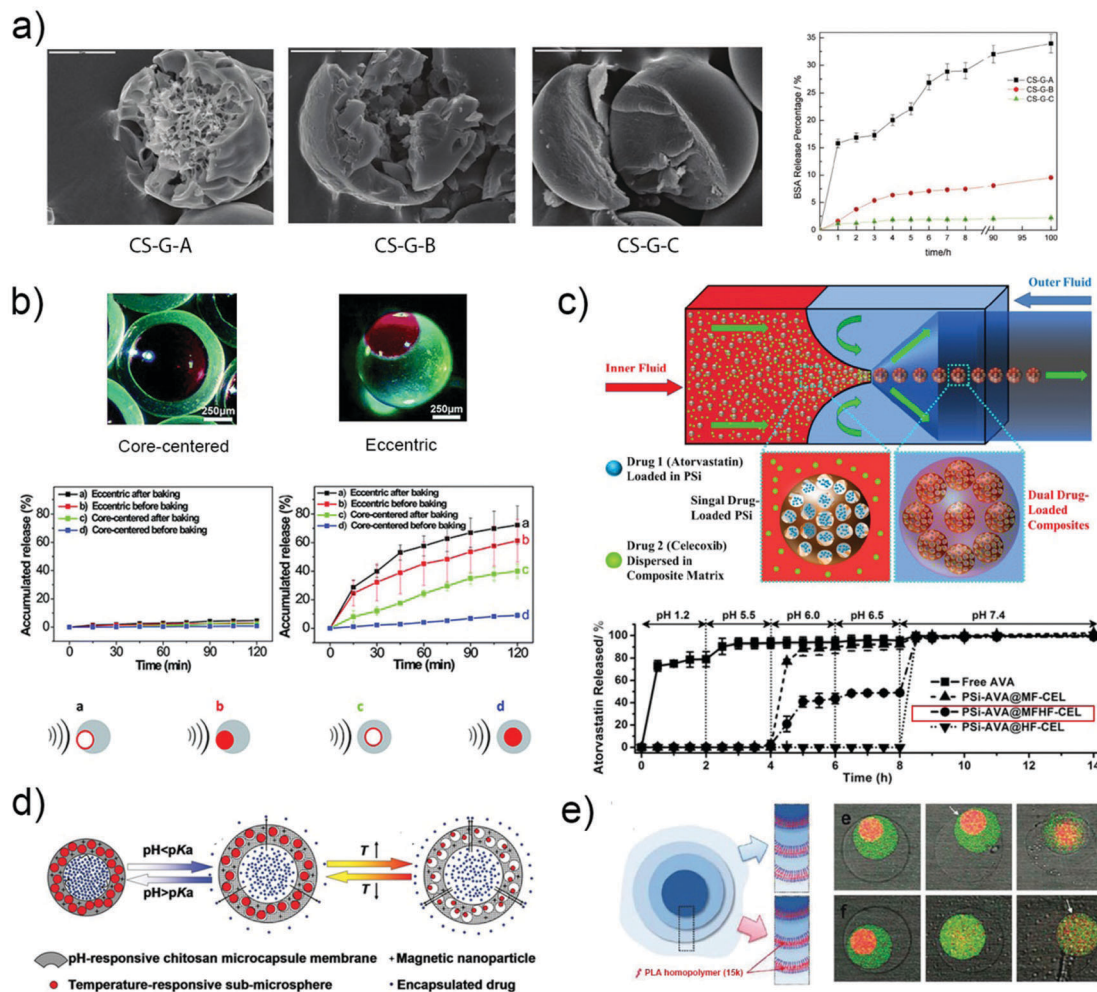


Fig. 13 The sustained release of drugs. (a) SEM images of chitosan microspheres with three different structures and their *in vitro* BSA release profiles.¹⁴³ Reprinted with permission from ref. 143. Copyright 2012, John Wiley & Sons, Inc. (b) Optical images of the eccentric and core-centered internal structures, and release profiles of rhodamine 6G from the four types of microcapsules with and without ultrasound.¹⁶⁸ Reprinted with permission from ref. 168. Copyright 2014, The Royal Society of Chemistry. (c) The fabrication of multi-drugs loaded polymer/porous silicon (PSi) composite microparticles for multi-stage release of AVA drugs in different pH conditions.¹⁶⁹ Reprinted with permission from ref. 169. Copyright 2014, John Wiley & Sons, Inc. (d) Schematic illustration of the multi-stimuli-responsive microcapsules with adjustable controlled-release.¹⁷³ Reprinted with permission from ref. 173. Copyright 2014, John Wiley & Sons, Inc. (e) Schematic illustration of a triple polymersome showing bilayers with no internal homopolymer on the top right and two of the bilayers containing homopolymer on the bottom right. Series of confocal images showing the sequential dissociation of these two kinds of membranes in the mixture of water and ethanol.¹⁰² Reprinted with permission from ref. 102. Copyright 2011, American Chemical Society.

pH-responsive behavior. They maintained their structural integrity at pH from 1.2 to 5.5, whereas they started to dissolve between pH 6.0 and 6.5 and released 50% of the drugs in 2 h. Above pH 6.5, the structure completely collapsed to release all of the remaining drugs in half an hour. Upon incubation of these microparticles with colorectal cancer cells, cell viability decreases to less than 50% under pH 6.5 while 90% cell viability is observed under pH 5.5 after 24 h. By encapsulating multi-drug loaded silicon nanoparticles and magnetic nanowires into the same polymeric microspheres, pH-responsive microspheres with long term sustained release profile and magnetic targeting properties was achieved.¹⁷¹ These microspheres can protect the payloads under acidic conditions and release them gradually under basic conditions, making them superior carriers for intestinal delivery of therapeutics. Core-shell alginate microcapsules

encapsulating vitamin A and gelatin were also prepared for intestine-targeted drug delivery. The alginate microcapsule remains intact in an acidic environment while it degrades in alkaline environment to release the encapsulated gelatin.¹⁷²

Microparticles with multi-stimuli responsive properties have been prepared to achieve enhanced control over drug release. For instance, responsive microcapsules with adjustable mesh size in the shell were fabricated from W/O/W emulsions.¹⁷³ The shell of these microcapsules is composed of crosslinked pH-responsive chitosan membrane with embedded magnetic nanoparticles and thermoresponsive nanospheres as shown in Fig. 13d. When the local pH is lower than the pK_a of chitosan, the membrane swells, resulting in a high drug release rate. The release rate can be further tuned by varying the interspace distance between the nanosphere in the capsule membrane.

This is achieved by the temperature regulated volume change of the nanospheres. In addition, due to the magnetic nanoparticles, microcapsules can be directed to the desired site by an external magnetic field.

The programmable release of multiple components can be achieved through preparation of microparticles with complex structures; this includes microparticles with several shell layers and additional compartments. For instance, polymersome-in-polymersomes were fabricated from multiple-stage W/O/W double emulsions, providing convenient strategies for encapsulating multiple actives into different membrane layers.¹⁰² The programmed rupture of the membrane triggered by mechanical strain or osmotic pressure enables sequential release of the payloads (Fig. 13e).

Microparticles prepared from biodegradable materials have also been demonstrated to show sustained drug release *in vivo*. Microcapsules with biodegradable thin shells of PLGA exhibit continuous release of encapsulated bioactives in times ranging from two to five months, at different pH conditions (Fig. 14).¹⁴⁵ When these microparticles are introduced into mouse dorsum through subcutaneous injection, the encapsulated drugs are observable even after one month, while the free drugs dissolved in the tissue are barely detected after one day. Acetalated dextran (AcDX)-based biodegradable microspheres were prepared by droplet microfluidics for spinal cord injury treatment.¹⁷⁴ These monodisperse microspheres have a diameter of 7.2 μm and exhibit gradual degradation at pH 7.4 during a period of one month. After intrathecally injecting into injured rats, they not

only effectively suppress the astrogliosis and inflammation in the injured spinal cord, but also protect the neurons from glutamate-induced excitotoxicity. This reveals the potential application of these AcDX microspheres for severe neurological diseases treatment.

4.1.2.2 Burst release. Microparticles for burst release are typically composed of stimuli-responsive materials, which can respond to external stimuli and abruptly change or rupture their structures followed by ejection of the drugs.

Temperature is one of the most widely used stimuli for triggering a fast response. The temperature alteration can induce the microparticles to either melt or change the volume to achieve burst release. For microcapsules with a frozen shell, increasing the ambient temperature above the melting point of the shell material can trigger the solid shell to melt in few seconds and abruptly release the payloads. For instance, microcapsules with fatty acid glyceride shell remain stable at room temperature for at least six months with no observable leakage. However, when heated above 37 $^{\circ}\text{C}$, the solid shell turns into liquid in 30 s and encapsulated actives are completely released after 5 min.⁵⁹ Microparticles composed of PNIPAM, a thermo-responsive polymer with a lower critical solution temperature (LCST) about 32 $^{\circ}\text{C}$, can collapse or swell by tuning the temperature above or below the LCST. Thermoresponsive microcapsules made from PNIPAM have been fabricated using double-emulsion templates.^{175,176} They release actives in two ways: (1) the actives are encapsulated at low temperature, and when the temperature is raised above the LCST, the particles quickly shrink and rupture due to the sudden increase in internal pressure,¹⁷⁵ (2) the actives are sealed in the core at high temperature and when the temperature is lowered below the LCST, the shell sharply swells to enlarge the mesh size, which releases the actives.¹⁷⁶ Block copolymers of PNIPAM¹²² and nanogels¹⁷⁷ have also been used as composites in the microcapsule shells. Increasing the temperature results in enlarged mesh size due to shrinkage of the PNIPAM nanogels, and therefore release of the encapsulated actives.

Microparticles composed of pH responsive polymers have also been explored for burst release. A large pH variation dramatically changes the polymer solubility, resulting in change of mesh size or even decomposition of the particle matrix. Monodisperse microcapsules composed of a crosslinked chitosan shell and a core containing fluorescent dyes are sealed at neutral pH. At acidic conditions (pH \sim 3), the chitosan shell decomposes rapidly and releases the dyes completely within a few minutes.¹¹¹ To achieve more effective acute gastritis therapy, different chitosan based pH-responsive microcapsules can be fabricated containing both free drugs and drug-loaded PLGA nanoparticles for programmed sequential release of drugs.¹⁷⁸ In an acidic environment, microcapsules release both the free drugs and the PLGA nanoparticles rapidly within 60 s due to the decomposition of the chitosan shell. This results in sufficient drug dose for immediate relief of patient symptoms after drug administration (Fig. 15a). Then the drugs inside the PLGA nanoparticles are slowly released over 2 days to maintain the therapeutic effect and reduce complications.

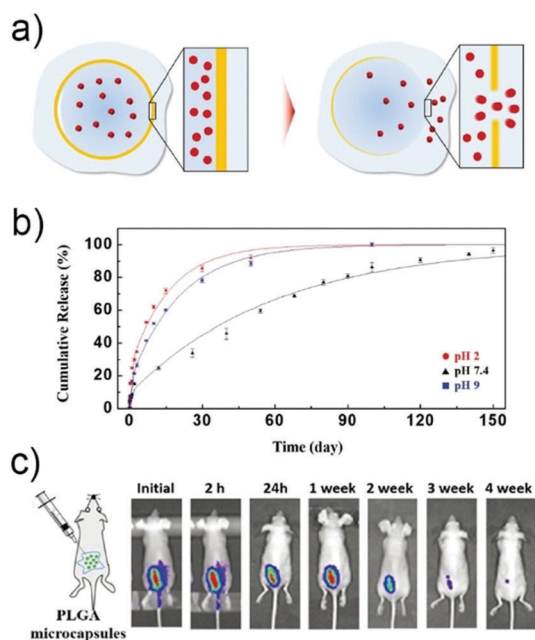


Fig. 14 (a) Schematic illustration of release of encapsulants through a hole formed at the thinnest part of a PLGA membrane by degradation.¹⁴⁵ (b) Cumulative release of sulforhodamine B from the microcapsules at different pH. (c) *In vivo* fluorescence images for ICG-loaded PLGA microcapsules that are subcutaneously injected into dorsum of mice. Reprinted with permission from ref. 145. Copyright 2017, John Wiley & Sons, Inc.

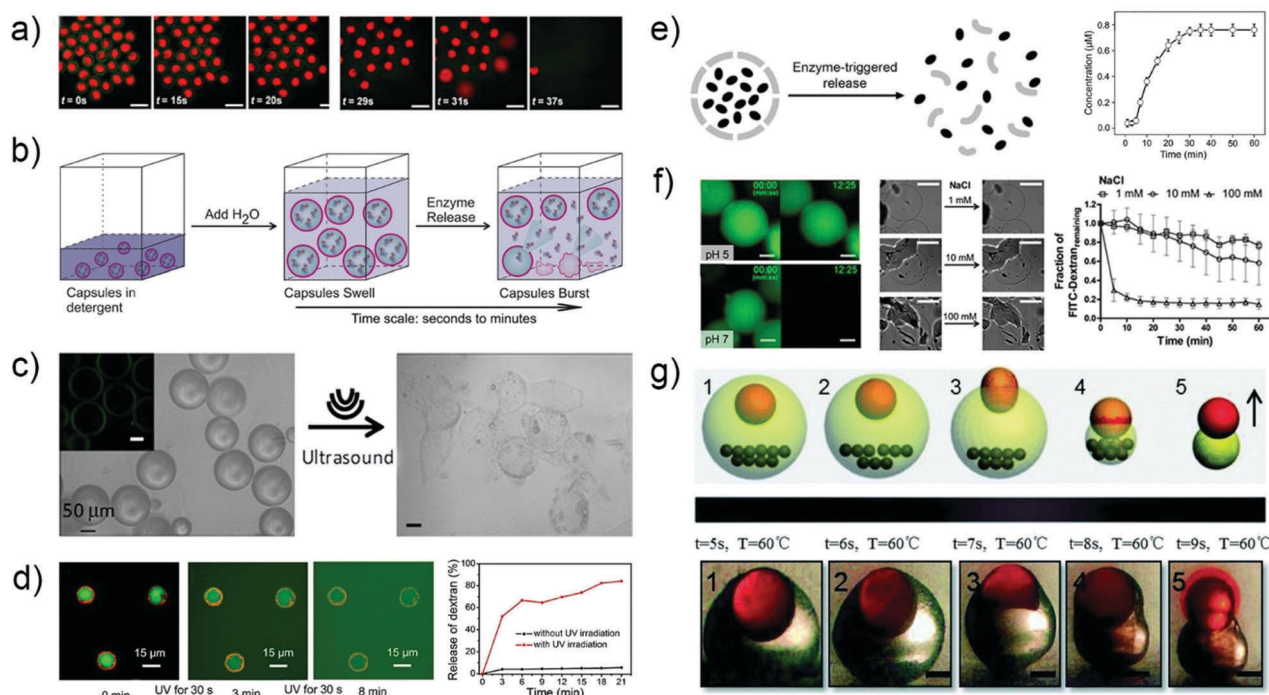


Fig. 15 The burst release of drugs. (a) The CLSM snapshots showing the decomposition of chitosan shell to release the encapsulated free RhB drugs and the RhB-PLGA nanoparticles rapidly in an acidic environment.¹⁷⁸ Reprinted with permission from ref. 178. Copyright 2016, American Chemical Society. (b) The schematic illustration of osmotic pressure triggered release of encapsulated enzymes.¹⁷⁹ Reprinted with permission from ref. 179. Copyright 2017, John Wiley & Sons, Inc. (c) The images of PFC-alginate microcapsules before and after ultrasound exposure.¹⁸⁰ Reprinted with permission from ref. 180. Copyright 2014, American Chemical Society. (d) The fluorescent micrographs showing the triggered release of FITC-dextran cargo from hydrated microcapsules under ultraviolet light.¹⁸⁵ The release profile of FITC-dextran from the microcapsules as a function of the rehydration time. Reprinted with permission from ref. 185. Copyright 2016, American Chemical Society. (e) The enzyme-triggered release of protein-based microcapsules and the release profile of the FITC-BSA.¹⁶⁵ Reprinted with permission from ref. 165. Copyright 2014, John Wiley & Sons, Inc. (f) The microcapsules showing both pH and ionic strength triggered release. The fluorescent images of PAA/bPEI microcapsules containing FITC-dextran showing pH-triggered release, the optical images showing the salt-triggered deformation of the microcapsules and the encapsulated FITC-dextran molecules release profile in NaCl solutions.¹¹² Reprinted with permission from ref. 112. Copyright 2015, American Chemical Society. (g) Temperature triggered release of the upper-oriented inner core when the magnet is in the bottom.¹⁸⁷ Reprinted with permission from ref. 187. Copyright 2014, The Royal Society of Chemistry.

Osmotic shock is induced by a sudden change in solute concentration around the microparticles, causing a rapid change in the movement of solvent across its shell membrane. This particular stimulus has been widely applied for the burst release of actives. Polymersomes are prepared from self-assembly of amphiphilic diblock copolymers (PEG-*b*-PLA) by using multiple-stage W/O/W droplets. Their shells are semi-permeable membranes with relatively low mechanical properties and high-water diffusivity, enabling easy rupture of the shell under osmotic pressure to release the payloads.^{96,103} Microcapsules with ultra-thin polymeric shell have also been utilized to achieve osmotic pressure triggered burst release of enzymes. These microparticles fabricated from W/O/W double emulsions have a shell with thickness ranging from tens to hundreds of nanometers. Enzymes protected by these thin shells maintain a much prolonged activity compared to free enzymes, while over 90% of the encapsulated enzymes can be released when triggered by osmotic shock (Fig. 15b).¹⁷⁹

Ultrasound and light are attractive stimuli for triggering drug release from microparticles due to their remote manipulation capability and non-invasiveness. For example, alginate core-perfluorocarbon-oil-shell microcapsules¹⁸⁰ can maintain

their integrity after injection into a polyacrylamide gel that mimics the tissue matrix. However, upon exposure to ultrasound for 15 min, the particles can be disrupted, demonstrating their potential for ultrasound-based therapies (Fig. 15c). Light is another easily applied stimulus. In particular, near-infrared (NIR) can penetrate deeply into tissue and is barely absorbed by the hemoglobin and body water, making it an attractive external stimulus for *in vivo* drug release.^{181,182} Microcapsules exhibiting NIR-sensitive properties are normally comprised of temperature responsive polymer materials¹⁸³ and NIR-absorbing materials such as gold nanorods or nanoparticles. For example, microcapsules with an ethyl cellulose shell containing PNIPAM nanogels and gold nanorods were fabricated.¹⁷⁷ After irradiation with NIR laser, the gold nanomaterials absorb energy and generate localized heat. The increase of the local temperature induces shrinkage of the PNIPAM nanogels and formation of macrogaps, resulting in enhanced release of encapsulants. Microcapsules composed of PLGA and gold nanomaterials can also be ruptured under NIR illumination since PLGA melts at temperature above its T_g (40–60 °C).¹⁸⁴ In addition, UV-responsive supramolecular microcapsules were formed through interface host-guest interaction

between amphiphilic polymer micelles containing azobenzene groups and cucurbit[8]uril (CB[8]).¹⁸⁵ Upon exposure to UV for 3 min, the *trans*-to-*cis* photoisomerization of azobenzene groups induces a facile increase of the microcapsule porosity, releasing 84% of the payloads after 18 min (Fig. 15d).

Other stimuli such as enzymes and ions are attractive in achieving fast responses in biological environments. For example, protein based microcapsules can be degraded when a digestive enzyme is introduced. This induces the degradation of shell layer into small pieces due to the cleavage of amide bonds, leading to a total release of the encapsulants in 40 min (Fig. 15e).¹⁶⁵ Microcapsules with a shell membrane composed of 15-crown-5, NiPAM, and AAm-based copolymer can recognize K^+ ion to form a sandwich complex and induce phase transition of PNiPAM. The capsules shrink and rupture rapidly, leading to the ejection of all the encapsulated lipophilic actives in the cores.¹⁸⁶

Microparticles with multi-responsive properties have also been developed for burst release. Polyelectrolyte microcapsules were fabricated through interfacial complexation of two oppositely charged polymers at the inner (W/O) interface of W/O/W double emulsions.¹¹² These microcapsules show both pH and ionic strength responsive behavior (Fig. 15f). The change of pH from 5 to 7 reduces the interaction between the two polymers causing drastic swelling of the microcapsules in less than 13 min. Increasing the ionic strength of the solution from 1 to 100 mM also induces sudden deformation of the particles and subsequent release of the encapsulants. Through incorporation of magnetic nanoparticles in the shell, microcapsules can respond to a magnetic field for targeted drug release. In particular, microparticles containing magnetic particles with an asymmetric shape can burst release drugs at the target site. Microcapsules with a magnetically eccentric core-shell structure were fabricated from O/W/O double emulsions through a combination of gravitational and magnetic forces.¹⁸⁷ The microparticles are composed of a PNiPAM shell with an off-center core and magnetic nanoparticles dispersed in the shell, on the opposite side of the core from the nanoparticles. The off-centered core induces heterogeneity in the shell thickness: the shell near the core is thinner while the side far from the core is thicker, as shown in Fig. 15g. When the temperature is raised above the LCST of PNiPAM, the shell breaks at the thinner side and eject the core. With the presence of magnetic nanoparticles, drugs can be released at a desired location with a specific orientation by applying an external magnetic field.

4.2 Cell-laden matrix

Cells in the body exist in a 3D microenvironment comprising of proteins and polysaccharides, defined as the extracellular matrix (ECM).¹⁸⁸ The properties of ECM strongly influence cellular phenotype and function. Biocompatible hydrogel microparticles with sizes ranging from 60 to 200 μm are promising platforms for *in vitro* cell culture, as they perform as 3D matrices that can mimic various aspects of the ECM.^{16,96} Their properties such as stiffness and porosity can be tuned by altering the gel components. In addition, the intrinsic porous

structure and the high surface-to-volume ratio of hydrogel microparticles facilitate exchange of oxygen, nutrients and waste, while protecting the cells from the surrounding environment and retaining cell viability. These advantages lead to emergence of a large number of biomedical applications related to cell-laden hydrogel microparticles including cell life study,^{77,189} drug screening and discovery,^{190,191} and tissue engineering.^{17,192}

Although several techniques have been exploited for generating cell-laden microparticles, such as bioprinting,¹⁹³ micromolding,¹⁰ and soft-lithography,¹⁹⁴ droplet microfluidics is often the most suitable choice as it allows continuous production of mono-disperse hydrogel microparticles in a high-throughput manner. More importantly, microfluidics allows control over both the number of cells encapsulated in each gel particle, and the overall encapsulation efficiency. In this section, we introduce recent advances in cell encapsulation and culture in hydrogel microparticles generated by droplet microfluidics. We also discuss the application of cell-laden microparticles in cell-fate studies, tissue engineering, and single cell analysis.

4.2.1 Cell encapsulation and culture. In a typical cell-encapsulation process, a hydrogel precursor solution containing cells is emulsified in a continuous oil phase to form discrete droplets on-chip, followed by crosslinking to result in cell-embedded hydrogel microparticles as shown in Fig. 10. The cells can also adhere to the surface of microparticles after their formation with the advantages of fast cell proliferation and easy collection. However, this strategy only allows cells cultured on a curved surface instead of a 3D matrix inside the microparticles. The most common examples of engineered cell-laden micro-matrix include microgels with uniform spherical structure, and core-shell microcapsules with either a liquid or a hydrogel core. Only a few examples of cell-laden microparticles with Janus structure have been addressed.^{195,196} Overall, the number, type, and distribution of cells can be custom designed, leading to versatile 3D compartments within these hydrogel microparticles as shown in Fig. 16.

4.2.1.1 Cell encapsulation and culture in microgels. In the simplest case, cell-laden microgels can be prepared by encapsulating cells in W/O emulsions, followed by gelation. The size, shape, porosity, and mechanical properties of the microgels can be tuned by varying the channel size, flow rate, polymer concentration, and crosslinking density. All of these factors significantly affect the cell fate. Therefore, deliberate consideration of materials selection, crosslinking method, and fabrication conditions is required for production of cell-laden microgels. In general, high biocompatibility of precursors, low precursor concentration, and fast gelation kinetics under mild condition are key requirements for the formation of microgels that resemble ECM. Moreover, they need to be immediately transferred into an aqueous solution such as cell culture medium after microgel formation to retain high cell viability.¹⁹⁷

Many natural polymers including alginate,¹⁹⁸ gelatin,¹⁹⁹ collagen,²⁰⁰ agarose,¹¹⁶ and peptide²⁰¹ have been investigated for cell-laden microgels due to their biocompatibility and degradability. By virtue of their fast solidification kinetics,

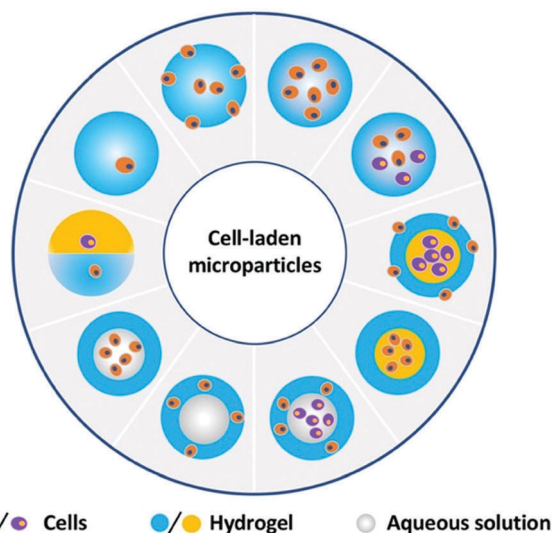


Fig. 16 Schematic illustration of cells distributed in different positions of the hydrogel microparticles.

alginate-calcium microgels have been extensively studied for cell encapsulation and culture. For instance, encapsulated breast tumor cells can form multicellular spheroids in alginate microbeads.⁵² However, the rapid ionic crosslinking between alginate and calcium ions often results in heterogeneous microgels. To resolve this issue, a method that utilizes water-soluble

calcium–ethylenediaminetetraacetic acid (Ca–EDTA) complex as a crosslinking precursor has been developed (Fig. 17a).²⁰² This method allows homogenous distribution of calcium ions within the generated alginate droplets. The dissociation of this complex is triggered by pH reduction, leading to gelation of the droplets with high homogeneity. Human mesenchymal stem cells (MSCs) were encapsulated and cultured inside these homogenous microgels for 15 days and stable cell growth and proliferation were observed. It was also reported that different shapes of cell aggregates can be produced by adjusting the concentration of alginate and CaCl_2 .²⁰³ Using this approach, human cervical carcinoma, human hepatocellular liver carcinoma and human umbilical vein endothelial cell aggregates with spherical, spindle- and branch-like shapes are successfully obtained in a controllable manner. Cell viability assay shows that more than 95% of the retrieved cells retain their proliferation ability. In addition, different types of cells can be embedded in alginate microbeads for co-culture. For example, equal amounts of HeLa and HEK293 cells were embedded in the alginate microbeads, and formed heterologous 3D spheroids after 3 days culture.²⁰⁴

Synthetic polymers can be chemically modified, unlike natural polymers, and thus have advantages for producing microgels with tunable properties by utilizing cytocompatible reactions. These polymeric materials are often incorporated in cell-laden microgels by free radical photoinitiated polymerization, among which PEG–DA has been most widely used. However, as this reaction involves use of free radicals which have

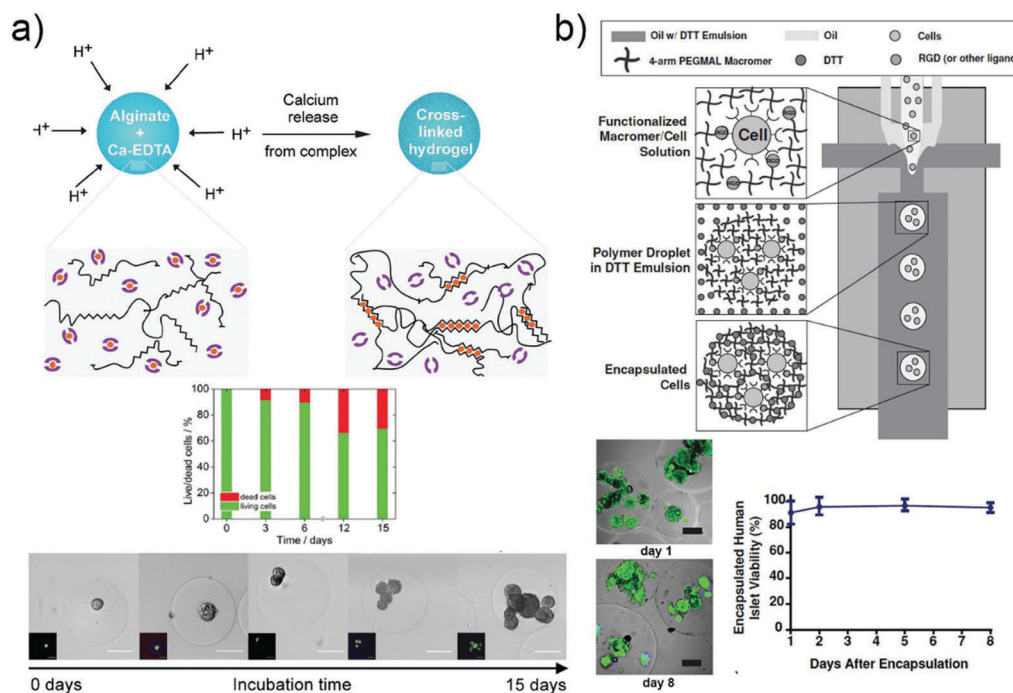


Fig. 17 Cell encapsulation and culture in microgels. (a) Formation of homogeneously crosslinked alginate microparticles by on-demand release of calcium ions from a water-soluble calcium–EDTA complex. Cell viability is determined to be 70% after 15 days culture. Microscopic images showing the stable growth and proliferation of cells.²⁰² Reprinted with permission from ref. 202. Copyright 2015, John Wiley & Sons, Inc. (b) Encapsulation of cells and proteins in PEG-4MAL microgels by using a flow-focusing microfluidic chip through a cytocompatible crosslinking reaction. Viability of cells was imaged and quantified, indicating human islets maintain high viability after culture for 8 days in microgels.²⁰⁶ Reprinted with permission from ref. 206. Copyright 2014, John Wiley & Sons, Inc.

cytotoxic effects on cells, different methods have been developed to achieve cytocompatibility. By combining the droplet microfluidic technique with bio-orthogonal thiol-ene click reactions, cell-laden microgels were fabricated without involvement of free radicals in the system. Cell-laden microgels were prepared by Michael addition of dithiolated PEG macro-crosslinkers to acrylated hyperbranched polyglycerol (hPG) building blocks.²⁰⁵ By varying the PEG molecular weight, microgels with different properties can be achieved, which affects the viability of encapsulated cells. Yeast cells in the PEG_{6.0kDa} matrix show higher viability compared to those in the PEG_{1.5kDa} matrix, due to the high diffusivity of PEG_{6.0kDa} microgel that facilitates the metabolism of encapsulated cells. Moreover, yeast cells encapsulated in PEG_{6.0kDa} microgels are able to proliferate extensively, forming huge colonies of cells. Cell-laden 4-arm PEG maleimide microgels, functionalized with cell adhesive peptides were reported, and are also crosslinked by Michael addition reaction in the presence of small molecule dithiothreitol (DTT) (Fig. 17b).²⁰⁶ Human pancreatic islets encapsulated in microgels retained viability of about 90% after 8 days of culture. This approach was shown to have almost no detrimental effect on islet cells function. PEG norbornene (PEGNB)-based droplets encapsulating cells were generated in a flow focusing microfluidic device. These cell-laden droplets were collected and then exposed to UV light in bulk solution to induce step-growth photopolymerization which is not inhibited by oxygen.²⁰⁷ The higher cytocompatibility of PEGNB over PEG-DA has been demonstrated by higher viability of cells in PEGNB microgels compared to PEG-DA microgels after long-term encapsulation.

Uniform microgels formed through reversible crosslinking have also been developed. This allows the cells to not only be encapsulated but also to be released afterwards, which benefits subsequent operations and examination for deeper understanding of the cells. Importantly, all these advantages can be achieved without any detrimental effect on their properties and functions. Cell-laden microgels with pH-cleavable properties are fabricated through azide-alkyne cycloaddition using droplet microfluidics.²⁰⁸ Here, PEG-dicyclooctyne and dendritic poly(glycerol azide) serve as bioinert hydrogel precursors. Azide conjugation was performed using different substituted acid-labile benzacetal linkers that allowed precise control of the microgel degradation kinetics in the pH range from 4.5 to 7.4; pH-controlled release of the encapsulated cells was achieved upon demand with minimum effect on cell viability and spreading. Reversibly cross-linked microgels from linear PEG precursor polymers that carry bipyridine moieties on both chain ends were also prepared.²⁰⁹ The gelation was induced by complexation of iron(II) ions with the polymers. By using this method, the encapsulated mammalian cells retained 90% cell viability. The microgels were degradable by addition of competitive ligands under very mild conditions with negligible effect on cell viability of the encapsulated as well as the released cells.

Besides using a single component, hybrid microgels can also be prepared by combination of multiple components to achieve tunable and optimized properties for cell encapsulation and culture.

For example, collagen-gelatin composite microbeads were fabricated. By varying the composition of the precursor droplets, microgels exhibited tailored mechanical properties in the range of 1–10 kPa, comparable to human tissue.²¹⁰ Enzymatically crosslinked dextran-tyramine conjugates have also been explored for on-chip microgel formation.²¹¹ When encapsulated in these microgels, MSCs demonstrated higher viability (95%) compared to alginate (81%) or PEG-DA (69%) microgels. Hydrogel microbeads embedded with Human neonatal dermal fibroblasts (HDFn) were formed from peptide-star PEG conjugates and oligosaccharides through noncovalent assembly. Cell viability as high as 98% was maintained even after 7 days of continuous culture.²⁰¹ Additional functionalities can be further afforded through both covalent and non-covalent interactions by using cell attachment sequence or biotinylated peptide.

4.2.1.2 Cell encapsulation and culture in microcapsules.

Although microgels with uniform structure are suitable carriers for cell behavior study *in vitro*, their simple structure limits their ability to mimic the 3D physical microenvironment. More sophisticated structures are thus required for complex cell culture study, such as cell-cell interaction study with controllable spatial distribution of different cells in a 3D cellular microenvironment.

Microcapsules templated from W/O/W double emulsions have also been generated for cell encapsulation, and can be categorized into two types: matrix-core/shell and liquid-core/shell microcapsules. Incorporating cells in the core of the microcapsules enhances their resistance against external effects, such as enzymatic attack and UV irradiation, and prevents them from egressing. It is also critical to rapidly transfer the cross-linked microcapsules into liquid phase to avoid any detrimental effects on the cells. Cell-laden PEG-DA and alginate/Ca²⁺ microcapsules were fabricated by utilizing droplets with an ultra-thin shell as templates in a capillary microfluidic device. Due to its large surface area, the thin oil shell spontaneously dewets upon crosslinking of the innermost precursor droplet, allowing direct dispersion of the microgels in the aqueous phase.²¹² Moreover, this thin-shell rupture approach prevents long-term exposure of cells to oil and surfactants, leading to biocompatible cell encapsulation.

Microcapsules with hydrogel-core/shell can better restrict the cells from egressing, and thus allow long-term cell culture studies. Encapsulating cell-laden PEG microbeads within a non-degradable gel shell can prevent cell escape, allowing the study of cell behavior in different microenvironments during 2 weeks of culture.²¹³ For instance, the proliferation of mouse embryonic stem cells (ESC) in microcapsules with different elasticities was studied. Cells in stiff microgels showed a lower proliferation rate and lower cell viability than in soft microgels after 4 days of culture (Fig. 18a). Microcapsules were prepared in a T-junction microfluidic device by electrostatic self-assembly of peptide amphiphiles (E₃-PA and K₃-PA).²¹⁴ The stiffness of these capsules with a fibrillar structure can be tuned by changing the peptide concentration. Human dermal fibroblasts were encapsulated within these capsules and their morphologies

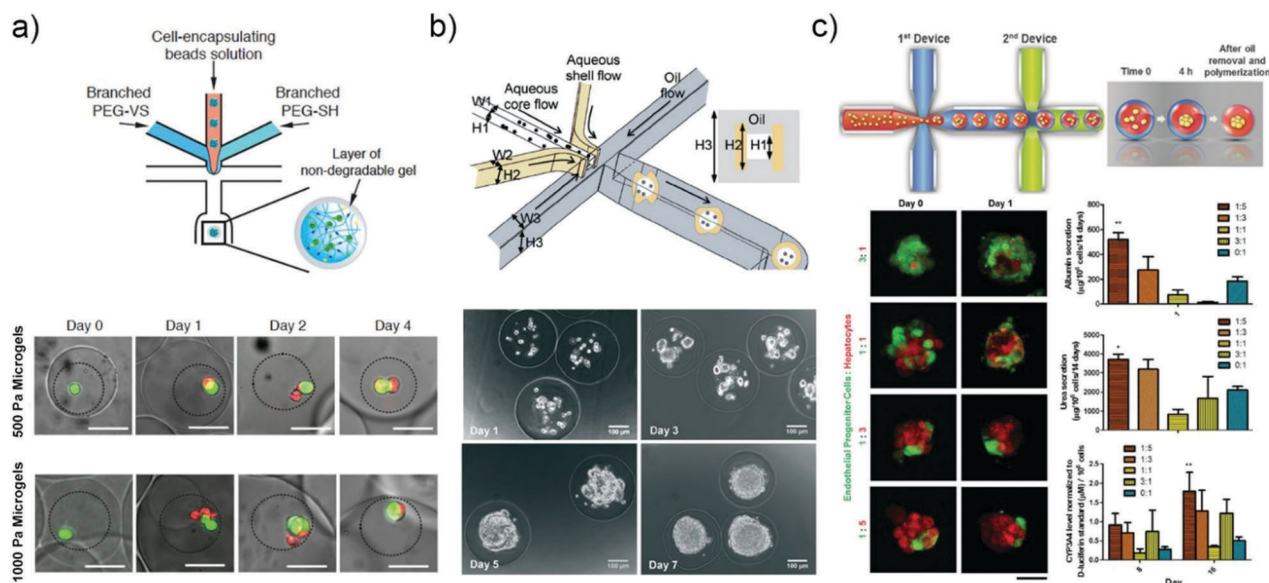


Fig. 18 Cell encapsulation and culture in microcapsules. (a) Microfluidic approach used for coencapsulation of cell containing bead-in-a-bead. Images showing the growth of ESCs encapsulated in soft and stiff microgels at different time points.²¹³ GFP marks Oct4 expression of the ESC colonies, and the dead cells exhibit red fluorescence. Reprinted with permission from ref. 213. Copyright 2015, John Wiley & Sons, Inc. (b) Generation of microcapsules by using a non-planar (3D) microfluidic flow-focusing device.²¹⁹ Phase contrast images of ES cells encapsulated in the pre-hatching embryo-like microcapsules after different number of days, showing proliferation of the cells to form a single aggregate. Reprinted with permission from ref. 219. Copyright 2013, The Royal Society of Chemistry. (c) The process of generating microencapsulated hepatocyte spheroid using double emulsion droplet generated by two connected microfluidic devices.²²⁰ Tracking of cell organization in the composite spheroids at different co-culture ratios. Functional assessments of hepatocyte with different ratio of EPC to hepatocyte. Reprinted with permission from ref. 220. Copyright 2016, John Wiley & Sons, Inc.

were studied. In 0.5 wt% E₃-PA capsules, fibroblasts exhibited extended protrusions that interacted with the fibrillar matrix, and adopted a spindle shape with fine filopodia after 7 days. After 14 days, the spread cells elongated and formed a 3D network. On the contrary, cells cultured in 1 and 2 wt% E₃-PA capsules always maintained a round shape. Further study also proved that keratinocytes can adhere to the peptide capsule surface and be cocultured with fibroblasts within the capsules.

Microcapsules with solid barcode particle core and GelMA hydrogel shell which are applicable for cell culture and drug screening were also prepared.²¹⁵ The microgel shell layer serves as a 3D ECM microenvironment for enhanced cell adhesion and culture. The photonic crystal cores of the barcode particles provide stable diffraction peaks that can encode different cell aggregates during culture and distinguish their biological response during drug testing. Different kinds of cells (HepG2, HCT-116 and NIH-3T3) were loaded on the barcode particles and cocultured as liver and tumor cell spheroids to test the cytotoxic effect of tegafur (TF). The cytotoxicity of TF against the HCT-116 tumor cell spheroids was enhanced in the multiple cell coculture system, revealing the effectiveness of this cell spheroids and barcodes platform for drug screening.

Microcapsules with liquid-core/shell structure allow encapsulated cells to form cell aggregates in the liquid core due to enhanced cell–cell interactions. This strategy is of special value for stem cell studies. For example, the comparison between P19 EC cells cultured in alginate microbeads and liquid-core/shell microcapsules shows that the latter allows formation of single

spherical embryoid body (EB) cells within 2 days.²¹⁶ In contrast, cells in the alginate microbeads only form bumpy shapes from several clusters of cells. Liquid-core/shell microcapsules were also adopted for human MSCs culture. The cells can rapidly form stem cell spheroids with controllable size (30–80 μm) in 150 min and can be retrieved *via* a droplet-releasing agent.²¹⁷ Further study proved that additional RGD-modification of the microcapsules enhanced the hMSCs osteogenic differentiation. Furthermore, liquid-core/shell microcapsules are also beneficial for pluripotent stem cells with high differentiation and self-renewal ability; culturing pluripotent stem cells in an aqueous environment with enhanced cell–cell interaction is helpful in forming 3D cell aggregates and better maintaining their stemness.²¹⁸ Similar liquid-core/shell structure was also applied to encapsulate mouse embryonic stem (ES) cells, which mimics miniaturized 3D architecture of pre-hatching embryos (Fig. 18b).²¹⁹ In each microcapsule, the cells proliferated and formed multiple small aggregates within 3 days, and further merged into a single aggregate on day 5–7 depending on the number of cells initially encapsulated in the core.

Hepatocytes are liver epithelial cells which dedifferentiate rapidly *in vitro*, resulting in low level of hepatic function. They require 3D culture systems with enhanced cell–cell interaction or co-culturing with feeder cells to rescue or enhance the liver-specific function. Microcapsules with a liquid core and polymer shell have also been applied for hepatocytes co-culture. For example, alginate or alginate/collagen double emulsion droplets encapsulating primary hepatocytes were produced using two

connected microfluidic flow-focusing PDMS devices (Fig. 18c).²²⁰ These droplets promote cell assembly within the liquid core in 4 h to form the spheroids. Microgels with single spheroids were subsequently generated upon oil removal and polymerization of the inner alginate phase. Hepatocyte functions can be further enhanced when mixed with endothelial progenitor cells at an optimal ratio of 5:1 to form co-cultured spheroids in the microgel. Microcapsules with a liquid core and PEG hydrogel shell were also used for trapping primary hepatocytes and assembling the cells into spheroids.²²¹ The hydrogel shell protects cells from shear associated with suspension cultures. High levels of hepatic function were maintained for two weeks. Furthermore, microencapsulated hepatocytes were cocultured within a 3T3 fibroblast monolayer shell, without mixing the two kinds of cells to further enhance hepatic function. This microencapsulated-spheroid formation method has high yield, versatility, and uniformity, showing great potential in liver-tissue engineering.

4.2.2 Tissue engineering and regenerative medicine.

Tissue engineering and regenerative medicine are related to the generation of biological tissue replacements for transplant and tissue culture.^{17,222} These can be used for patients who suffer from tissue damage or disease. Tissues are integrated 3D structures of multiple types of cells and ECMs. The function of a tissue is typically governed by multiple cues, such as inter-cellular signaling and cell interactions with the surrounding ECMs. Cell-laden microgel “modules” carrying different types of cells can be combined or reconfigured to mimic various types of tissues. These microgels generated from microfluidics serve as building blocks for construction of tissue engineering scaffolds. Their applications in tissue engineering, including organ-on-a-chip, bone/cartilage regeneration, stem cell culture and therapy have been extensively studied.¹⁷

4.2.2.1 3D organ/tumor models. Organs such as the liver consist of multiple cells, which are arranged in a 3D scaffold.

To mimic organs or tissues with improved functionality, 3D tissue models that have a spatial distribution of multiple different types of cells in the ECMs are required. Microgels encapsulating different types of cells are thus promising for building *in vitro* organ models for artificial tissue applications.

A 3D liver model was produced through controlled assembly of heterotypic cells in a 3D core-shell hydrogel microparticle.²²³ Microcapsules with a liquid core and an alginate hydrogel shell were generated by using a flow-focusing microfluidic device. Different types of cells were spatially distributed within the microcapsules (Fig. 19a). The hierarchical assembly of hepatocytes in the core and fibroblasts in the shell resulted in the formation of hetero-cellular spheroids. The high permeability of the alginate shell allows long-term culture (>10 days) of the spheroids to form microtissues with dense cell aggregates in the microcapsules. The core-shell structure allows co-culture of hepatocytes and fibroblasts spatially separated, which is beneficial for the expression of liver-specific functions. A large number of monodisperse microtissues, each in every microcapsule, were achieved.

Development of high-fidelity 3D models to recapitulate the tumor microenvironment is essential for high-throughput cancer drug screening and drug discovery assays. A 3D vascularized human tumor with controlled formation of a complex 3D vascular network is produced through a “bottom-up” approach (Fig. 19b).¹⁹¹ Microcapsules consisting of a fibrous collagen core enclosed in a semipermeable alginate hydrogel shell were generated. MCF-7 human mammary cancer cells were encapsulated in the core for miniaturized 3D culture, which can gradually develop into avascular microtumors after prolonged culture. The microtumors were then used as building blocks and assembled with endothelial cells and other stromal cells to form macroscale 3D vascularized tumor. Moreover, *in vitro* study illustrated that such 3D tumors are more resistant to free anticancer drugs compared to conventional 3D avascular microtumors and

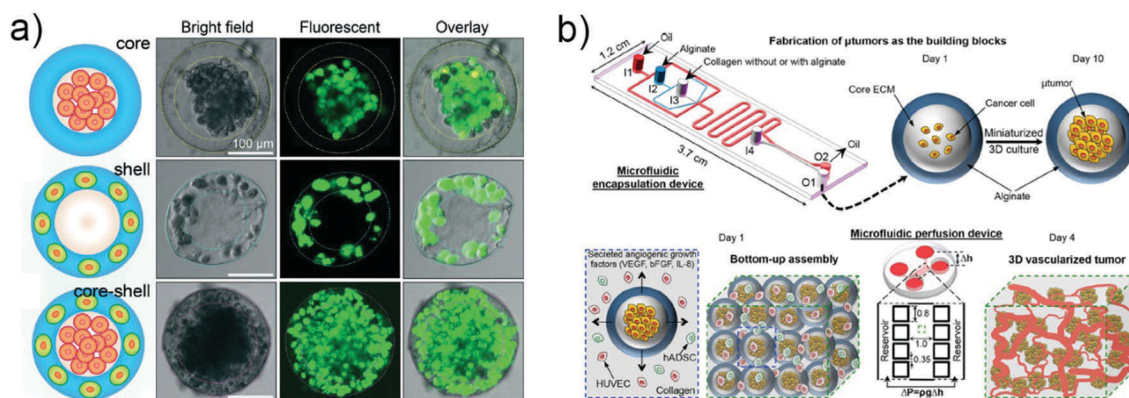


Fig. 19 (a) Spatial assembly of different cells in the 3D core-shell scaffold, including HepG2 cells confined in the core by the hydrogel shell, NIH-3T3 fibroblasts immobilized by the crosslinked alginate network in the shell, and simultaneous assembly of hepatocytes in the core and fibroblasts in the shell, forming an artificial liver in a droplet.²²³ Reprinted with permission from ref. 223. Copyright 2016, The Royal Society of Chemistry. (b) A non-planar microfluidic device is used for encapsulating cancer cells in microcapsules, and cells cultured in the microcapsules for 10 days to form microtumors.¹⁹¹ The microtumors in microcapsules are assembled together with human umbilical vein endothelial cells (HUVECs) and human adipose-derived stem cells (hADSCs) in collagen hydrogel by using microfluidic perfusion device. Reprinted with permission from ref. 191. Copyright 2017, American Chemical Society.

2D-cultured cells, but can be effectively killed by nanoparticle encapsulated drugs, demonstrating its value in anticancer drug discovery.

4.2.2.2 Injectable scaffolds. The small size of the hydrogel microparticles is particularly attractive for injectable cell delivery systems in regenerative medicine, as it allows direct delivery of cells through needles to the damaged tissue area.²²⁴ This minimizes surgical invasiveness and thus is beneficial in practical clinical applications. Gelatin-silica monodisperse microparticles were fabricated for *in vitro* cell culture scaffolds and injectable tissue constructs.⁸¹ The gelatin microgels were first prepared and cardiac side population (CSP) cells adhered on the surface of these microgels, which showed high proliferation, migration and spreading onto their cell-conductive surrounding. A thin layer of degradable silica hydrogel was then coated on the surface of these cell-laden microgels. This layer serves as an effective protection layer against oxidative stress which is detrimental to the cells during and after injection and implantation. Simultaneously, it keeps the migratory and proliferative capability of the CSP cells. In a separate work, bacterial cellulose (BC) microspheres with a hollow structure were fabricated by using agarose microgels as the template to form an injectable scaffold (Fig. 20a).²²⁵ Through assembling these hollow microspheres, a robust scaffold with high porosity was achieved. Cells loaded in this porous scaffold exhibit enhanced proliferation after culturing for 2 or 4 days. Furthermore, these hollow microspheres with cells have been used as an injectable scaffold *in vivo* for wound healing; this was tested by using a male Sprague Dawley rat skin wound-healing model. These scaffolds promoted significant and rapid wound closure due to high porosity and the ability to retain culture medium (Fig. 20b).

4.2.2.3 Stem cell therapy. Stem cells have gained considerable attention in tissue restoration and regenerative medicine due to their inherent capability of renewing and differentiating into specialized cell types.²²⁶ Microgels prepared *via* microfluidics show great promise for stem cell research,¹⁸ as stem cells can be spatially paired with suitable environmental factors to modulate their viability, growth, proliferation and differentiation.

Among stem cells, bone marrow-derived mesenchymal stem cells (BMSCs) have been widely used for bone regeneration owing to their osteogenic differentiation capability, low immunogenicity, and high proliferation ability.²²⁷ GelMA microgels encapsulating BMSCs and growth factors were produced as injectable osteogenic tissue constructs (Fig. 21a).²²⁸ GelMA microgels were able to sustain stem cell viability, support cell spreading inside the microspheres, and enhance cell proliferation (Fig. 21b). Moreover, an osteogenic growth factor, bone morphogenic protein-2 (BMP-2), was co-encapsulated within these microgels. BMSCs laden GelMA microgels, with or without BMP-2, were implanted into a rabbit femoral defect for *in vivo* bone formation evaluation. It was found that microgels with both BMSCs and BMP-2 showed synergistic therapeutic efficacy on bone formation (Fig. 21c). This work reveals that BMSCs laden GelMA microgels exhibit enhanced osteogenesis

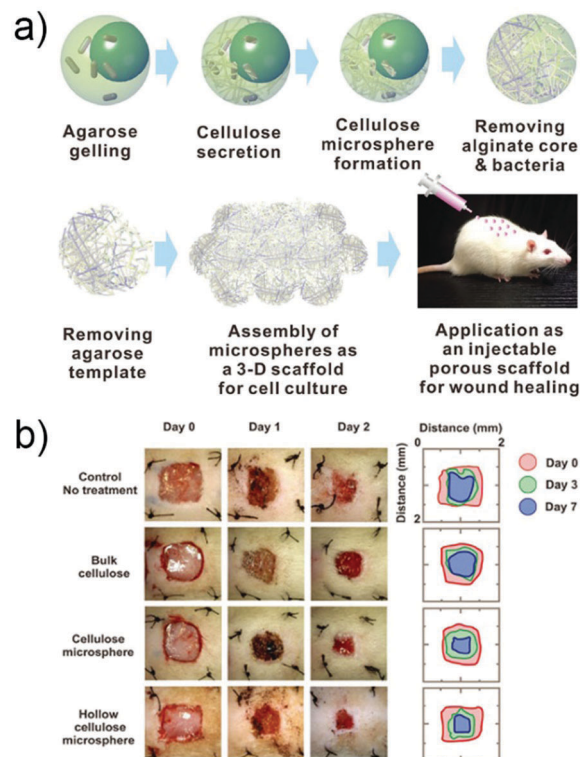


Fig. 20 (a) Schematic illustration of the steps to produce hollow bacterial cellulose microspheres.²²⁵ This includes gelling, cellulose secretion, purification, and application of the microsphere as a cell culture scaffold *in vitro* and an injectable scaffold for wound healing *in vivo*. (b) Representative images of wound closure in an *in vivo* epidermal wound-healing model in male Sprague Dawley rats and the traces of wound-bed closure for the different treatments. Reprinted with permission from ref. 225. Copyright 2016, John Wiley & Sons, Inc.

both *in vitro* and *in vivo*, making them a promising engineered injectable tissue construct for regenerative medicine. Instead of GelMA microgels that are generated under UV exposure, gelatin-based visible light curable microgels were produced by thiol-ene reaction between gelatin norbornene (GelNB) and a PEG-dithiol cross-linker.¹⁹⁹ This reaction enables rapid *in situ* microencapsulation of human BMSCs under biocompatible conditions and the cells can maintain high viability ($91 \pm 2\%$) after 7 days of culture. Moreover, the encapsulated human BMSCs exhibit rapid cell migration and considerable improvement in chondrogenic differentiation. Thus, these injectable microgels hold great promise as therapeutic candidates for articular cartilage regeneration.

4.2.3 Single cell study. Single cell study enables detection of cellular heterogeneity between large cell populations at the genomic and proteomic levels.^{229–231} The results have a significant impact on basic biology, cancer, immunology, and stem cell research. Droplet microfluidics provides an efficient method to encapsulate single cells in monodisperse microdroplets, allowing high-throughput analysis and manipulation of single cells, and thus highly sensitive assays.^{232,233} Currently, most of the microfluidic single cell studies have focused on studying a cell in a droplet. More sophisticated studies are

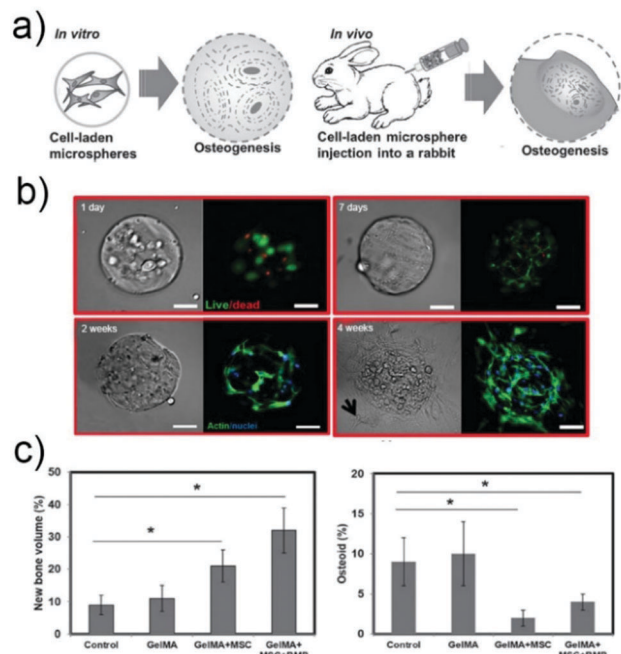


Fig. 21 (a) Schematic illustration of the application of BMSC-laden GelMA microspheres for osteogenesis and regeneration of injured bones *in vitro* and *in vivo*.²²⁸ (b) Viability of BMSCs encapsulated in GelMA after 1 and 7 d of culture. Phalloidin/DAPI images of BMSCs cultured in GelMA after 2 and 4 weeks. (c) Bone defect repair *in vivo*. Histomorphometrical analysis (%) of new bone formation and osteoid (arrows) formation and total area in the defect zone (* $p < 0.05$). Reprinted with permission from ref. 228. Copyright 2016, John Wiley & Sons, Inc.

enabled by encapsulation of cells in microgels. This allows transfer of microgels into an aqueous culture medium for prolonged cell culture. Here, we focus on the strategy of encapsulating and culturing single cells in microgels. We will also introduce the most recent progress on single-cell-laden microgels for analysis.

4.2.3.1 Single cell encapsulation and culture. Ensuring that single cells are encapsulated in each microgel can be accomplished by using the Poisson distribution. A highly diluted cell solution containing polymer is injected into a microfluidic device to create monodisperse droplets that are then solidified to obtain single cell-laden microniches. Encapsulation of single cells in a microgel with controllable properties enable studying the influence of local microenvironment on single cells. For instance, single prostate cells encapsulated in a Matrigel microbead, without any interaction with neighbouring cells, were able to proliferate and differentiate into an acinus within 6 days.²³⁴ Hyaluronic acid microbeads containing cell binding site-fibrinogen were prepared through mild biorthogonal thiol-ene click chemistry for culture of single human MSCs.²³⁵ This was the first example for long term culture of human MSCs up to 4 weeks and the cells displayed round morphology independent of mechanical property. Also, these microbeads supported the preferential differentiation of human MSCs into adipocytes after 14 days of culture.

These examples have demonstrated the potential of using microfluidics for generating single-cell-laden microgels. However, since they all follow Poisson encapsulation statistics, the majority of the microniches generated are empty. To purify the cell-laden microniches, post-encapsulation sorting is required. To overcome this problem, single cells can be encapsulated in a thin layer of alginate-calcium microgel by using a cross-junction microfluidic device (Fig. 22a).²³⁶ Cells pre-coated with calcium carbonate were delivered together with an aqueous solution of alginate polymer. Acetic acid dissolved in the oil phase mediated calcium release and resulted in the formation of microgels. The fraction of microgels containing mMSCs and pre-adipocyte cells (OP9s) dramatically increased by a factor of ten in comparison to direct injection without pre-coating. The encapsulation efficiencies were over 90% and the cells exhibited high *in vitro* cell viability over 3 days. Furthermore, increased differentiation of the cells was observed in singly encapsulated mMSCs compared to larger microgels encapsulating multiple mMSCs due to the higher ratio of cell to hydrogel matrix in singly encapsulated cells. In addition, *in vivo* study proved that intravenous injection of singly encapsulated mMSCs into mice delayed clearance kinetics and sustained donor-derived soluble factors.

Another problem for single cell study is that cells egress from the microniches during subsequent cell culture. Strategies to center cells inside the microgels have been developed to retain long term cell culture. Orbital shaking at 1000 rpm during the gelation step at 37 °C allows positioning of the cells in the center of the microniches after creation in a microfluidic device with two consecutive cross junctions.²³⁷ This strategy almost fully prevents the encapsulated cells from escape, and $79 \pm 17\%$ and $83 \pm 2\%$ of cells are viable after 7 days culture within 5% and 7.5% (w/v) polymer microniches, respectively. Another strategy for centering cells was designed by using a PDMS microfluidic chip consisting of three equally-long and high parallel channels. This enables delayed enzymatic cross-linking of tyramine-conjugated hydrogel precursor microdroplets and resulted in almost perfectly centered single cells in the microgels (Fig. 22b).²³⁸ Only $4 \pm 1\%$ cells escaped after 7 days in these centered microconstructs. The prevention of cell escape enabled long-term (28 d) culture of the MSCs and differentiation of MSCs in less than 5 μm -thick 3D hydrogel coatings. Single cell analysis revealed high cell viability ($>90\%$).

Apart from encapsulating single cells in microgels, multiple single cells can be encapsulated inside microgels in distinct compartments for the cell-cell interaction study at a single cell level. The interactions between these cells are important in regulating cell behavior by biochemical signaling cues from neighbouring cells. A one-step microfluidic approach for preparing multi-compartment microgels was developed, and a cell-cell interaction study was performed using a Janus microgel.¹⁹⁵ By encapsulating both single human MSCs and single HUVEC cells in a Janus microgel, positive ALP activity, which represents the osteogenesis of MSCs, was only observed when co-cultured with HUVECs (Fig. 22c). This biocompatible microfluidic approach can be applied for controlled cell

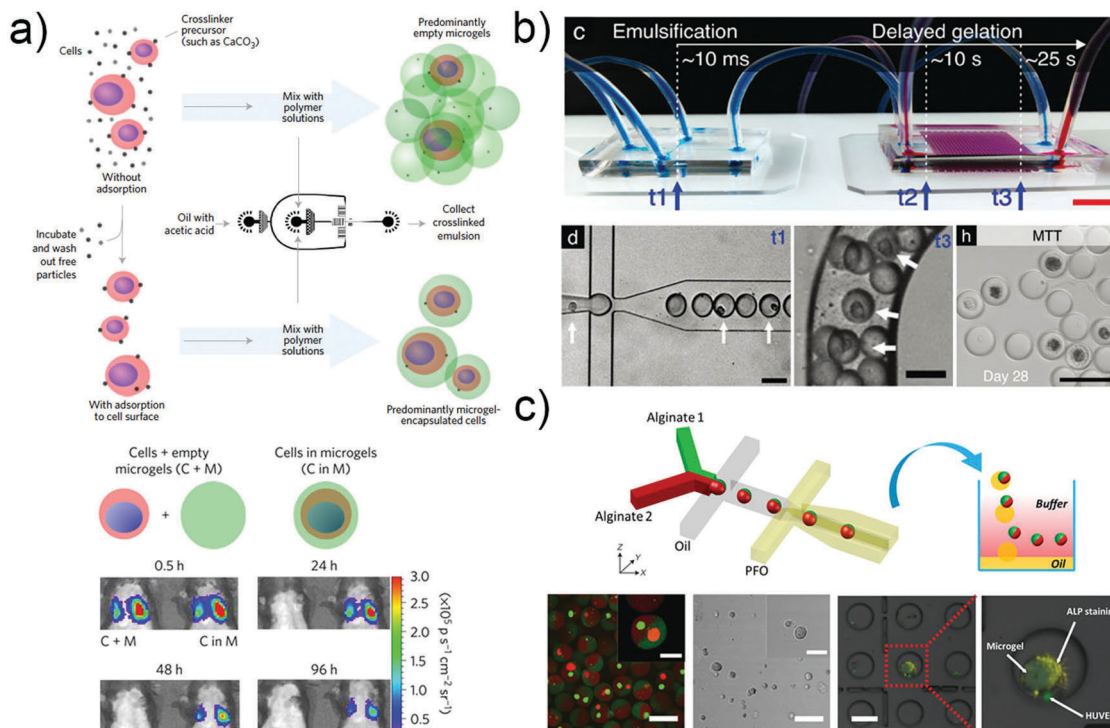


Fig. 22 Single cell encapsulation and culture. (a) Schematic showing the steps in encapsulation of single cells in thin layers of alginate gel. Representative bioluminescence images showing the biodistribution of mMSCs overexpressing Firefly luciferase with or without microgel encapsulation after *in vivo* injection.²³⁶ Reprinted with permission from ref. 236. Copyright 2017, Nature Publishing Group. (b) A standard microfluidic droplet generator was connected to the H_2O_2 diffusion-based crosslinking chip.²³⁸ The position of cells in microgel precursor droplets was analyzed immediately after droplet generation (t_1), and at the end of the crosslinking chip (t_3). MSCs encapsulated in delayed enzymatically crosslinked microgels remained viable and metabolically active throughout 28 d of *in vitro* culture. Reprinted with permission from ref. 238. Copyright 2017, John Wiley & Sons, Inc. (c) Schematic illustration of PDMS microfluidic device for the production of Janus microgels.¹⁹⁵ Each microgel contains two different cells labelled using red and green cell trackers, respectively, in adjacent compartments. The positive ALP staining assay results indicate that the presence of HUVEC favour the differentiation of MSC towards osteogenesis. Reprinted with permission from ref. 195. Copyright 2018, John Wiley & Sons, Inc.

delivery in cell immobilization and targeted reorganization, and for directed bottom-up assembly of hierarchical tissue-like structures.

4.2.3.2 Single cell modular bioinks. Single-cell-laden microgels have great potential as modular bioinks for 3D biomaterial fabrication. Engineering of multifunctional tissues by a modular approach using bioink that comprises of single-cell-laden microgels in an injectable macrogel was reported.²³⁹ The single-cell-laden PEG-DA microgels (35 μ m) were first produced by using a microfluidic flow-focusing device with a small nozzle size. After purification with fluorescence-activated cell sorting (FACS), the single-cell-laden microgels were incorporated into multiple distinct injectable macrogel precursors to effectively create several modular bioinks. These include macroconstructs of PEGDA created using photolithography and dextran-tyramine conjugates created using emulsification. They are used for the biofabrication of various 3D constructs with an independently controllable micro- and macroenvironment.

4.2.3.3 Single cell screening. Single cell screening is very important in cell biology and therapeutic applications. To perform a single cell immunoassay on a heterogeneous

population of cells, alginate microgels were used as permeable cell culture chambers for screening single cells secreting antigen-specific antibodies (Fig. 23a).²⁴⁰ A co-flow microfluidic device was used to generate alginate droplets, which encapsulated single antibody-secreting cells and high-molecular-weight capturing complexes. These droplets were used to capture the secreted antibodies, followed by solidification to form microgels. The alginate microgel had a nanometer-sized porous structure which allows easy removal of the unbound fluorescent antigens, enhancing the detection efficiency, while the cells and macromolecules were retained within the particle. This approach was employed to screen antibodies against TNF α antigen produced by single cells.

More complex structures have also been used for high throughput molecular screening. For example, microparticles composed of a polyelectrolyte shell embedded with an agarose bead have been developed.²⁴¹ The core contains transformed enzyme-producing *E. coli*, cell lysate and an enzyme-activity-sensing mixture for enzyme screening. The active enzyme triggers fluorescent signals, enabling it to be distinguished from the other, non-active enzymes. Since the inner core is gelled after the enzyme reaction, when it is cooled to 4 $^{\circ}$ C, the enzyme, the encoding plasmid, and the fluorescence signals, can

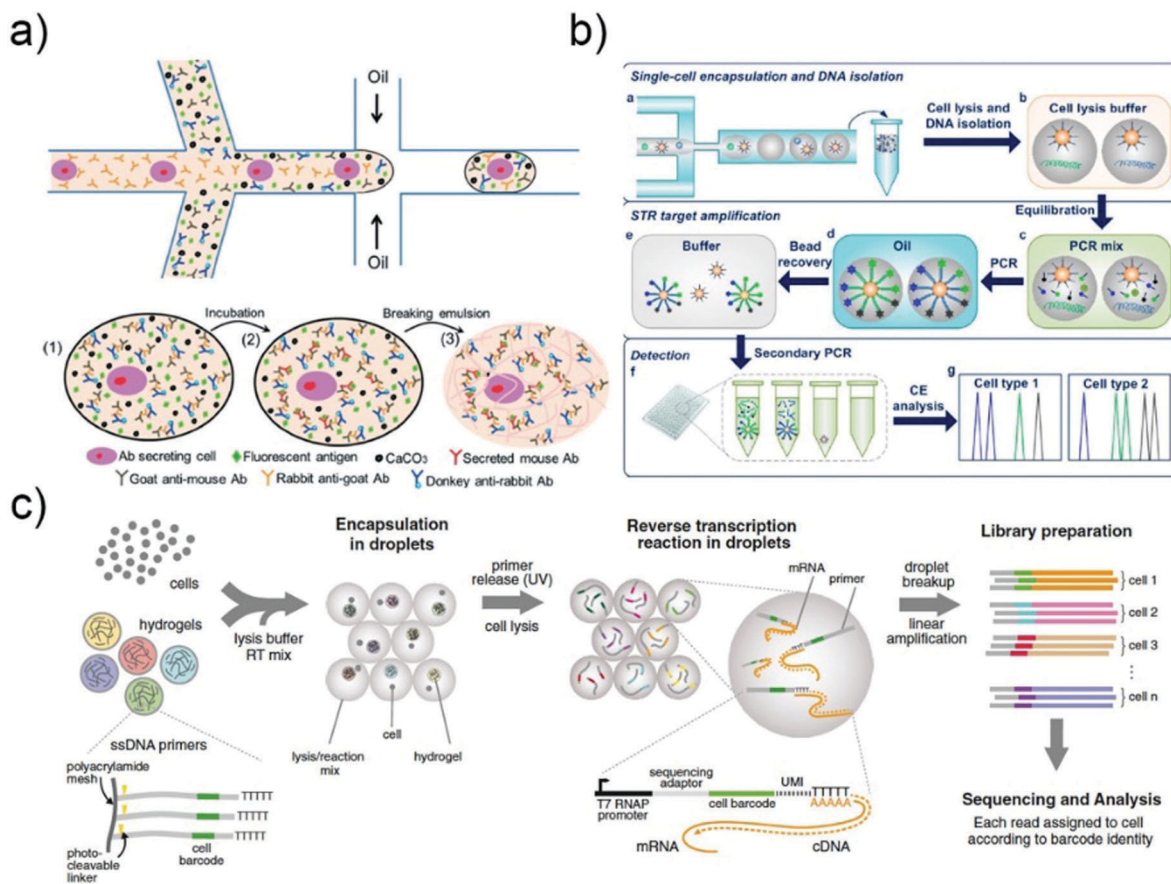


Fig. 23 (a) Schematic illustration of the heterogeneous immunoassay in alginate microparticles.²⁴⁰ Reprinted with permission from ref. 240. Copyright 2014, The Royal Society of Chemistry. (b) Analytical procedure for single-cell forensic STR typing, including encapsulation of single cells and DNA isolation, STR target amplification and STR products analysis.²⁴³ Reprinted with permission from ref. 243. Copyright 2014, American Chemical Society. (c) Platform for DNA barcoding thousands of cells.²⁴⁴ Cells are encapsulated into droplets with lysis buffer, reverse-transcription mix, and hydrogel microspheres carrying barcoded primers. After encapsulation, primers are released. cDNA in each droplet is tagged with a barcode during reverse transcription. Droplets are then broken and material from all cells is linearly amplified before sequencing. Reprinted with permission from ref. 244. Copyright 2015, Elsevier.

all be analysed well. After FACS, the polymeric shell was removed by increasing the pH above 12. Then, cells with the highest fluorescent intensity were separated and subsequently, plasmids from fluorescent cells were collected for further evolution or genomic analysis. Several rounds of selection can be carried out sequentially to obtain the best enzymatic activity.

4.2.3.4 Single cell sequencing. Mapping the gene expression at the single-cell level is very important for observing heterogeneity within cell populations. Droplet microfluidics is a powerful technology for quantitative in-depth single cell sequencing, as it allows simultaneous processing of a large number of cells.

In most of the studies, droplets containing cells and hydrogel beads are used to prepare single cells for sequencing. Only a few examples use hydrogel microparticles for single cell sequencing. An agarose gel platform was developed by using droplet microfluidics for high-throughput single-cell genetic detection and sequencing in 2011.²⁴² The same platform was used for multiplex short tandem repeat (STR) typing at the single-cell level.²⁴³ The procedures are shown in Fig. 23b. Briefly, single cells are

first encapsulated with primer-functionalized beads in nanoliter agarose droplets using a microfluidic droplet generator. Then the gelled droplets are incubated in cell lysis buffer to release genomic DNA. Small reagents can diffuse into the interior of the porous microgels, while large DNA remains within the microgels; thus, multiplex STR amplification can be realized within the nanoliter reactors. The microgels also allow mechanical manipulation and long-term storage of the microdroplets.

Polymer hydrogel microspheres generated by droplet microfluidics are also used as barcode beads for single cell sequencing. For example, a high-throughput inDrop (indexing droplets) droplet microfluidic approach was developed for indexing thousands of individual cells for RNA sequencing (Fig. 23c).²⁴⁴ A library of barcoded polyacrylamide hydrogel microspheres containing acrydite-modified DNA primer is prepared by droplet microfluidics. Then, the barcoded beads are prepared by split-pool synthesis for combinatorial addition of the barcodes. Each bead carries 10⁹ covalently coupled, photo-releasable primers encoding one of 147 456 barcodes. Because the beads are deformable, they can be loaded into drops with high precision,

with over 90% of the droplets containing exactly one bead. Cells are added at high dilution, ensuring that only very few drops are with more than a single cell. This allows a barcoded library of the genomic material from individual cells to be prepared. InDrop sequencing was evaluated by analyzing mMSCs, revealing in detail the structure of the population and the heterogeneous onset of differentiation after a leukemia inhibitory factor was withdrawn. This method has become widely used for other sequencing-based assays.

4.3 Biosensors

Biosensors are devices comprised of biological recognition elements and signal transduction elements for quantitative and semi-quantitative analysis.^{245,246} An ideal biosensor can detect analytes, such as glucose, enzymes, DNA, and antibodies in a rapid, efficient, and convenient manner. They are increasingly in demand for many biomedical applications from fundamental biological studies to clinical diagnostics. Microparticles containing sensing components prepared from droplet microfluidics have been exploited for sensing applications.²⁴⁷

One of the most widely used microparticles for biosensors are PEG-based hydrogel microparticles by virtue of their biocompatibility and antifouling properties. Single emulsion droplets coupled with UV polymerization were used to produce PEG-based microgels for sensing glucose concentrations (Fig. 24a).²⁴⁸ The functional TRITC-CoA-dextran-FITC complex was directly integrated into the microgels. TRITC-ConA is a sugar binding protein that can bind to dextran thereby quenching the fluorescent signal of FITC-dextran. In the presence of glucose, higher binding affinity of glucose to ConA than dextran results in the release of FITC-dextran from TRITC-ConA, and increases the signal proportional to the amount of glucose. Alternatively, functional sensing elements can also be introduced into microparticles through post-functionalization to further enrich their applicability for biosensing. For example, PEG microspheres containing either carboxylates or primary amines were fabricated by droplet microfluidics (Fig. 24b).²⁴⁹ These chemically functionalized microspheres can conjugate with various molecules, such as antibodies or peptide probes, which allow binding of biospecific targets for sensing or medical diagnostic applications.

The generation of microparticles with complex structures *via* droplet microfluidics enables the production of biosensors with extended properties. For instance, hollow PEG-based microcapsules were fabricated to encapsulate nanosensors such as glucose-responsive quantum dots and heparin-responsive gold nanorods in the liquid core (Fig. 24c).²⁵⁰ The microcapsules not only protect the nanosensors from the external matrix, but also allow free diffusion of biomolecules into the microcapsules. The biomolecules interact with the encapsulated nanosensors, generating detectable optical signals. These microcapsules were further immobilized into alginate calcium hydrogels for implantable detection devices. The multiplex immunoassay was realized by utilizing multicolor encoded multicompartment microcapsules (Fig. 24d).¹¹⁵ The microparticles were encoded with multiple core droplets of three distinct colors

for optical coding. The surface of the microparticles was decorated with silicon particle arrays, enabling integration of functional groups for immobilizing target biomolecules.

Other materials based hydrogel microbeads including polyacrylamide²⁵¹ and poly(acrylamide-co-acrylic acid)²⁵² can also serve as the matrix to encapsulate colloidal nanoparticles for DNA or glucose detection. Fluorescent polyacrylamide hydrogel beads were fabricated using droplet microfluidics. These monodispersed microbeads behave as highly sensitive, bio-stable, long-lasting, and injectable sensors that can continuously monitor the glucose level *in vivo* (Fig. 24e).²⁵³

Microparticle sensors are not limited to the detection of biomolecules; other microsensors which can detect microenvironment conditions, such as temperature, osmolyte concentration, pH, *etc.*, have also been prepared by droplet microfluidics. Microcapsules with a semipermeable membrane have been reported to directly measure the osmolyte concentration in the media.²⁵⁴ By having an ultra-thin shell with known osmolarity solution inside, highly sensitive sensors that detect a small amount of sample have been demonstrated. When injected to the target area, microcapsules either shrink or swell depending on the difference in the osmolyte concentration across the shell membrane. This sensor does not require any delicate equipment. Microparticle-based microsensors that sense the temperature variation can be produced by encapsulating temperature sensitive materials, such as PNIPAM-based gels,²⁵⁵ or temperature dependent photonic liquid crystals.²⁵⁶ The temperature sensitive materials were encapsulated either inside the core or in the shell of the microparticles, endowing them with reversible color and spectral shifts upon temperature changes.²⁵⁵

4.4 Artificial cells

Artificial cells are micrometer-sized systems that are able to mimic or substitute some of the functional characteristics of living cells.²⁰ They typically have a semi-permeable membrane, similar to living cells, which encloses cell constituents. Artificial cells enable a deeper understanding of the cellular functions and the origin of life. They can also accelerate the development of biomedical applications, including cell substitution, gene therapy, and targeted drug delivery. However, it is an immense challenge to generate artificial cells that can mimic real cellular structure and function.

Droplet microfluidics can be used to produce multicompartment microparticles to serve as artificial cells with well-designed functions. Liposomes, polymersomes and polymer microcapsules are three typical structures which can be generated by droplet microfluidics to resemble natural cells. Since natural cell membranes are composed of lipid bilayers, most research on artificial cells uses liposomes as basic models (Fig. 25a).²⁵⁷ Although the first unilamellar liposome templated by the W/O/W emulsion was published as early as 2006,²⁵⁸ their application as artificial cells was long bottlenecked by the existence of trace oil between the lipid bilayers. This may change the natural state of membrane proteins or the way they are integrated onto the membrane.¹⁰¹ Fortunately, this problem was partly resolved

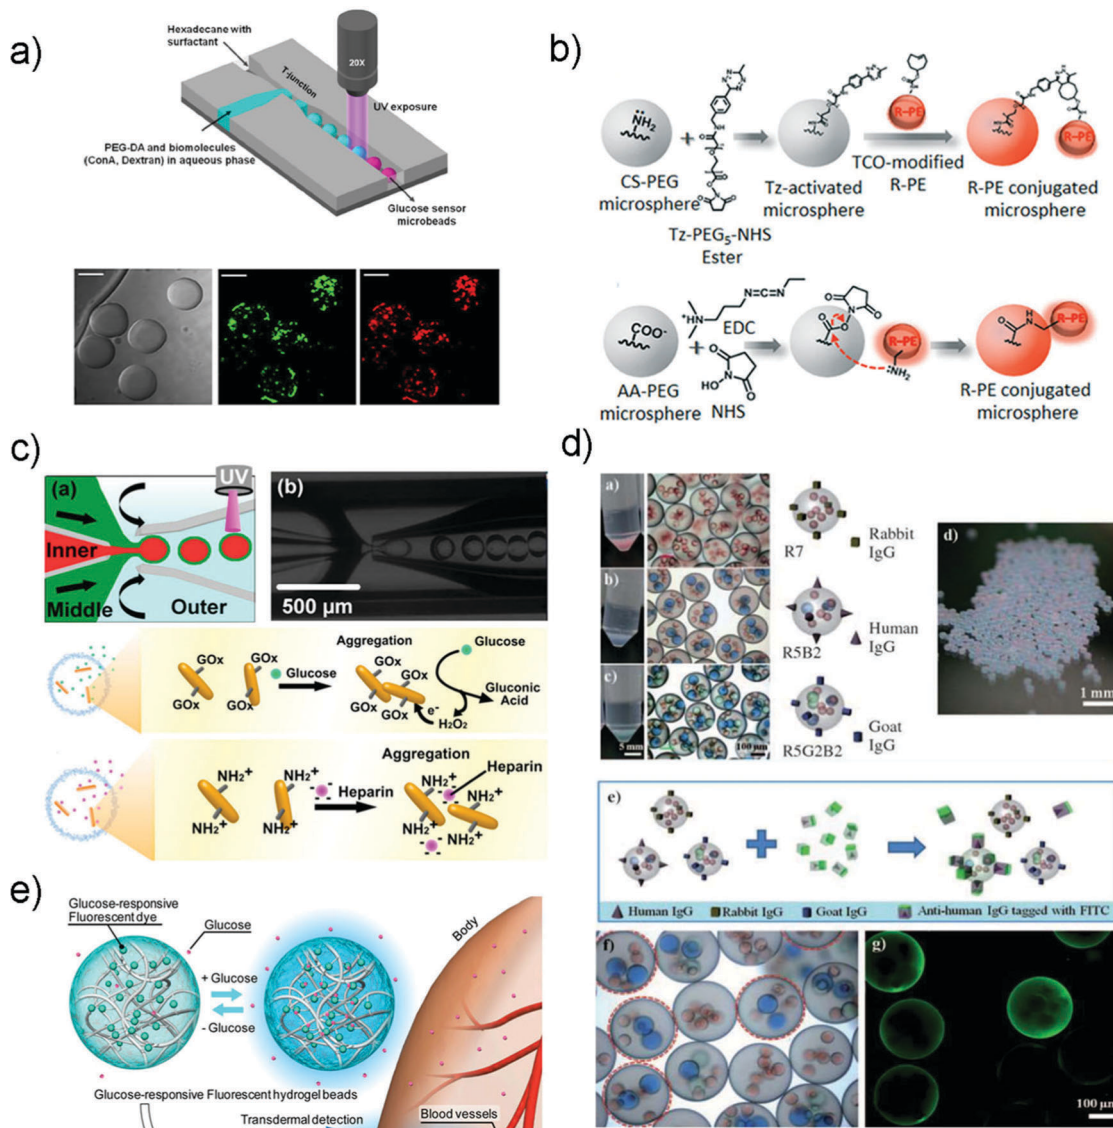


Fig. 24 Microparticle-based biosensors. (a) PEG-based microparticles produced in PDMS device for measuring the concentration of glucose *in vitro*.²⁴⁸ Reprinted with permission from ref. 248. Copyright 2012, AIP Publishing. (b) Microcapsule-based biosensor encapsulating quantum dots or gold nanorods for the detection of glucose and heparin.²⁴⁹ Reprinted with permission from ref. 249. Copyright 2018, The Royal Society of Chemistry. (c) Hydrogel microspheres with tunable chemical functionalities for biomolecular conjugation reactions.²⁵⁰ Reprinted with permission from ref. 250. Copyright 2017, American Chemical Society. (d) Microparticles encoded with colored core droplets and functionalized silica nanoparticles for multiplex immunoassay.¹¹⁵ Reprinted with permission from ref. 115. Copyright 2011, John Wiley & Sons, Inc. (e) Microparticle biosensors for monitoring the glucose concentration *in vivo*.²⁵³ Reprinted with permission from ref. 253. Copyright 2010, National Academy of Sciences.

by utilizing surfactant assisted dewetting processes.^{259,260} Both octanol²⁵⁹ and Pluronic F-68²⁶⁰ have a strong tendency to lower the surface tension of lipid membranes, leading to complete dewetting and thus formation of oil-free liposomes. Liposomes with a more complex structure, named vesosome have also been generated to better mimic cell functions. These include two-compartment liposomes,²⁶¹ multi-lamellar²⁶² and multivesicular liposomes.^{260,263} For example, a two-step approach was used to form vesosomes, including concentric, pericentric and multi-compartment structures (Fig. 25b).²⁶⁴ Hierarchical vesosomes were generated by sequential dewetting of lipid-bilayer-templated liposomes. To mimic the biofunctions, the inner liposome

modelled the nucleus, and was filled with an *in vitro* transcription mixture that allowed for RNA generation.

Transportation of small ions from “nucleus” to cytoplasm was also achieved by integration of transmembrane nanopores which should enable RNA transfer. Membrane composition is another important factor for designing artificial cells. Natural cell membranes are asymmetric and have varied regional microdomains,²⁶⁵ which can be generated by droplet microfluidic techniques.^{97,206,266} Asymmetric phospholipids based liposomes have been generated by a droplet emulsion-transfer method.²⁶⁶ A tetra-layer system was constructed, where a single-layer emulsion can move through the different layers by gravity

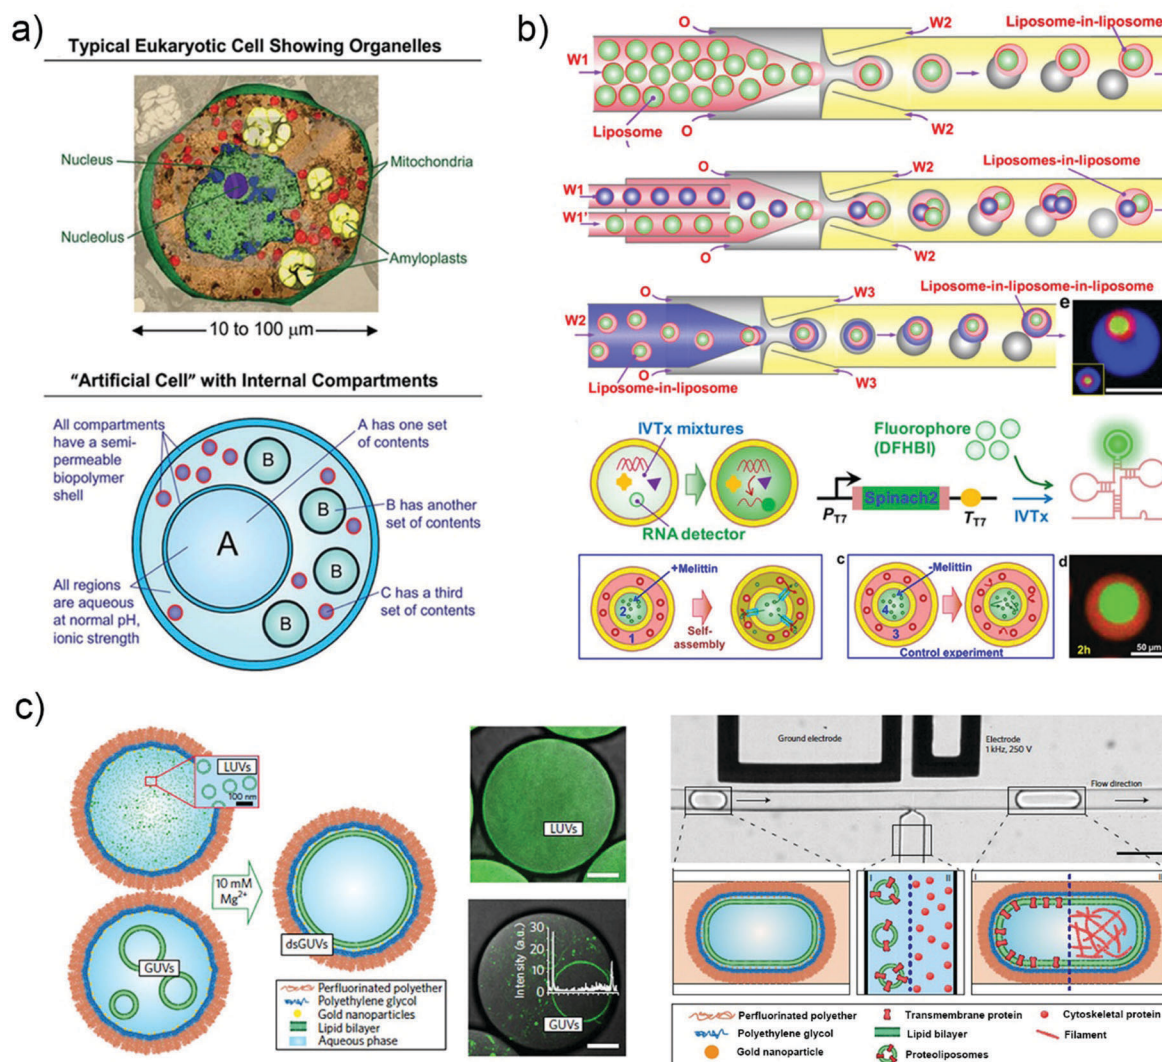


Fig. 25 Microfluidic microparticle based artificial cells. (a) Demonstration of the typical structure of eukaryotic cells and corresponding artificial cells.²⁵⁷ Reprinted with permission from ref. 257. Copyright 2017, The Royal Society of Chemistry. (b) Schematics and snapshots of the microfluidic preparation of vesosomes from emulsion dewetting and their application for molecular recognition reaction, membrane protein expression and integration.²⁶⁴ Reprinted with permission from ref. 264. Copyright 2017, American Chemical Society. (c) dsGUV cell-like compartments encapsulated in water-in-oil copolymer-stabilized droplets.²⁷⁰ Representative combined images of green fluorescence from lipids (ATTO 488-labelled DOPE) and bright-field microscopy of the encapsulated LUVs. Schematic representation of the process for incorporating transmembrane and cytoskeletal proteins into dsGUVs using high-throughput droplet-based pico-injection technology. Reprinted with permission from ref. 270. Copyright 2018, Nature Publishing Group.

induced sedimentation; it is subsequently coated with a second lipid layer with different compositions. Vesicles with controlled micro-domains on lipid bilayers were successfully generated by using double emulsions as templates. A solution of lipids dissolved in a mixture of a highly volatile good solvent and a less volatile poor solvent is used as the middle oil phase in double emulsion droplets. The evaporation of the good solvent triggered the dewetting of the less volatile poor solvent and subsequently formed micro-domains.

Polymersomes, composed of amphiphilic block copolymers, have many features that make them superior structures as artificial cells by comparison to liposomes. They are more stable than liposomes due to the molecular size and structure of the polymers, and they can be custom-tailored to have

diverse properties. For example, their permeability can be tuned by varying the polymer compositions.²⁶⁷ Biocompatible and biodegradable polymersomes with multicompartments,²⁶⁸ and double bilayers²⁶⁹ have been developed to mimic the properties of cells. For instance, polymersome-based artificial cells for protein expression, aggregation and triggered release have been reported.²⁶⁷ These polymersomes were produced from double-emulsion templates by glass capillary devices, where PEG-*b*-PLA copolymers and an *in vitro* protein expression mixture were used as the middle phase and the inner phase, respectively. The stable structure of these polymersomes provides an isolated environment to encapsulate different cell contents and allows monitoring of long-term reactions. The cytoskeletal actin-like protein MreB was expressed using

in vitro transcription and translation. These proteins inside the polymersomes can be trigger-released by osmolarity difference across the semi-permeable membrane, and the polymersomes can self-heal afterwards.

Multicompartment polymer microcapsules were fabricated using only aqueous media to mimic eukaryotic cells.²⁵⁷ Briefly, anionic alginate was infused from a capillary device into a container filled with cationic chitosan and CaCl_2 to drive the crosslinking. Cell-mimicking membrane was formed immediately upon contact between anionic and cationic biopolymers. The resulting small capsules were then mixed with alginate and extruded as the aqueous phase to another capillary device to form multicompartment structures. Their applicability as artificial cells was confirmed by embedding two groups of *E. coli* as sensors: one for generating target molecules and one for responding to the target molecules.

The stability of the artificial cells can be further enhanced by combining the merits of both liposomes and polymersomes (Fig. 25c).²⁷⁰ An AuNPs@PEG@perfluorinated polyether multilayer structure was used as a shell to stabilize liposomes. Small and giant unilamellar liposomes were produced by accurately tuning the concentration of encapsulated lipids. In addition, both membrane and cytoskeleton proteins have been effectively loaded into the structures by pico-injection. Subsequently, *in vitro* expression of integrin and its integration to the cell membrane were demonstrated. Moreover, integrin mediated cellular interactions with both BSA and fibrinogen-coated glasses were characterized. The results revealed that the artificial cells can effectively mimic the behavior of cell attachment as do living cells.

The advance of artificial cells constructed by droplet microfluidics has also promoted mimicry of the cellular functions. Liposome-based artificial cells are especially advantageous for research on cell membrane-based functions, where structuring of the membranes,^{97,271} integration of membrane proteins^{259,261} and transmembrane reactions,^{261,272–274} have been explored. Encapsulation of protein expression systems in artificial cells and subsequent integration of membrane protein are of special value for “bottom-up” functioning of artificial cells.²⁷⁵ Despite these advances, there are still challenges for future development. For example, segmented transmembrane reactions inside artificial cells are still not well developed because of the difficulty in generating functional vesosome structures. Although this limitation has been partially resolved,^{263,264} it remains a challenge to achieve RNA transport from the nucleus to the cytoplasm, or transport of the Krebs cycle product through the mitochondria membrane. The instability of artificial liposomes also precludes the possibility of carrying out cellular reactions under harsh conditions. In contrast, polymersomes can be more stable, and are easier to fabricate as complex structures such as multi-segment structures. However, applications of polymersomes besides protein expression and controlled release are still in the early stage of development.

5. Challenges and perspective

Recent advances in droplet microfluidic technology have enabled production of uniform microparticles with well-defined

structures, and multiple functionalities. Diverse microfluidic devices have been developed to generate complex droplet templates. Moreover, various materials and solidification methods have been exploited to produce microparticles encapsulating bioactives for different applications. Despite these encouraging achievements, there remain challenges to be resolved to realize the broader applicability of these microparticles in biomedical fields.

5.1 Microparticles production

Although droplet microfluidic technology is easy to use in the lab for microparticle production, it is still not feasible to employ them outside an academic lab.²⁷⁶ The lack of robustness and high cost of devices are two main concerns. For instance, capillary-based devices are resistant to organic solvent, and the particles can be produced by various chemical reactions. However, they have to be delicately made one by one by hand, especially when producing particles with complex structures by using assembled devices. Alternatively, PDMS or other polymer-based devices fabricated by lithographic techniques can alleviate this limitation. These devices, even with complicated geometries, can be precisely designed and replicated to produce microparticles on demand. However, the cost of production of the particles or other structures remains relatively high.

Another concern is the scale-up and mass production of microparticles. With droplet microfluidics, microparticles are fabricated droplet-by-droplet, which is far below the production rate of traditional bulk emulsification methods. A typical single droplet generator can produce droplets with throughput in the range of $0.1\text{--}10\text{ mL h}^{-1}$, while typically rates above L h^{-1} , are required for commercial-scale manufacturing. Some strategies have been reported to scale-up generation of droplets,^{36,277} among which parallelization of multiple droplet generators has been developed sufficiently to attain commercially viable flow rates. Three-dimensional (3D) microchannels are designed to implement the parallelization of droplet generators. Nevertheless, there are still several critical concerns for commercial-scale manufacturing, including (1) device design to achieve an even distribution of fluids in each droplet generator, (2) device materials that are mechanically robust enough to withstand high pressure fluid injection, (3) surface wettability control of the microchannels for stable generation of droplets. Moreover, most scale-up studies are focused on production of single emulsions. High-throughput production of complex emulsions by droplet microfluidics has been less addressed.²⁷⁷ Improvement in the mass production of complex structures like multicompartment droplets are expected to meet more sophisticated applications.

5.2 Biomedical applications

Microparticles fabricated by droplet microfluidics have great potential in the fields of drug delivery, cell biology and biosensors. Materials with good biocompatibility and controlled biodegradability are required to form such microparticles. Currently, only a few types of materials from synthetic polymers to natural macromolecules have been exploited to fulfil this requirement. More biocompatible materials with optimized

functions and properties suitable for microparticle fabrication need to be further investigated.

Microparticles with sizes ranging from a few microns to hundreds of microns can be generated by droplet microfluidics. They are ideal vehicles for drug delivery through oral or subcutaneous administration. However, the ideal size of the drug-loaded particles should be at sub-micron scales to avoid occlusion of blood vessels. Although nanoscale particles can be fabricated by droplet microfluidics,^{278,279} low concentration of precursor solutions are used, which reduces the production rate. Thus, development of efficient methods for producing particles with nanoscale size is crucial for effective drug delivery.

Hydrogel microparticles produced by droplet microfluidics can serve as ideal ECM-like materials for 3D cell culture. Cytocompatible materials and reactions have been developed to generate microparticles for effective cell encapsulation and long-term 3D cell culture. However, encapsulation of cells with controlled number of cells per particle is still a big challenge, especially for single cell study. Currently, encapsulation of single cells can be achieved from precursor solutions with low cell concentration, and the results follow a Poisson distribution with only a few single-cell-laden microgels being obtained. Enhancing the efficiency of single cell encapsulation remains an obstacle that must be overcome.

Apart from the intensive research on cell encapsulation and culture, there is a growing interest in the application of these cell-laden hydrogel microparticles as therapeutics or artificial organ/tissue building blocks for tissue engineering. A very important area is the development of functional tissues with assembled multiple cells *in vitro* for tissue repair. While microparticles prepared by droplet microfluidics can be used for controlled assembly and miniaturized 3D culture of cells to form a microtissue, it is not easy to build a macro-tissue by assembling these cell-laden microparticles. 3D printing technology can form tissues using cell-laden microgels as the ink. However, it usually takes several hours to do the printing, which reduces the cell viability during the operation. Moreover, a properly organized vascular system must be incorporated into the artificial tissues, which is essential for the metabolism of embedded cells to maintain the tissues viability. Different methods have been developed to engineer the vascular networks, including generation of microchannels by using sacrificial materials, such as gelatin, alginate or LCST polymers.^{193,280} However, the size of the channels formed is typically hundreds of microns, which is far beyond that of the human vascular system. These issues need to be resolved before cell-laden microparticles can be practically used for *in vivo* tissue engineering.

Droplet microfluidics also offers great opportunity to generate cargo-loaded microparticles for cell mimicry.²⁸¹ The outcome of this research can provide insights in the understanding of the basic principles of life, and holds promise for various cell-based biomedical applications. This appealing research area is still at an early development stage, with major challenges remaining in the fabrication of microparticles with high stability, enhanced functionality, and environmental sensitivity for mimicking natural cells.

6. Conclusion

In this paper, we summarize the mechanism of droplet formation, microfluidic devices, and solidification methods to convert these droplets into microparticles with various structures. These microparticles with controlled properties and integrated functions have solved many major problems in biomedical fields. Considerable progress has been made in controlled drug delivery, 3D cell culture, artificial organ building, biomolecules sensing, and cell mimicking. More research still needs to be done to overcome the remaining challenges, and bring such engineered microparticles out of academic research and into practical applications. This paper provides a compendium of the work in droplet microfluidics that will be a valuable resource for the scientific and industrial communities.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

Financial support from the National Natural Science Foundation of China (No. 21474060, 21574078 and 21327902), the Shanghai Rising-Star Program (No. 16QA1401800), the China Scholarship Council (201606895013 and 201606210262) and the National Key R&D Program of China (2016YFA0201200) is acknowledged. This work was also supported by Basic Science Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education (NRF-2018R1D1A1B07041102), POSTECH Basic Science Research Institute, the National Science Foundation (DMR-1708729, DMR-1420570), and by the National Institutes of Health (P01GM096971, R01EB023287).

References

- 1 R. M. Hernandez, G. Orive, A. Murua and J. L. Pedraz, *Adv. Drug Delivery Rev.*, 2010, **62**, 711–730.
- 2 A. Choi, K. D. Seo, D. W. Kim, B. C. Kim and D. S. Kim, *Lab Chip*, 2017, **17**, 591–613.
- 3 L. Shang, Y. Cheng and Y. Zhao, *Chem. Rev.*, 2017, **117**, 7964–8040.
- 4 V. T. Tran, J. P. Benoit and M. C. Venier-Julienne, *Int. J. Pharm.*, 2011, **407**, 1–11.
- 5 J. Thiele, *Macromol. Chem. Phys.*, 2017, **218**, 1600429.
- 6 W. J. Duncanson, T. Lin, A. R. Abate, S. Seiffert, R. K. Shah and D. A. Weitz, *Lab Chip*, 2012, **12**, 2135–2145.
- 7 K. Saralidze, L. H. Koole and M. L. W. Knetsch, *Materials*, 2010, **3**, 3537–3564.
- 8 K. D. Seo, D. S. Kim and S. Sanchez, *Lab Chip*, 2015, **15**, 3622–3626.
- 9 D. Dendukuri and P. S. Doyle, *Adv. Mater.*, 2009, **21**, 4071–4086.
- 10 J. Yeh, Y. Ling, J. M. Karp, J. Gantz, A. Chandawarkar, G. Eng, J. Blumling Iii, R. Langer and A. Khademhosseini, *Biomaterials*, 2006, **27**, 5391–5398.

- 11 T. Y. Lee, T. M. Choi, T. S. Shim, R. A. Frijns and S. H. Kim, *Lab Chip*, 2016, **16**, 3415–3440.
- 12 J. H. Kim, T. Y. Jeon, T. M. Choi, T. S. Shim, S. H. Kim and S. M. Yang, *Langmuir*, 2014, **30**, 1473–1488.
- 13 T. Heida, J. W. Neubauer, M. Seuss, N. Hauck, J. Thiele and A. Fery, *Macromol. Chem. Phys.*, 2017, **218**, 1600418.
- 14 W. Wang, M.-J. Zhang and L.-Y. Chu, *Acc. Chem. Res.*, 2014, **47**, 373–384.
- 15 D. F. Liu, H. B. Zhang, F. Fontana, J. T. Hirvonen and H. A. Santos, *Lab Chip*, 2017, **17**, 1856–1883.
- 16 D. Velasco, E. Tumarkin and E. Kumacheva, *Small*, 2012, **8**, 1633–1642.
- 17 W. Jiang, M. Li, Z. Chen and K. W. Leong, *Lab Chip*, 2016, **16**, 4482–4506.
- 18 S. Allazetta and M. P. Lutolf, *Curr. Opin. Biotechnol.*, 2015, **35**, 86–93.
- 19 Z. Zhu and C. Y. J. Yang, *Acc. Chem. Res.*, 2017, **50**, 22–31.
- 20 T. Trantidou, M. Friddin, Y. Elani, N. J. Brooks, R. V. Law, J. M. Seddon and O. Ces, *ACS Nano*, 2017, **11**, 6549–6565.
- 21 K. Kamiya and S. Takeuchi, *J. Mater. Chem. B*, 2017, **5**, 5911–5923.
- 22 R. K. Shah, H. C. Shum, A. C. Rowat, D. Lee, J. J. Agresti, A. S. Utada, L.-Y. Chu, J.-W. Kim, A. Fernandez-Nieves, C. J. Martinez and D. A. Weitz, *Mater. Today*, 2008, **11**, 18–27.
- 23 S. Seiffert, *Macromol. Rapid Commun.*, 2011, **32**, 1600–1609.
- 24 Y. Li, M. Jain, Y. Ma and K. Nandakumar, *Soft Matter*, 2015, **11**, 3884–3899.
- 25 D. R. Link, E. Grasland-Mongrain, A. Duri, F. Sarrazin, Z. Cheng, G. Cristobal, M. Marquez and D. A. Weitz, *Angew. Chem., Int. Ed.*, 2006, **45**, 2556–2560.
- 26 J.-P. Huang, X.-H. Ge, J.-H. Xu and G.-S. Luo, *Chem. Eng. Sci.*, 2016, **152**, 293–300.
- 27 Q. Yan, S. Xuan, X. Ruan, J. Wu and X. Gong, *Microfluid. Nanofluid.*, 2015, **19**, 1377–1384.
- 28 K. Maeda, H. Onoe, M. Takinoue and S. Takeuchi, *Adv. Mater.*, 2012, **24**, 1340–1346.
- 29 R. Suryo and O. A. Basaran, *Phys. Fluids*, 2006, **18**, 082102.
- 30 P. G. Zhu, T. T. Kong, Z. X. Kang, X. W. Tian and L. Q. Wang, *Sci. Rep.*, 2015, **5**, 11102.
- 31 P. Zhu and L. Wang, *Lab Chip*, 2017, **17**, 34–75.
- 32 Z. Z. Chong, S. H. Tan, A. M. Ganan-Calvo, S. B. Tor, N. H. Loh and N. T. Nguyen, *Lab Chip*, 2016, **16**, 35–58.
- 33 A. Ofner, D. G. Moore, P. A. Rühls, P. Schwendimann, M. Eggersdorfer, E. Amstad, D. A. Weitz and A. R. Studart, *Macromol. Chem. Phys.*, 2016, **218**, 1600472.
- 34 Z. Li, A. M. Leshansky, L. M. Pismen and P. Tabeling, *Lab Chip*, 2015, **15**, 1023–1031.
- 35 S. Sahin, O. Bliznyuk, A. Roalino Cordova and K. Schroën, *Sci. Rep.*, 2016, **6**, 26407.
- 36 E. Amstad, M. Chemama, M. Eggersdorfer, L. R. Arriaga, M. P. Brenner and D. A. Weitz, *Lab Chip*, 2016, **16**, 4163–4172.
- 37 S. Sugiura, M. Nakajima, J. Tong, H. Nabetani and M. Seki, *J. Colloid Interface Sci.*, 2000, **227**, 95–103.
- 38 S. Sugiura, M. Nakajima, N. Kumazawa, S. Iwamoto and M. Seki, *J. Phys. Chem. B*, 2002, **106**, 9405–9409.
- 39 S. Sahin and K. Schroen, *Lab Chip*, 2015, **15**, 2486–2495.
- 40 S. Kahkeshani and D. Di Carlo, *Lab Chip*, 2016, **16**, 2474–2480.
- 41 F. Schuler, F. Schwemmer, M. Trotter, S. Wadle, R. Zengerle, F. von Stetten and N. Paust, *Lab Chip*, 2015, **15**, 2759–2766.
- 42 E. Stolovicki, R. Ziblat and D. A. Weitz, *Lab Chip*, 2018, **18**, 132–138.
- 43 M. L. Eggersdorfer, W. Zheng, S. Nawar, C. Mercandetti, A. Ofner, I. Leibacher, S. Koehler and D. A. Weitz, *Lab Chip*, 2017, **17**, 936–942.
- 44 A. S. Utada, E. Lorenceau, D. R. Link, P. D. Kaplan, H. A. Stone and D. A. Weitz, *Science*, 2005, **308**, 537–541.
- 45 L.-Y. Chu, A. S. Utada, R. K. Shah, J.-W. Kim and D. A. Weitz, *Angew. Chem.*, 2007, **119**, 9128–9132.
- 46 B. J. Sun, H. C. Shum, C. Holtze and D. A. Weitz, *ACS Appl. Mater. Interfaces*, 2010, **2**, 3411–3416.
- 47 W. Wang, R. Xie, X. J. Ju, T. Luo, L. Liu, D. A. Weitz and L. Y. Chu, *Lab Chip*, 2011, **11**, 1587–1592.
- 48 C.-H. Choi, H. Lee, A. Abbaspourrad, J. H. Kim, J. Fan, M. Caggioni, C. Wesner, T. Zhu and D. A. Weitz, *Adv. Mater.*, 2016, **28**, 3340–3344.
- 49 S.-H. Kim, J. W. Kim, J.-C. Cho and D. A. Weitz, *Lab Chip*, 2011, **11**, 3162–3166.
- 50 S.-H. Kim, J. W. Kim, D.-H. Kim, S.-H. Han and D. A. Weitz, *Microfluid. Nanofluid.*, 2013, **14**, 509–514.
- 51 J. Clausell-Tormos, D. Lieber, J.-C. Baret, A. El-Harrak, O. J. Miller, L. Frenz, J. Blouwolff, K. J. Humphry, S. Köster, H. Duan, C. Holtze, D. A. Weitz, A. D. Griffiths and C. A. Merten, *Chem. Biol.*, 2008, **15**, 427–437.
- 52 L. Yu, M. C. Chen and K. C. Cheung, *Lab Chip*, 2010, **10**, 2424–2432.
- 53 J. R. Anderson, D. T. Chiu, R. J. Jackman, O. Cherniavskaya, J. C. McDonald, H. Wu, S. H. Whitesides and G. M. Whitesides, *Anal. Chem.*, 2000, **72**, 3158–3164.
- 54 J. C. McDonald, M. L. Chabinyc, S. J. Metallo, J. R. Anderson, A. D. Stroock and G. M. Whitesides, *Anal. Chem.*, 2002, **74**, 1537–1545.
- 55 P. Garstecki, M. J. Fuerstman, H. A. Stone and G. M. Whitesides, *Lab Chip*, 2006, **6**, 437–446.
- 56 T. Ward, M. Faivre, M. Abkarian and H. A. Stone, *Electrophoresis*, 2005, **26**, 3716–3724.
- 57 A. R. Abate, A. Poitzsch, Y. Hwang, J. Lee, J. Czerwinska and D. A. Weitz, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2009, **80**, 026310.
- 58 J. A. Vickers, M. M. Caulum and C. S. Henry, *Anal. Chem.*, 2006, **78**, 7446–7452.
- 59 J. Zhou, D. A. Khodakov, A. V. Ellis and N. H. Voelcker, *Electrophoresis*, 2012, **33**, 89–104.
- 60 G. T. Roman, T. Hlaus, K. J. Bass, T. G. Seelhammer and C. T. Culbertson, *Anal. Chem.*, 2005, **77**, 1414–1422.
- 61 A. R. Abate, A. T. Krummel, D. Lee, M. Marquez, C. Holtze and D. A. Weitz, *Lab Chip*, 2008, **8**, 2157–2160.
- 62 A. R. Abate, J. Thiele, M. Weinhardt and D. A. Weitz, *Lab Chip*, 2010, **10**, 1774–1776.
- 63 C.-H. Choi, H. Lee and D. A. Weitz, *ACS Appl. Mater. Interfaces*, 2018, **10**, 3170–3174.

- 64 J.-O. Kim, H. Kim, D.-H. Ko, K.-I. Min, D. J. Im, S.-Y. Park and D.-P. Kim, *Lab Chip*, 2014, **14**, 4270–4276.
- 65 A. M. Nightingale, S. H. Krishnadasan, D. Berhanu, X. Niu, C. Drury, R. McIntyre, E. Valsami-Jones and J. C. deMello, *Lab Chip*, 2011, **11**, 1221–1227.
- 66 D. Lidia, G. Laura, L. Alfio, M. Giacomo, N. Alfio and R. Marco, *J. Micromech. Microeng.*, 2015, **25**, 035013.
- 67 T. Femmer, A. Jans, R. Eswein, N. Anwar, M. Moeller, M. Wessling and A. J. C. Kuehne, *ACS Appl. Mater. Interfaces*, 2015, **7**, 12635–12638.
- 68 C. Martino, S. Berger, R. C. R. Wootton and A. J. deMello, *Lab Chip*, 2014, **14**, 4178–4182.
- 69 S. Waheed, J. M. Cabot, N. P. Macdonald, T. Lewis, R. M. Guijt, B. Paull and M. C. Breadmore, *Lab Chip*, 2016, **16**, 1993–2013.
- 70 K. G. Lee, K. J. Park, S. Seok, S. Shin, D. H. Kim, J. Y. Park, Y. S. Heo, S. J. Lee and T. J. Lee, *RSC Adv.*, 2014, **4**, 32876–32880.
- 71 S. Yang and D. L. DeVoe, in *Microfluidic Diagnostics: Methods and Protocols*, ed. G. Jenkins and C. D. Mansfield, Humana Press, Totowa, NJ, 2013, pp. 115–123.
- 72 P. N. Nge, C. I. Rogers and A. T. Woolley, *Chem. Rev.*, 2013, **113**, 2550–2583.
- 73 R. Liedert, L. K. Amundsen, A. Hokkanen, M. Maki, A. Aittakorpi, M. Pakanen, J. R. Scherer, R. A. Mathies, M. Kurkinen, S. Uusitalo, L. Hakalahti, T. K. Nevanen, H. Siitari and H. Soderlund, *Lab Chip*, 2012, **12**, 333–339.
- 74 X. Wang, C. Liedert, R. Liedert and I. Papautsky, *Lab Chip*, 2016, **16**, 1821–1830.
- 75 X. Wang, C. Liedert, R. Liedert and I. Papautsky, *Lab Chip*, 2016, **16**, 1821–1830.
- 76 S. D. Hann, K. J. Stebe and D. Lee, *Langmuir*, 2017, **33**, 10107–10117.
- 77 T. Rossow, P. S. Lienemann and D. J. Mooney, *Macromol. Chem. Phys.*, 2017, **218**, 1600380.
- 78 W. J. Jeong, J. Y. Kim, J. Choo, E. K. Lee, C. S. Han, D. J. Beebe, G. H. Seong and S. H. Lee, *Langmuir*, 2005, **21**, 3738–3741.
- 79 S. Guo, T. Yao, X. Ji, C. Zeng, C. Wang and L. Zhang, *Angew. Chem., Int. Ed.*, 2014, **53**, 7504–7509.
- 80 H. Liu, X. Qian, Z. Wu, R. Yang, S. Sun and H. Ma, *J. Mater. Chem. B*, 2016, **4**, 482–488.
- 81 C. Cha, J. Oh, K. Kim, Y. Qiu, M. Joh, S. R. Shin, X. Wang, G. Camci-Unal, K.-t. Wan, R. Liao and A. Khademhosseini, *Biomacromolecules*, 2014, **15**, 283–290.
- 82 K. G. Lee, T. J. Park, S. Y. Soo, K. W. Wang, B. I. I. Kim, J. H. Park, C.-S. Lee, D. H. Kim and S. J. Lee, *Biotechnol. Bioeng.*, 2010, **107**, 747–751.
- 83 J.-W. Kim, A. S. Utada, A. Fernández-Nieves, Z. Hu and D. A. Weitz, *Angew. Chem., Int. Ed.*, 2007, **46**, 1819–1822.
- 84 H. Gu, B. Ye, H. Ding, C. Liu, Y. Zhao and Z. Gu, *J. Mater. Chem. C*, 2015, **3**, 6607–6612.
- 85 N. Visaveliya and J. M. Kohler, *J. Mater. Chem. C*, 2015, **3**, 844–853.
- 86 T. Nisisako and T. Hatsuzawa, *Microfluid. Nanofluid.*, 2010, **9**, 427–437.
- 87 D. V. Amato, H. Lee, J. G. Werner, D. A. Weitz and D. L. Patton, *ACS Appl. Mater. Interfaces*, 2017, **9**, 3288–3293.
- 88 Y. Zhao, H. C. Shum, L. L. A. Adams, B. Sun, C. Holtze, Z. Gu and D. A. Weitz, *Langmuir*, 2011, **27**, 13988–13991.
- 89 T. A. Comunian, A. Abbaspourrad, C. S. Favaro-Trindade and D. A. Weitz, *Food Chem.*, 2014, **152**, 271–275.
- 90 S. Sugiura, T. Oda, Y. Izumida, Y. Aoyagi, M. Satake, A. Ochiai, N. Ohkohchi and M. Nakajima, *Biomaterials*, 2005, **26**, 3327–3331.
- 91 H. Zhang, E. Tumarkin, R. Peerani, Z. Nie, R. M. A. Sullan, G. C. Walker and E. Kumacheva, *J. Am. Chem. Soc.*, 2006, **128**, 12205–12210.
- 92 W. H. Tan and S. Takeuchi, *Adv. Mater.*, 2007, **19**, 2696–2701.
- 93 Q. Xu, M. Hashimoto, T. T. Dang, T. Hoare, D. S. Kohane, G. M. Whitesides, R. Langer and D. G. Anderson, *Small*, 2009, **5**, 1575–1581.
- 94 T. Watanabe, T. Ono and Y. Kimura, *Soft Matter*, 2011, **7**, 9894–9897.
- 95 M. F. Haase and J. Brujic, *Angew. Chem., Int. Ed.*, 2014, **53**, 11793–11797.
- 96 H. C. Shum, J.-W. Kim and D. A. Weitz, *J. Am. Chem. Soc.*, 2008, **130**, 9543–9549.
- 97 L. R. Arriaga, S. S. Datta, S.-H. Kim, E. Amstad, T. E. Kodger, F. Monroy and D. A. Weitz, *Small*, 2014, **10**, 950–956.
- 98 N. G. Min, M. Ku, J. Yang and S.-H. Kim, *Chem. Mater.*, 2016, **28**, 1430–1438.
- 99 W. Shi and D. A. Weitz, *Macromolecules*, 2017, **50**, 7681–7686.
- 100 C.-H. Choi, D. A. Weitz and C.-S. Lee, *Adv. Mater.*, 2013, **25**, 2536–2541.
- 101 D. van Swaay and A. deMello, *Lab Chip*, 2013, **13**, 752–767.
- 102 S.-H. Kim, H. C. Shum, J. W. Kim, J.-C. Cho and D. A. Weitz, *J. Am. Chem. Soc.*, 2011, **133**, 15165–15171.
- 103 E. Amstad, S.-H. Kim and D. A. Weitz, *Angew. Chem., Int. Ed.*, 2012, **51**, 12499–12503.
- 104 B.-U. Moon, N. Abbasi, S. G. Jones, D. K. Hwang and S. S. H. Tsai, *Anal. Chem.*, 2016, **88**, 3982–3989.
- 105 Y. Song, A. Sauret and H. Cheung Shum, *Biomechanics*, 2013, **7**, 061301.
- 106 B.-U. Moon, S. G. Jones, D. K. Hwang and S. S. H. Tsai, *Lab Chip*, 2015, **15**, 2437–2444.
- 107 A. Sauret, *Appl. Phys. Lett.*, 2012, **100**, 154106.
- 108 I. Ziemecka, V. van Steijn, G. J. Koper, M. Rosso, A. M. Brizard, J. H. van Esch and M. T. Kreutzer, *Lab Chip*, 2011, **11**, 620–624.
- 109 S. Ma, J. Thiele, X. Liu, Y. Bai, C. Abell and W. T. Huck, *Small*, 2012, **8**, 2356–2360.
- 110 R. Ameloot, F. Vermoortele, W. Vanhove, M. B. J. Roelofs, B. F. Sels and D. E. De Vos, *Nat. Chem.*, 2011, **3**, 382–387.
- 111 L. Liu, J.-P. Yang, X.-J. Ju, R. Xie, Y.-M. Liu, W. Wang, J.-J. Zhang, C. H. Niu and L.-Y. Chu, *Soft Matter*, 2011, **7**, 4821–4827.
- 112 M. Kim, S. J. Yeo, C. B. Highley, J. A. Burdick, P. J. Yoo, J. Doh and D. Lee, *ACS Nano*, 2015, **9**, 8269–8278.
- 113 L. Y. Zhang, L. H. Cai, P. S. Lienemann, T. Rossow, I. Polenz, Q. Vallmajo-Martin, M. Ehrbar, H. Na, D. J. Mooney and D. A. Weitz, *Angew. Chem., Int. Ed.*, 2016, **55**, 13470–13474.

- 114 L. Shang, F. Shangguan, Y. Cheng, J. Lu, Z. Xie, Y. Zhao and Z. Gu, *Nanoscale*, 2013, **5**, 9553–9557.
- 115 S. H. Kim, J. W. Shim and S. M. Yang, *Angew. Chem., Int. Ed.*, 2011, **50**, 1171–1174.
- 116 A. Kumachev, J. Greener, E. Tumarkin, E. Eiser, P. W. Zandstra and E. Kumacheva, *Biomaterials*, 2011, **32**, 1477–1483.
- 117 N. Raz, J. K. Li, L. K. Fiddes, E. Tumarkin, G. C. Walker and E. Kumacheva, *Macromolecules*, 2010, **43**, 7277–7281.
- 118 Y.-S. Lin, C.-H. Yang, Y.-Y. Hsu and C.-L. Hsieh, *Electrophoresis*, 2013, **34**, 425–431.
- 119 S. Xu, Z. Nie, M. Seo, P. Lewis, E. Kumacheva, H. A. Stone, P. Garstecki, D. B. Weibel, I. Gitlin and G. M. Whitesides, *Angew. Chem., Int. Ed.*, 2005, **44**, 724–728.
- 120 S.-H. Kim, A. Abbaspourrad and D. A. Weitz, *J. Am. Chem. Soc.*, 2011, **133**, 5516–5524.
- 121 T. Nisisako and T. Torii, *Adv. Mater.*, 2007, **19**, 1489–1493.
- 122 N.-N. Deng, W. Wang, X.-J. Ju, R. Xie, D. A. Weitz and L.-Y. Chu, *Lab Chip*, 2013, **13**, 4047–4052.
- 123 S. S. Datta, A. Abbaspourrad, E. Amstad, J. Fan, S.-H. Kim, M. Romanowsky, H. C. Shum, B. Sun, A. S. Utada, M. Windbergs, S. Zhou and D. A. Weitz, *Adv. Mater.*, 2014, **26**, 2205–2218.
- 124 Z. Nie, W. Li, M. Seo, S. Xu and E. Kumacheva, *J. Am. Chem. Soc.*, 2006, **128**, 9408–9412.
- 125 K. P. Yuet, D. K. Hwang, R. Haghighoie and P. S. Doyle, *Langmuir*, 2010, **26**, 4281–4287.
- 126 R. K. Shah, J.-W. Kim and D. A. Weitz, *Adv. Mater.*, 2009, **21**, 1949–1953.
- 127 Y. Zhao, H. C. Shum, H. Chen, L. L. A. Adams, Z. Gu and D. A. Weitz, *J. Am. Chem. Soc.*, 2011, **133**, 8790–8793.
- 128 Y. Zhao, Z. Xie, H. Gu, L. Jin, X. Zhao, B. Wang and Z. Gu, *NPG Asia Mater.*, 2012, **4**, e25.
- 129 S. Seiffert, M. B. Romanowsky and D. A. Weitz, *Langmuir*, 2010, **26**, 14842–14847.
- 130 H. Lee, C.-H. Choi, A. Abbaspourrad, C. Wesner, M. Caggioni, T. Zhu, S. Nawar and D. Weitz, *Adv. Mater.*, 2016, **28**, 8425–8430.
- 131 S. Huang, B. Lin and J. Qin, *Electrophoresis*, 2011, **32**, 3364–3370.
- 132 C.-L. Mou, X.-J. Ju, L. Zhang, R. Xie, W. Wang, N.-N. Deng, J. Wei, Q. Chen and L.-Y. Chu, *Langmuir*, 2014, **30**, 1455–1464.
- 133 L. Y. Chu, J. W. Kim, R. K. Shah and D. A. Weitz, *Adv. Funct. Mater.*, 2007, **17**, 3499–3504.
- 134 J. Wan, A. Bick, M. Sullivan and H. A. Stone, *Adv. Mater.*, 2008, **20**, 3314–3318.
- 135 X. Gong, W. Wen and P. Sheng, *Langmuir*, 2009, **25**, 7072–7077.
- 136 W. J. Duncanson, M. Zieringer, O. Wagner, J. N. Wilking, A. Abbaspourrad, R. Haag and D. A. Weitz, *Soft Matter*, 2012, **8**, 10636–10640.
- 137 T. Watanabe, C. G. Lopez, J. F. Douglas, T. Ono and J. T. Cabral, *Langmuir*, 2014, **30**, 2470–2479.
- 138 T. S. Shim, S. H. Kim and S. M. Yang, *Part. Part. Syst. Charact.*, 2013, **30**, 9–45.
- 139 R. Vasiliauskas, D. F. Liu, S. Cito, H. B. Zhang, M. A. Shahbazi, T. Sikanen, L. Mazutis and H. A. Santos, *ACS Appl. Mater. Interfaces*, 2015, **7**, 14822–14832.
- 140 F. Araujo, N. Shrestha, M. A. Shahbazi, D. F. Liu, B. Herranz-Blanco, E. M. Makila, J. J. Salonen, J. T. Hirvonen, P. L. Granja, B. Sarmento and H. A. Santos, *ACS Nano*, 2015, **9**, 8291–8302.
- 141 C. X. Zhao, *Adv. Drug Delivery Rev.*, 2013, **65**, 1420–1446.
- 142 C. H. Yang, K. S. Huang and J. Y. Chang, *Biomed. Microdevices*, 2007, **9**, 253–259.
- 143 J. H. Xu, H. Zhao, W. J. Lan and G. S. Luo, *Adv. Healthcare Mater.*, 2012, **1**, 106–111.
- 144 B. Lu, M. D. Tarn, N. Pamme and T. K. Georgiou, *J. Mater. Chem. B*, 2016, **4**, 3086–3093.
- 145 T. Y. Lee, M. Ku, B. Kim, S. Lee, J. Yang and S. H. Kim, *Small*, 2017, **13**, 11.
- 146 H. Lee, C.-H. Choi, A. Abbaspourrad, C. Wesner, M. Caggioni, T. Zhu and D. Weitz, *ACS Appl. Mater. Interfaces*, 2016, **8**, 4007–4013.
- 147 Y. N. Li, D. Yan, F. F. Fu, Y. X. Liu, B. Zhang, J. Wang, L. R. Shang, Z. Gu and Y. Zhao, *Sci. China Mater.*, 2017, **60**, 543–553.
- 148 F. He, W. Wang, X. H. He, X. L. Yang, M. Li, R. Xie, X. J. Ju, Z. Liu and L. Y. Chu, *ACS Appl. Mater. Interfaces*, 2016, **8**, 8743–8754.
- 149 P. Pradhan, J. Giri, F. Rieken, C. Koch, O. Mykhaylyk, M. Döblinger, R. Banerjee, D. Bahadur and C. Plank, *J. Controlled Release*, 2010, **142**, 108–121.
- 150 K. Zhang, W. Wu, K. Guo, J. Chen and P. Zhang, *Langmuir*, 2010, **26**, 7971–7980.
- 151 A. San Miguel, J. Scrimgeour, J. E. Curtis and S. H. Behrens, *Soft Matter*, 2010, **6**, 3163–3166.
- 152 K. E. Broaders, S. J. Pastine, S. Grandhe and J. M. J. Fréchet, *Chem. Commun.*, 2011, **47**, 665–667.
- 153 L. Cui, J. L. Cohen, C. K. Chu, P. R. Wich, P. H. Kierstead and J. M. J. Fréchet, *J. Am. Chem. Soc.*, 2012, **134**, 15840–15848.
- 154 K. Kooiman, M. R. Böhmer, M. Emmer, H. J. Vos, C. Chlon, W. T. Shi, C. S. Hall, S. H. P. M. de Winter, K. Schroën, M. Versluis, N. de Jong and A. van Wamel, *J. Controlled Release*, 2009, **133**, 109–118.
- 155 A. M. Pavlov, V. Saez, A. Cobley, J. Graves, G. B. Sukhorukov and T. J. Mason, *Soft Matter*, 2011, **7**, 4341–4347.
- 156 M. Ochs, S. Carregal-Romero, J. Rejman, K. Braeckmans, S. C. De Smedt and W. J. Parak, *Angew. Chem.*, 2013, **125**, 723–727.
- 157 D. Volodkin, A. Skirtach and H. Möhwald, *Polym. Int.*, 2012, **61**, 673–679.
- 158 S. J. Pastine, D. Okawa, A. Zettl and J. M. J. Fréchet, *J. Am. Chem. Soc.*, 2009, **131**, 13586–13587.
- 159 A. Giteau, M. C. Venier-Julienne, A. Aubert-Pouessel and J. P. Benoit, *Int. J. Pharm.*, 2008, **350**, 14–26.
- 160 C. Loira-Pastoriza, J. Todoroff and R. Vanbever, *Adv. Drug Delivery Rev.*, 2014, **75**, 81–91.
- 161 X. Huang and C. S. Brazel, *J. Controlled Release*, 2001, **73**, 121–136.
- 162 L. Devez, J. Ashoken, G. Castaneda, X. Tong, M. Keeney, L.-H. Han and F. Yang, *ACS Biomater. Sci. Eng.*, 2015, **1**, 157–165.
- 163 B. Kim, T. Y. Lee, A. Abbaspourrad and S.-H. Kim, *Chem. Mater.*, 2014, **26**, 7166–7171.

- 164 J. Li and D. J. Mooney, *Nat. Rev. Mater.*, 2016, **1**, 16071.
- 165 J. H. Zhou, D. C. Hyun, H. Liu, H. K. Wu and Y. N. Xia, *Macromol. Rapid Commun.*, 2014, **35**, 1436–1442.
- 166 U. Shimanovich, I. Efimov, T. O. Mason, P. Flagmeier, A. K. Buell, A. Gedanken, S. Linse, K. S. Åkerfeldt, C. M. Dobson, D. A. Weitz and T. P. J. Knowles, *ACS Nano*, 2015, **9**, 43–51.
- 167 D. F. Liu, B. Herranz-Blanco, E. Makila, L. R. Arriaga, S. Mirza, D. A. Weitz, N. Sandler, J. Salonen, J. Hirvonen and H. A. Santos, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12127–12134.
- 168 J. Huang, W. Li, Y. Li, C. Luo, Y. Zeng, Y. Xu and J. Zhou, *J. Mater. Chem. B*, 2014, **2**, 6848–6854.
- 169 D. Liu, H. Zhang, B. Herranz-Blanco, E. Makila, V. P. Lehto, J. Salonen, J. Hirvonen and H. A. Santos, *Small*, 2014, **10**, 2029–2038.
- 170 H. B. Zhang, D. F. Liu, M. A. Shahbazi, E. Makila, B. Herranz-Blanco, J. Salonen, J. Hirvonen and H. A. Santos, *Adv. Mater.*, 2014, **26**, 4497–4503.
- 171 S. Maher, A. Santos, T. Kumeria, G. Kaur, M. Lambert, P. Forward, A. Evdokiou and D. Losic, *J. Mater. Chem. B*, 2017, **5**, 4097–4109.
- 172 K. S. Huang, C. H. Yang, C. P. Kung, A. M. Grumezescu, M. D. Ker, Y. S. Lin and C. Y. Wang, *Electrophoresis*, 2014, **35**, 330–336.
- 173 J. Wei, X. J. Ju, X. Y. Zou, R. Xie, W. Wang, Y. M. Liu and L. Y. Chu, *Adv. Funct. Mater.*, 2014, **24**, 3312–3323.
- 174 D. Liu, J. Chen, T. Jiang, W. Li, Y. Huang, X. Lu, Z. Liu, W. Zhang, Z. Zhou, Q. Ding, H. A. Santos, G. Yin and J. Fan, *Adv. Mater.*, 2018, **30**, 1706032.
- 175 L. Liu, W. Wang, X.-J. Ju, R. Xie and L.-Y. Chu, *Soft Matter*, 2010, **6**, 3759–3763.
- 176 S. Seiffert, J. Thiele, A. R. Abate and D. A. Weitz, *J. Am. Chem. Soc.*, 2010, **132**, 6606–6609.
- 177 W. C. Jeong, S. H. Kim and S. M. Yang, *ACS Appl. Mater. Interfaces*, 2014, **6**, 826–832.
- 178 X. L. Yang, X. J. Ju, X. T. Mu, W. Wang, R. Xie, Z. Liu and L. Y. Chu, *ACS Appl. Mater. Interfaces*, 2016, **8**, 10524–10534.
- 179 W. Zhang, A. Abbaspourrad, D. Chen, E. Campbell, H. Zhao, Y. Li, Q. Li and D. A. Weitz, *Adv. Funct. Mater.*, 2017, **27**, 1700975.
- 180 A. R. Duarte, B. Unal, J. F. Mano, R. L. Reis and K. F. Jensen, *Langmuir*, 2014, **30**, 12391–12399.
- 181 B. Radt, T. A. Smith and F. Caruso, *Adv. Mater.*, 2004, **16**, 2184–2189.
- 182 R. Weissleder, *Nat. Biotechnol.*, 2001, **19**, 316–317.
- 183 B. Kim, H. Soo Lee, J. Kim and S. H. Kim, *Chem. Commun.*, 2013, **49**, 1865–1867.
- 184 M. H. Lee, K. C. Hribar, T. Brugarolas, N. P. Kamat, J. A. Burdick and D. Lee, *Adv. Funct. Mater.*, 2012, **22**, 131–138.
- 185 Z. Yu, Y. Zheng, R. M. Parker, Y. Lan, Y. Wu, R. J. Coulston, J. Zhang, O. A. Scherman and C. Abell, *ACS Appl. Mater. Interfaces*, 2016, **8**, 8811–8820.
- 186 Z. Liu, L. Liu, X.-J. Ju, R. Xie, B. Zhang and L.-Y. Chu, *Chem. Commun.*, 2011, **47**, 12283–12285.
- 187 X.-H. Ge, J.-P. Huang, J.-H. Xu and G.-S. Luo, *Lab Chip*, 2014, **14**, 4451–4454.
- 188 G. Huang, F. Li, X. Zhao, Y. Ma, Y. Li, M. Lin, G. Jin, T. J. Lu, G. M. Genin and F. Xu, *Chem. Rev.*, 2017, **117**, 12764–12850.
- 189 H. Huang, Y. Yu, Y. Hu, X. He, O. Berk Usta and M. L. Yarmush, *Lab Chip*, 2017, **17**, 1913–1932.
- 190 N. Shembekar, C. Chaipan, R. Utharala and C. A. Merten, *Lab Chip*, 2016, **16**, 1314–1331.
- 191 P. Agarwal, H. Wang, M. Sun, J. Xu, S. Zhao, Z. Liu, K. J. Gooch, Y. Zhao, X. Lu and X. He, *ACS Nano*, 2017, **11**, 6691–6702.
- 192 B. G. Chung, K. H. Lee, A. Khademhosseini and S. H. Lee, *Lab Chip*, 2012, **12**, 45–59.
- 193 D. B. Kolesky, R. L. Truby, A. S. Gladman, T. A. Busbee, K. A. Homan and J. A. Lewis, *Adv. Mater.*, 2014, **26**, 3124–3130.
- 194 Š. Selimović, J. Oh, H. Bae, M. Dokmeci and A. Khademhosseini, *Polymers*, 2012, **4**, 1554–1579.
- 195 L. Zhang, K. Chen, H. Zhang, B. Pang, C. H. Choi, A. S. Mao, H. Liao, S. Utech, D. J. Mooney, H. Wang and D. A. Weitz, *Small*, 2018, **14**, 1702955.
- 196 Z. Liu and H. C. Shum, *Biomicrofluidics*, 2013, **7**, 44117.
- 197 M. Sun, P. Durkin, J. Li, T. L. Toth and X. He, *ACS Sens.*, 2018, **3**, 410–417.
- 198 C. J. Martinez, J. W. Kim, C. Ye, I. Ortiz, A. C. Rowat, M. Marquez and D. Weitz, *Macromol. Biosci.*, 2012, **12**, 946–951.
- 199 F. Li, V. X. Truong, H. Thissen, J. E. Frith and J. S. Forsythe, *ACS Appl. Mater. Interfaces*, 2017, **9**, 8589–8601.
- 200 M. Yamada, A. Hori, S. Sugaya, Y. Yajima, R. Utoh, M. Yamato and M. Seki, *Lab Chip*, 2015, **15**, 3941–3951.
- 201 R. Wieduwild, S. Krishnan, K. Chwalek, A. Boden, M. Nowak, D. Drechsel, C. Werner and Y. Zhang, *Angew. Chem., Int. Ed.*, 2015, **54**, 3962–3966.
- 202 S. Utech, R. Prodanovic, A. S. Mao, R. Ostafe, D. J. Mooney and D. A. Weitz, *Adv. Healthcare Mater.*, 2015, **4**, 1628–1633.
- 203 Y. Wang, L. Zhao, C. Tian, C. Ma and J. Wang, *Anal. Methods*, 2015, **7**, 10040–10051.
- 204 S. Yoon, J. A. Kim, S. H. Lee, M. Kim and T. H. Park, *Lab Chip*, 2013, **13**, 1522–1528.
- 205 T. Rossow, J. A. Heyman, A. J. Ehrlicher, A. Langhoff, D. A. Weitz, R. Haag and S. Seiffert, *J. Am. Chem. Soc.*, 2012, **134**, 4983–4989.
- 206 D. M. Headen, G. Aubry, H. Lu and A. J. Garcia, *Adv. Mater.*, 2014, **26**, 3003–3008.
- 207 Z. Jiang, B. Xia, R. McBride and J. Oakey, *J. Mater. Chem. B*, 2017, **5**, 173–180.
- 208 D. Steinhilber, T. Rossow, S. Wedepohl, F. Paulus, S. Seiffert and R. Haag, *Angew. Chem., Int. Ed.*, 2013, **52**, 13538–13543.
- 209 T. Rossow, S. Bayer, R. Albrecht, C. C. Tzschucke and S. Seiffert, *Macromol. Rapid Commun.*, 2013, **34**, 1401–1407.
- 210 S. H. Ma, M. Natoli, X. Liu, M. P. Neubauer, F. M. Watt, A. Fery and W. T. S. Huck, *J. Mater. Chem. B*, 2013, **1**, 5128–5136.

- 211 S. Henke, J. Leijten, E. Kemna, M. Neubauer, A. Fery, A. van den Berg, A. van Apeldoorn and M. Karperien, *Macromol. Biosci.*, 2016, **16**, 1524–1532.
- 212 C.-H. Choi, H. Wang, H. Lee, J. H. Kim, L. Zhang, A. Mao, D. J. Mooney and D. A. Weitz, *Lab Chip*, 2016, **16**, 1549–1555.
- 213 S. Allazetta, L. Kolb, S. Zerbib, J. Bardy and M. P. Lutolf, *Small*, 2015, **11**, 5647–5656.
- 214 D. S. Ferreira, R. L. Reis and H. S. Azevedo, *Soft Matter*, 2013, **9**, 9237–9248.
- 215 F. Fu, L. Shang, F. Zheng, Z. Chen, H. Wang, J. Wang, Z. Gu and Y. Zhao, *ACS Appl. Mater. Interfaces*, 2016, **8**, 13840–13848.
- 216 C. Kim, S. Chung, Y. E. Kim, K. S. Lee, S. H. Lee, K. W. Oh and J. Y. Kang, *Lab Chip*, 2011, **11**, 246–252.
- 217 H. F. Chan, Y. Zhang, Y. P. Ho, Y. L. Chiu, Y. Jung and K. W. Leong, *Sci. Rep.*, 2013, **3**, 3462.
- 218 G. Su, Y. Zhao, J. Wei, J. Han, L. Chen, Z. Xiao, B. Chen and J. Dai, *Biomaterials*, 2013, **34**, 3215–3222.
- 219 P. Agarwal, S. Zhao, P. Bielecki, W. Rao, J. K. Choi, Y. Zhao, J. Yu, W. Zhang and X. He, *Lab Chip*, 2013, **13**, 4525–4533.
- 220 H. F. Chan, Y. Zhang and K. W. Leong, *Small*, 2016, **12**, 2720–2730.
- 221 C. Siltanen, M. Diakatou, J. Lowen, A. Haque, A. Rahimian, G. Stybayeva and A. Revzin, *Acta Biomater.*, 2017, **50**, 428–436.
- 222 C. M. Magin, D. L. Alge and K. S. Anseth, *Biomed. Mater.*, 2016, **11**, 022001.
- 223 Q. Chen, S. Utech, D. Chen, R. Prodanovic, J. M. Lin and D. A. Weitz, *Lab Chip*, 2016, **16**, 1346–1349.
- 224 D. R. Griffin, W. M. Weaver, P. O. Scumpia, D. Di Carlo and T. Segura, *Nat. Mater.*, 2015, **14**, 737–744.
- 225 J. Yu, T. R. Huang, Z. H. Lim, R. Luo, R. R. Pasula, L. D. Liao, S. Lim and C. H. Chen, *Adv. Healthcare Mater.*, 2016, **5**, 2983–2992.
- 226 Q. Huang, Y. Zou, M. C. Arno, S. Chen, T. Wang, J. Gao, A. P. Dove and J. Du, *Chem. Soc. Rev.*, 2017, **46**, 6255–6275.
- 227 A. Geraili, P. Jafari, M. S. Hassani, B. H. Araghi, M. H. Mohammadi, A. M. Ghafari, S. H. Tamrin, H. P. Modarres, A. R. Kolahchi, S. Ahadian and A. Sanati-Nezhad, *Adv. Healthcare Mater.*, 2017, **7**, 1700426.
- 228 X. Zhao, S. Liu, L. Yildirim, H. Zhao, R. Ding, H. Wang, W. Cui and D. Weitz, *Adv. Funct. Mater.*, 2016, **26**, 2809–2819.
- 229 H. Yin and D. Marshall, *Curr. Opin. Biotechnol.*, 2012, **23**, 110–119.
- 230 S. Hosic, S. K. Murthy and A. N. Koppes, *Anal. Chem.*, 2016, **88**, 354–380.
- 231 K. Galler, K. Brautigam, C. Grosse, J. Popp and U. Neugebauer, *Analyst*, 2014, **139**, 1237–1273.
- 232 B. L. Wang, A. Ghaderi, H. Zhou, J. Agresti, D. A. Weitz, G. R. Fink and G. Stephanopoulos, *Nat. Biotechnol.*, 2014, **32**, 473–478.
- 233 L. Mazutis, J. Gilbert, W. L. Ung, D. A. Weitz, A. D. Griffiths and J. A. Heyman, *Nat. Protoc.*, 2013, **8**, 870–891.
- 234 M. E. Dolega, F. Abeille, N. Picollet-D'hahan and X. Gidrol, *Biomaterials*, 2015, **52**, 347–357.
- 235 Y. Ma, M. P. Neubauer, J. Thiele, A. Fery and W. T. S. Huck, *Biomater. Sci.*, 2014, **2**, 1661–1671.
- 236 A. S. Mao, J.-W. Shin, S. Utech, H. Wang, O. Uzun, W. Li, M. Cooper, Y. Hu, L. Zhang, D. A. Weitz and D. J. Mooney, *Nat. Mater.*, 2017, **16**, 236–243.
- 237 P. S. Lienemann, T. Rossow, A. S. Mao, Q. Vallmajomartin, M. Ehrbar and D. J. Mooney, *Lab Chip*, 2017, **17**, 727–737.
- 238 T. Kamperman, S. Henke, C. W. Visser, M. Karperien and J. Leijten, *Small*, 2017, **13**, 1603711.
- 239 T. Kamperman, S. Henke, A. van den Berg, S. R. Shin, A. Tamayol, A. Khademhosseini, M. Karperien and J. Leijten, *Adv. Healthcare Mater.*, 2017, **6**, 1600913.
- 240 S. Akbari and T. Pirbodaghi, *Lab Chip*, 2014, **14**, 3275–3280.
- 241 M. Fischlechner, Y. Schaerli, M. F. Mohamed, S. Patil, C. Abell and F. Hollfelder, *Nat. Chem.*, 2014, **6**, 791–796.
- 242 R. Novak, Y. Zeng, J. Shuga, G. Venugopalan, D. A. Fletcher, M. T. Smith and R. A. Mathies, *Angew. Chem., Int. Ed.*, 2011, **50**, 390–395.
- 243 T. Geng, R. Novak and R. A. Mathies, *Anal. Chem.*, 2014, **86**, 703–712.
- 244 Allon M. Klein, L. Mazutis, I. Akartuna, N. Tallapragada, A. Veres, V. Li, L. Peshkin, David A. Weitz and Marc W. Kirschner, *Cell*, 2015, **161**, 1187–1201.
- 245 Q. Liu and B. J. Boyd, *Analyst*, 2013, **138**, 391–409.
- 246 J. Kirsch, C. Siltanen, Q. Zhou, A. Revzin and A. Simonian, *Chem. Soc. Rev.*, 2013, **42**, 8733–8768.
- 247 G. C. Le Goff, R. L. Srinivas, W. A. Hill and P. S. Doyle, *Eur. Polym. J.*, 2015, **72**, 386–412.
- 248 C. Kantak, Q. D. Zhu, S. Beyer, T. Bansal and D. Trau, *Biomicrofluidics*, 2012, **6**, 9.
- 249 E. Y. Liu, S. Jung, D. A. Weitz, H. Yi and C.-H. Choi, *Lab Chip*, 2018, **18**, 323–334.
- 250 X. Xie, W. Zhang, A. Abbaspourrad, J. Ahn, A. Bader, S. Bose, A. Vegas, J. Lin, J. Tao and T. Hang, *Nano Lett.*, 2017, **17**, 2015–2020.
- 251 Y. Zhao, X. Zhao, B. Tang, W. Xu, J. Li, J. Hu and Z. Gu, *Adv. Funct. Mater.*, 2010, **20**, 976–982.
- 252 H. Li, D. Men, Y. Sun, T. Zhang, L. Hang, D. Liu, C. Li, W. Cai and Y. Li, *Nanotechnology*, 2017, **28**, 405502.
- 253 H. Shibata, Y. J. Heo, T. Okitsu, Y. Matsunaga, T. Kawanishi, S. Takeuchi and M. E. Davis, *Proc. Natl. Acad. Sci. U. S. A.*, 2010, **107**, 17894–17898.
- 254 T. M. Choi, J.-G. Park, Y.-S. Kim, V. N. Manoharan and S.-H. Kim, *Chem. Mater.*, 2015, **27**, 1014–1020.
- 255 T. Kanai, D. Lee, H. C. Shum, R. K. Shah and D. A. Weitz, *Adv. Mater.*, 2010, **22**, 4998–5002.
- 256 S. S. Lee, B. Kim, S. K. Kim, J. C. Won, Y. H. Kim and S. H. Kim, *Adv. Mater.*, 2015, **27**, 627–633.
- 257 A. X. Lu, H. Oh, J. L. Terrell, W. E. Bentley and S. R. Raghavan, *Chem. Sci.*, 2017, **8**, 6893–6903.
- 258 Y. C. Tan, K. Hettiarachchi, M. Siu and Y. P. Pan, *J. Am. Chem. Soc.*, 2006, **128**, 5656–5658.
- 259 S. Deshpande, Y. Caspi, A. E. C. Meijering and C. Dekker, *Nat. Commun.*, 2016, **7**, 10447.

- 260 N.-N. Deng, M. Yelleswarapu and W. T. S. Huck, *J. Am. Chem. Soc.*, 2016, **138**, 7584–7591.
- 261 Y. Elani, R. V. Law and O. Ces, *Nat. Commun.*, 2014, **5**, 5305.
- 262 S. Matosevic and B. M. Paegel, *Nat. Chem.*, 2013, **5**, 958–963.
- 263 N. Nuti, P. E. Verboket and P. S. Dittrich, *Lab Chip*, 2017, **17**, 3112–3119.
- 264 N. N. Deng, M. Yelleswarapu, L. Zheng and W. T. Huck, *J. Am. Chem. Soc.*, 2017, **139**, 587–590.
- 265 C. G. Siontorou, G. P. Nikoleli, D. P. Nikolelis and S. K. Karapetis, *Membranes*, 2017, **7**, 38.
- 266 S. Pautot, B. J. Frisken and D. A. Weitz, *Proc. Natl. Acad. Sci. U. S. A.*, 2003, **100**, 10718–10721.
- 267 C. Martino, S.-H. Kim, L. Horsfall, A. Abbaspourrad, S. J. Rosser, J. Cooper and D. A. Weitz, *Angew. Chem., Int. Ed.*, 2012, **51**, 6416–6420.
- 268 H. C. Shum, Y.-J. Zhao, S.-H. Kim and D. A. Weitz, *Angew. Chem., Int. Ed.*, 2011, **50**, 1648–1651.
- 269 S.-H. Kim, J. Nam, J. W. Kim, D.-H. Kim, S.-H. Han and D. A. Weitz, *Lab Chip*, 2013, **13**, 1351–1356.
- 270 M. Weiss, J. P. Frohnmayer, L. T. Benk, B. Haller, J. W. Janiesch, T. Heitkamp, M. Borsch, R. B. Lira, R. Dimova, R. Lipowsky, E. Bodenschatz, J. C. Baret, T. Vidakovic-Koch, K. Sundmacher, I. Platzman and J. P. Spatz, *Nat. Mater.*, 2018, **17**, 89–96.
- 271 D. J. Paterson, J. Reboud, R. Wilson, M. Tassieri and J. M. Cooper, *Lab Chip*, 2014, **14**, 1806–1810.
- 272 Y. Elani, X. C. Solvas, J. B. Edel, R. V. Law and O. Ces, *Chem. Commun.*, 2016, **52**, 5961–5964.
- 273 B. Schlicht and M. Zagnoni, *Sci. Rep.*, 2015, **5**, 9951.
- 274 M. Schwarz-Schilling, L. Aufinger, A. Muckl and F. C. Simmel, *Integr. Biol.*, 2016, **8**, 564–570.
- 275 K. K. Ho, J. W. Lee, G. Durand, S. Majumder and A. P. Liu, *PLoS One*, 2017, **12**, e0174689.
- 276 D. Mark, S. Haeberle, G. Roth, F. von Stetten and R. Zengerle, *Chem. Soc. Rev.*, 2010, **39**, 1153–1182.
- 277 E. Amstad, S. S. Datta and D. A. Weitz, *Lab Chip*, 2014, **14**, 705–709.
- 278 H. F. Chan, S. Ma and K. W. Leong, *Regener. Biomater.*, 2016, **3**, 87–98.
- 279 D. Liu, H. Zhang, F. Fontana, J. T. Hirvonen and H. A. Santos, *Adv. Drug Delivery Rev.*, 2018, **128**, 54–83.
- 280 X. Y. Wang, Z. H. Jin, B. W. Gan, S. W. Lv, M. Xie and W. H. Huang, *Lab Chip*, 2014, **14**, 2709–2716.
- 281 A. Armada-Moreira, E. Taipaleenmaki, F. Itel, Y. Zhang and B. Stadler, *Nanoscale*, 2016, **8**, 19510–19522.